


CrystEngComm

Accepted Manuscript



This article can be cited before page numbers have been issued, to do this please use: C. Warakulwit, S. Yadnam, C. Boonyuen, C. Wattanakit, A. Karajic, P. Garrigue, N. Mano, D. Bradshaw, J. Limtrakul and A. Kuhn, *CrystEngComm*, 2016, DOI: 10.1039/C6CE00658B.

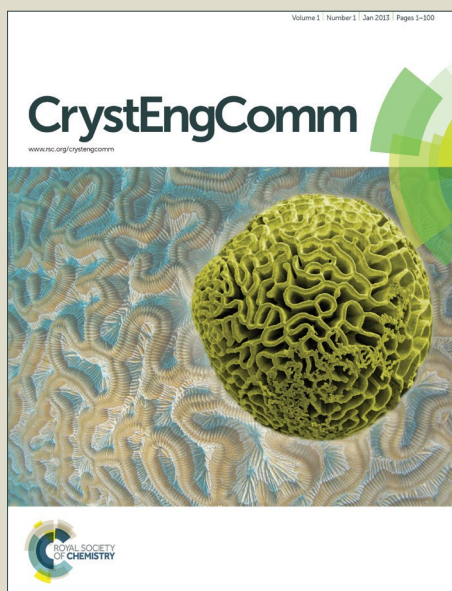

This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

ARTICLE

Elaboration of Metal Organic Framework Hybrid Materials with Hierarchical Porosity by Electrochemical Deposition-Dissolution

Chompunuch Warakulwit,^a Sudarat Yadnum,^b Chaiyan Boonyuen,^a Chularat Wattanakit,^f Aleksandar Karajic,^c Patrick Garrigue,^c Nicolas Mano,^d Darren Bradshaw,^e Jumras Limtrakul,^f and Alexander Kuhn^{*c}

Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/

Rationally designed hierarchical macro-/microporous HKUST-1 electrodes were prepared via an electrochemical deposition-dissolution technique with the motivation to overcome diffusion limits that are typically occurring for conventional microporous MOFs. A colloidal crystal of silica spheres was prepared by the Langmuir–Blodgett (LB) technique. Using this crystal as a template, macroporous copper electrodes with a controlled number of pore layers were prepared via electrodeposition. After the removal of the template, the synthesis of HKUST-1 was performed via partial anodic dissolution of the copper surface in the presence of the organic linker, leading to the deposition of the HKUST-1 on the electrode surface with the designed macroporous structure. The macroporous Cu electrodes do not only behave as structural template but are also the Cu source for the formation of MOFs. Applied potential and deposition time allow to fine-tune the characteristics of the porous layer. The developed synthesis is rapid, occurs under mild conditions and therefore opens up various potential applications including catalysis, separation and sensing based on these hierarchical materials.

Introduction

Metal-organic frameworks (MOFs) are crystalline and porous solid materials with a framework composed of metal ions and organic linkers.¹ Owing to their unique properties such as well-defined structures, uniform and stable pores, large pore volume, high surface area, and tuneable surface chemistry,¹ MOFs have been considered as interesting candidate materials for various applications including adsorption,² separation,²⁻⁴ capture,^{3,5} storage,⁶ biomedical imaging,⁷ drug delivery,⁸ catalysis,⁹ recognition,¹⁰ sensing,¹¹ and electronic devices.¹² MOFs have also been found to be of great importance in a large variety of electrochemical applications,¹³ and have been applied as materials for electrocatalysis,^{14, 15} electrochemical

sensing^{16, 17} and in supercapacitors.¹⁸ Recently, it has been reported that the method of synthesizing MOFs has an effect on their electrochemical behavior due to varying amounts of impurities and molecular guests in the final products.¹⁹ This illustrates that the choice of the synthetic route is of primary importance for the performance of the obtained material.

As conventional MOFs have sole micropores and large crystal sizes, many molecules with relatively large dimensions compared to the pore size of MOFs can experience severe diffusion limitations when penetrating the framework. In order to improve their performance, various synthetic strategies have been employed to create MOFs with pores of an increased size such as mesopores (2–50 nm) and macropores (>50 nm),^{20–24} thus allowing shorter diffusion path lengths when they are used as thin films, nanoaggregates or nanoparticles.^{20, 25–28} It also has been pointed out recently that structuring of MOFs in a hierarchical order opens up new opportunities to improve the material performance via the design of their physical form rather than altering the chemical components.²⁹ However to the best of our knowledge, there are so far no reports on the electrochemical synthesis of MOFs with the goal of obtaining a well-defined higher order porosity, which can be crucial for their integration into practical devices.^{30–33} Such well-organized hierarchical pore architectures would allow a straight forward access to thin films of MOFs with a high microstructural homogeneity.

HKUST-1 is a MOF with a cubic framework structure and an open 3D pore system obtained by linking copper (II) (Cu²⁺)

^a Department of Chemistry, Faculty of Science, NANOTEC-KU Center of Excellence on Nanoscale Materials Design for Green Nanotechnology, Kasetsart University, Bangkok, 10900, Thailand.

^b Corporate Technology Office, The Siam Cement Public Company Limited, Bangkok, 10800, Thailand.

^c Univ. Bordeaux, CNRS UMR 5255, Bordeaux INP, ENSCBP, 33607 Pessac Cedex, France.

^d Centre de Recherche Paul Pascal, UPR 8641, CNRS - University of Bordeaux, Avenue Albert Schweitzer, 33600 Pessac, France


^e School of Chemistry, University of Southampton, Highfield, Southampton, SO17 1BJ, UK.

^f School of Energy Science and Engineering & School of Molecular Science and Engineering, Vidyasirimedhi Institute of Science and Technology, Rayong 21210, Thailand

^{*} Electronic Supplementary Information (ESI) available: General experimental synthesis and characterization protocols. See DOI: 10.1039/x0xx00000x

paddlewheel dimers and 1,3,5-benzenetricarboxylic acid (BTC) ligands.³⁴ HKUST-1 (Cu-BTC or $\text{Cu}_3(\text{BTC})_2$) has Lewis acid Cu sites that are accessible for molecules, thus offering various applications ranging from gas adsorption and separation,³⁵ to gas storage,^{36, 37} gas sensing,^{38, 39} catalysis,^{28, 40, 41} and electrocatalysis.¹⁵ Recently, HKUST-1 was synthesized via electrochemical routes,^{15, 42} and compared to other preparation methods, electrochemistry has several advantages including shorter operation times, milder conditions⁴³ and better control over the synthesis in a continuous manner.⁴⁴ In addition, it allows the direct formation of thin films, which are of particular interest for adsorption, catalysis, separation and sensing,⁴² using a rather simple elaboration strategy.⁴⁵

We present in this work a direct method for the fabrication of a three-dimensional (3D) hierarchically structured macro-/microporous HKUST-1 composite material via an electrochemical deposition/dissolution technique (Scheme 1). It is based on the use of a colloidal template composed of 1 μm -silica spheres of narrow size distribution prepared via the Langmuir-Blodgett (LB) technique, followed by electrodeposition of a precursor metal. Subsequently a thin film of HKUST-1 (thickness $\sim 1.5 \mu\text{m}$) with a well-defined inverse opal structure and a direct contact to the structured underlying metal phase was successfully prepared by controlled anodization. The obtained highly controllable structures open up new perspectives for MOFs in various applications due to improved transport properties in the supported MOF matrix.

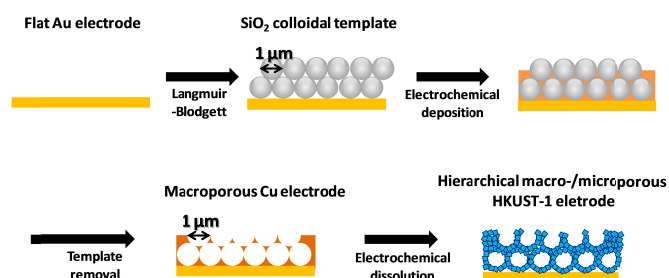

Scheme 1. Schematic illustration showing the experimental steps performed in this work for the synthesis of the hierarchical macro-/microporous HKUST-1.

Results and discussion

As suggested by cyclic voltammetry (CV) measurements, a suitable potential for Cu deposition is in the potential range from 0.00 V to -0.47 V. Before generating macroporous copper we first optimized the deposition conditions for a non-templated growth in order to identify which potential within this range leads to the smoothest copper deposit. Cu surfaces were generated with varying potentials ranging from -0.35 to -0.006 V (-0.35, -0.30, -0.25, -0.20, -0.05, -0.025, -0.012, and -0.006 V). Some SEM images of the corresponding samples are shown in Fig. 1. At relatively high negative potential values (-0.35 to -0.20 V), the Cu surfaces are not smooth (Fig. 1a-b) suggesting that the nucleation and growth of Cu is too fast.

However when increasing the potential to -0.05 V, a smooth Cu surface could be obtained (Fig. 1c), which is further confirmed by the cross section image of the film (Fig. 1d). An additional increase of applied potential to -0.025, -0.012 and -0.006 V does not result in a significant change of the smoothness of the surface. The SEM images of these samples (not shown) are comparable, only the thicknesses of the Cu layer is different. Therefore, we selected a potential of -0.05 V to generate the macroporous Cu electrodes required in the next step.

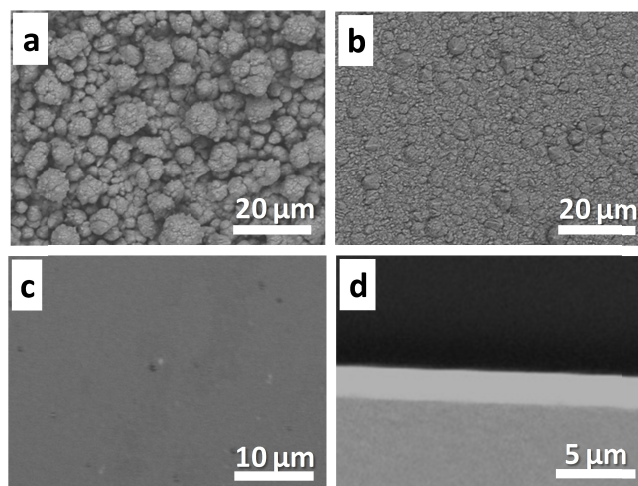


Fig. 1. Typical SEM images showing (a-c) the top-surface and (d) a cross-section of the Cu deposit using a Cu plating bath (CUBRAC 660) at various potentials: (a) -0.35, (b) -0.25 and (c-d) -0.05 V. The deposition time was 300 s.

For the formation of the macrostructured electrode, copper has been grown to a thickness corresponding to 3/2 silica bead layers. This should allow providing an ordered macroporous hybrid Cu/MOF film with a well-defined and open pore structure. The deposition time needed for reaching such a thickness was estimated by performing the Cu deposition on a smooth surface at a constant potential of -0.05 V.

Fig. 2 shows the SEM images of the deposited macroporous Cu obtained after the removal of the silica template with hydrofluoric acid. As expected, the layer thickness of Cu was found to increase with increasing deposition time. For a relatively short deposition time of 300 s, although the porous character is visible, it is not possible to create well-ordered pores under these conditions (data not shown). Increasing the deposition time to 700 s allows observing ordered macropores in the top view, but the cross sectional SEM image shows that the thickness of the Cu deposit is less than 1/2 of a silica bead layer. With a deposition time of 900 s, a complete 1/2 layer of Cu pores is obtained (Fig. 2a-b). The macropores were found to have a highly-organized hexagonal arrangement corresponding to a well-defined inverse opal structure. The pore diameter corresponds to the diameter of the silica template particles, analogous to what has been reported for other macroporous metal electrodes.^{46, 47} For a deposition time of 2300 s, the desired ordered Cu macropores with a 3/2 layer thickness are obtained (Fig. 2c-d). For this reason, we used a deposition time of 2300 s and a potential of -0.05 V for the synthesis of all the Cu

electrodes employed as starting materials for the preparation of structured MOF.

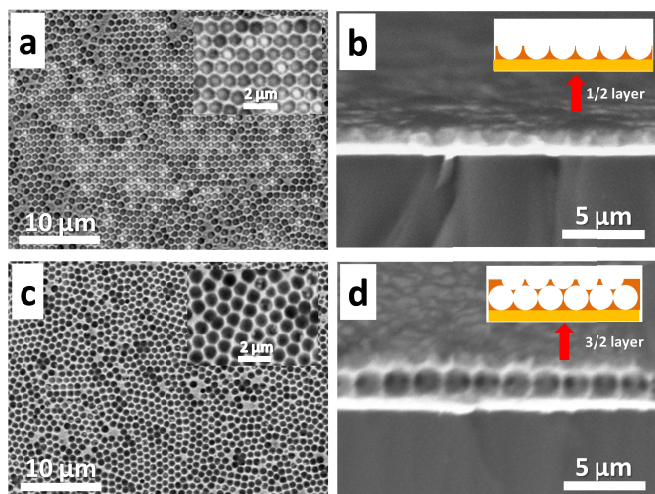


Fig. 2. Low and high (inset) magnification SEM images showing the top-surface of the ordered macroporous Cu electrodes (a,c) after the removal of the colloidal crystal template, obtained for an applied potential of -0.05 V but with various deposition times of (a) 900 and (c) 2300 s. Cross section images of deposits with a thickness of 1/2 and 3/2 layers of pores are shown in (b) and (d) for respective deposition times of 900 and 2300 s.

In order to optimize the conditions for the transformation of metallic Cu into HKUST-1, Au-coated slides modified with a flat Cu layer having a thickness equal to the one of the desired porous electrodes ($\sim 1.5 \mu\text{m}$) were first used. The electrodes were pretreated in 10% H_2SO_4 for 15 min before their use as working electrode. A silver wire and a platinum mesh were employed as the pseudo reference and counter electrodes, respectively. A solution of 0.05 M BTC in ethanol with 0.2 M tributylmethylammonium methylsulfate (MTBS) as a supporting salt was used as the electrolyte.

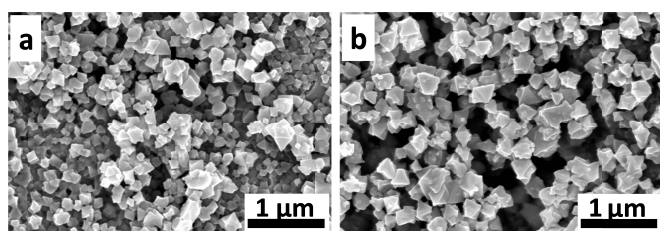


Fig. 3. SEM images showing the MOF products formed on flat Cu surfaces via electrochemical dissolution for different potentials, (a) 0.125 and (b) 0.5 V, but using the same reaction time (300 s) in a solution of 0.05 M BTC in ethanol containing 0.2 M MTBS supporting electrolyte.

The transformation of Cu into HKUST-1 was carried out for a constant time (300 s) but with varying potentials of 0.125, 0.25 and 0.5 V. By using a potential of 0.125 or 0.25 V, the obtained products were microcrystalline in character (Fig. 3a). When

increasing the applied potential to 0.5 V, the size of the crystals with an octahedral block-like shape increases (Fig. 3b). This finding corresponds well to previous literature reports for electrochemically deposited HKUST-1.^{43, 48} For this reason, we used 0.5 V for the further transformation of Cu into HKUST-1.

In the next optimization step, we tried to understand the influence of the deposition time on the product characteristics. Figures 4a-c show SEM images of HKUST-1 formed on the Cu surface at a constant potential of 0.5 V, but for various times. The products look more crystalline, the octahedral crystal structure becomes better defined, and the size of the crystals increases from one hundred nanometers to a few micrometers when increasing the deposition time from 60 s to 1800 s.

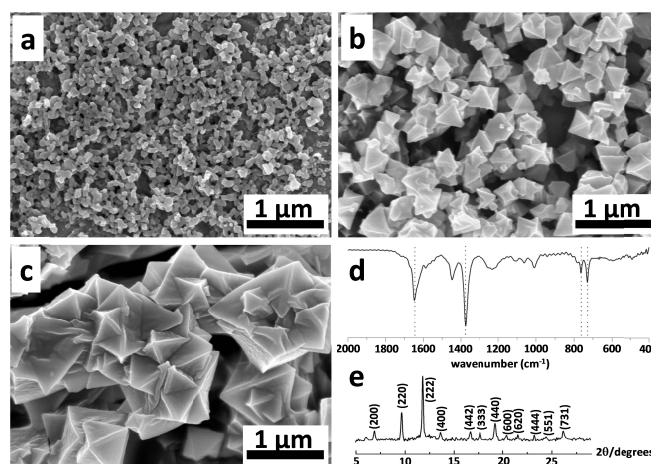


Fig. 4. (a-c) SEM images showing the MOF products formed on flat Cu surfaces via its electrochemical dissolution at 0.5 V for various times: (a) 60, (b) 600 and (c) 1800 s in a solution of 0.05 M BTC in ethanol containing 0.2 M MTBS supporting electrolyte. (d) FTIR and (e) XRD patterns recorded with the 1800s sample confirming the HKUST-1 structure.

The HKUST-1 deposits obtained after a reaction time of 1800s were subsequently characterized by FTIR and XRD. For IR (Fig. 4d), the band in the range of $1560\text{--}1440 \text{ cm}^{-1}$ is assigned to the asymmetric stretching vibrations of the BTC carboxylate groups. The symmetric vibrations centered at 1370 cm^{-1} and the peaks at 730 and 760 cm^{-1} are assigned to the phenyl group in the HKUST-1 structure. Most importantly, the band at $1690\text{--}1730 \text{ cm}^{-1}$, which is assigned to the acidic C=O stretching vibration, characteristic for the free BTC linker, was not found, thus suggesting the complete deprotonation during the complexation of the linker molecules with the Cu^{2+} ions.⁴⁹ For XRD (Fig. 4e), the diffraction peak positions and the relative diffraction intensities of the XRD pattern of the 1800s sample correspond well to what has been reported for HKUST-1 in the literature,⁵⁰ thus confirming the successful preparation of HKUST-1 under these conditions.

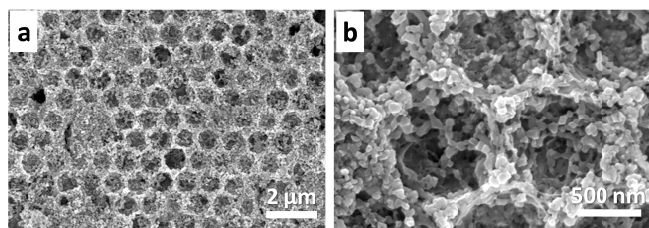


Fig. 5. (a) Low and high-magnification SEM images showing the top view of the macroporous Cu electrodes with 3/2 layers of pores after the MOF formation at a constant oxidation potential of 0.5 V and a reaction time of 60 s in a solution of 0.05 M BTC in ethanol containing 0.2 M MTBS supporting electrolyte.

After this initial screening of the experimental conditions we prepared HKUST-1 directly on the surface of macroporous Cu electrodes with 3/2 pore layers. A relatively short deposition time of 60 s was chosen in order to ensure that the macroporous copper will transform only partly into HKUST-1, thus preserving the underlying macroporous architecture. Application of a potential of 0.5 V triggers the electrochemical oxidation of Cu^0 to Cu^{2+} via several intermediate steps which have been recently investigated in detail.⁵¹ The produced Cu^{2+} species interact with the BTC molecules in the solution leading to an observable precipitation of solid material with its characteristic blue color, similar to what has been observed previously.⁵² Although the SEM images reveal the uniform distribution of HKUST-1 on the surface of the macroporous electrode with a morphology similar to what has been obtained in the case of flat Cu-coated electrodes, Fig. 5 nevertheless indicates an important alteration of the macropores due to the extensive formation of HKUST-1. In order to prevent this too rapid erosion and better preserve the originally designed macropores, the applied potential was decreased to 0.125 V for subsequent experiments.

The SEM images of Fig. 6a-f show the top-surface of the electrode after the anodic dissolution process at this lower potential of 0.125 V for various experimental times ranging from 30 s to 120 s. In this case the originally designed macroporous structure could be entirely preserved. As expected, the amount of MOF and its morphology vary when changing the deposition time, analogous to experimental observations on flat electrodes. The amount of the MOF product increases and the crystal facets are better defined with increasing deposition time. The obtained results indicate the successful preparation of a hierarchical macroporous HKUST-1 composite electrode via the currently employed technique. It should be noted that the desired hierarchically structured Cu/HKUST-1 composite electrode can be obtained in a relatively short reaction time (< 120 s), thus the employed approach is straight forward and rapid. The cross sectional image of the 60s sample (Fig. 6g) also confirms the preservation of the originally designed macroporous structure. AFM images further indicate the presence of MOF (white deposit in Fig. S4), although it is difficult to resolve its microstructure due to the high aspect ratio of the pores and the crystallites.

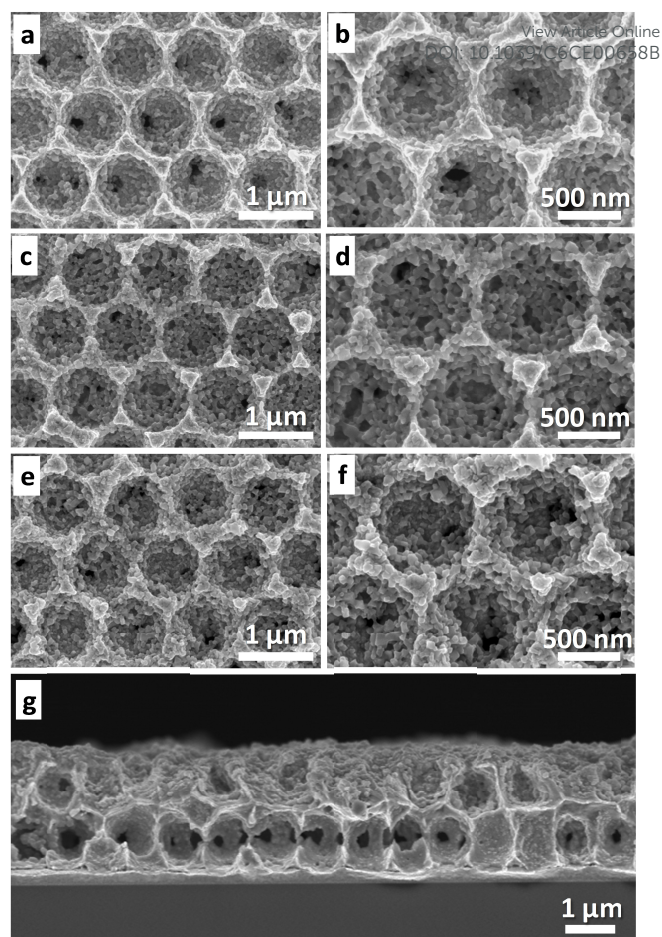


Fig. 6. (a-f) Top view SEM images at low and high magnifications showing the MOF products formed on the walls of the ordered macroporous Cu electrodes (3/2 layers of pores), via the oxidation at 0.125 V for various reaction times (a-b) 30 s, (c-d) 60 s and (e-f) 120 s in a solution of 0.05 M BTC in ethanol containing 0.2 M MTBS supporting electrolyte. (g) Typical cross sectional image obtained for the 60s samples.

Conclusions

Rationally designed hierarchical macro-/microporous HKUST-1 composite electrodes were prepared via an electrochemical deposition-dissolution technique. Silica spheres were first used to prepare a colloidal crystal template by the Langmuir-Blodgett technique. Macroporous copper electrodes with a controlled thickness were obtained via electrodeposition. After removal of the template, the synthesis of HKUST-1 was performed via the partial anodic dissolution of the copper surface in the presence of the organic linker, leading to the formation of the MOF on the electrode surface. The macroporous Cu electrodes do not only behave as a structural template, but also as a metal source for the formation of the MOF. The applied potential and deposition time play important roles for the structural characteristics of the final product. Therefore these parameters were optimized in order to transform only partially the well-organized macroporous Cu electrodes into a macroporous MOF

architecture. We found that the desired hierarchically structured Cu/HKUST-1 composite electrode can be obtained in a relatively short reaction time (< 120 s) at an optimized potential of 0.125 V. Thus, the employed technique is not time-consuming, uses only very mild electrochemical conditions and is easy to implement. It therefore represents an interesting enrichment of the already existing tool-box employed to generate structured high performance MOF layers.^{53,54} Even though we exemplified the approach in the present work with only one type of MOF, the method should be easily transposable to all other MOFs that can be electrochemically generated by anodic dissolution.³⁰ The obtained composite structures should allow using these materials advantageously when diffusional transport problems would otherwise be a limiting factor, as it might be the case for several applications including catalysis, sensing or separation and storage of gases.⁵⁵

Acknowledgements

We wish to thank Dr. Stephane Reculusa for helpful discussion. The Thailand Research Fund (TRF) is acknowledged for a Royal Golden Jubilee Ph.D. Fellowship (3.C.KU/51/A.1) and the French Government for its contribution to the Ph.D. co-tutelle program. The National Nanotechnology Center (NANOTEC), National Science and Technology Development Agency, Thailand is also acknowledged (for NANOTEC Center for Nanoscale Materials Design for Green Nanotechnology). DB thanks the European Research Council (ERC) for financial support (BIOMOF-258613). AK acknowledges support from the Institut Universitaire de France. Partial support has also been obtained within the frame of the Laboratory of Excellence AMADEus with the reference ANR-10-LABX-0042-AMADEUS.

Notes and references

- 1 S. Kitagawa, R. Kitaura and S. Noro, *Angewandte Chemie-International Edition*, 2004, **43**, 2334-2375.
- 2 J.-R. Li, R. J. Kuppler and H.-C. Zhou, *Chemical Society Reviews*, 2009, **38**, 1477-1504.
- 3 Y. S. Bae and R. Q. Snurr, *Angewandte Chemie-International Edition*, 2011, **50**, 11586-11596.
- 4 J. R. Li, J. Sculley and H. C. Zhou, *Chemical Reviews*, 2012, **112**, 869-932.
- 5 K. Sumida, D. L. Rogow, J. A. Mason, T. M. McDonald, E. D. Bloch, Z. R. Herm, T. H. Bae and J. R. Long, *Chemical Reviews*, 2012, **112**, 724-781.
- 6 N. L. Rosi, J. Eckert, M. Eddaoudi, D. T. Vodak, J. Kim, M. O'Keeffe and O. M. Yaghi, *Science*, 2003, **300**, 1127-1129.
- 7 J. Della Rocca, D. M. Liu and W. B. Lin, *Accounts of Chemical Research*, 2011, **44**, 957-968.
- 8 P. Horcajada, R. Gref, T. Baati, P. K. Allan, G. Maurin, P. Couvreur, G. Férey, R. E. Morris, C. Serre, *Chemical Reviews*, 2012, **112**, 1232-1268.
- 9 J. Lee, O. K. Farha, J. Roberts, K. A. Scheidt, S. T. Nguyen and J. T. Hupp, *Chemical Society Reviews*, 2009, **38**, 1450-1459.
- 10 B. L. Chen, S. C. Xiang and G. D. Qian, *Accounts of Chemical Research*, 2010, **43**, 1115-1124.
- 11 Z. C. Hu, B. J. Deibert and J. Li, *Chemical Society Reviews*, 2014, **43**, 5815-5840.
- 12 V. Stavila, A. A. Talin and M. D. Allendorf, *Chemical Society Reviews*, 2014, **43**, 5994-6010.
- 13 A. Morozan and F. Jaouen, *Energy & Environmental Science*, 2012, **5**, 9269-9290. DOI: 10.1039/C6CE00658B
- 14 J. J. Mao, L. F. Yang, P. Yu, X. W. Wei and L. Q. Mao, *Electrochemistry Communications*, 2012, **19**, 29-31.
- 15 R. Senthil Kumar, S. Senthil Kumar and M. Anbu Kulandainathan, *Electrochemistry Communications*, 2012, **25**, 70-73.
- 16 Y. Wang, Y. C. Wu, J. Xie and X. Y. Hu, *Sensors and Actuators B-Chemical*, 2013, **177**, 1161-1166.
- 17 H. Hosseini, H. Ahmar, A. Dehghani, A. Bagheri, A. Tadjarodi and A. R. Fakhari, *Biosensors & Bioelectronics*, 2013, **42**, 426-429.
- 18 R. Díaz, M. G. Orcajo, J. A. Botas, G. Calleja and J. Palma, *Materials Letters*, 2012, **68**, 126-128.
- 19 S. Loera-Serna, M. A. Oliver-Tolentino, M. de Lourdes López-Núñez, A. Santana-Cruz, A. Guzmán-Vargas, R. Cabrera-Sierra, H. I. Beltrán and J. Flores, *Journal of Alloys and Compounds*, 2012, **540**, 113-120.
- 20 A. Demessence, P. Horcajada, C. Serre, C. Boissiere, D. Grosso, C. Sanchez and G. Férey, *Chemical Communications*, 2009, 7149-7151.
- 21 Y. F. Yue, Z. A. Qiao, P. F. Fulvio, A. J. Binder, C. C. Tian, J. H. Chen, K. M. Nelson, X. Zhu and S. Dai, *Journal of the American Chemical Society*, 2013, **135**, 9572-9575.
- 22 H. L. Jiang, Y. Tatsu, Z. H. Lu and Q. Xu, *Journal of the American Chemical Society*, 2010, **132**, 5586-+.
- 23 J. Park, Z. Y. U. Wang, L. B. Sun, Y. P. Chen and H. C. Zhou, *Journal of the American Chemical Society*, 2012, **134**, 20110-20116.
- 24 D. Bradshaw, S. El-Hankari and L. Lupica-Spagnolo, *Chemical Society Reviews*, 2014, **43**, 5431-5443.
- 25 O. Shekhah, J. Liu, R. A. Fischer and C. Woll, *Chemical Society Reviews*, 2011, **40**, 1081-1106.
- 26 T. Yokamoto, S. Yamazoe, R. Takahata, J.-i. Nishigaki, A. Thivasasith, J. Limtrakul and T. Tsukuda, *ACS Catalysis*, 2014, **4**, 3696-3700.
- 27 R. Makiura, S. Motoyama, Y. Umemura, H. Yamanaka, O. Sakata and H. Kitagawa, *Nature Materials*, 2010, **9**, 565-571.
- 28 D. Jiang, T. Mallat, F. Krumeich and A. Baiker, *Catalysis Communications*, 2011, **12**, 602-605.
- 29 S. Furukawa, J. Reboul, S. Diring, K. Sumida and S. Kitagawa, *Chemical Society Reviews*, 2014, **43**, 5700-5734.
- 30 H. Al-Kutubi, J. Gascon, E. J. R. Sudhölter and L. Rassaei, *ChemElectroChem*, 2015, **2**, 462-474.
- 31 J. Reboul, S. Furukawa, N. Horike, M. Tsotsalas, K. Hirai, H. Uehara, M. Kondo, N. Louvain, O. Sakata and S. Kitagawa, *Nat Mater*, 2012, **11**, 717-723.
- 32 P. Falcaro, R. Ricco, C. M. Doherty, K. Liang, A. J. Hill and M. J. Styles, *Chemical Society Reviews*, 2014, **43**, 5513-5560.
- 33 N. Campagnol, T. R. C. Van Assche, M. Li, L. Stappers, M. Dinca, J. F. M. Denayer, K. Binnemans, D. E. De Vos and J. Fransaer, *Journal of Materials Chemistry A*, 2016, **4**, 3914-3925.
- 34 S. S.-Y. Chui, S. M.-F. Lo, J. P. H. Charmant, A. G. Orpen and I. D. Williams, *Science*, 1999, **283**, 1148-1150.
- 35 Q. Yang, C. Xue, C. Zhong and J.-F. Chen, *AIChE Journal*, 2007, **53**, 2832-2840.
- 36 P. Krawiec, M. Kramer, M. Sabo, R. Kunschke, H. Fröde and S. Kaskel, *Advanced Engineering Materials*, 2006, **8**, 293-296.
- 37 K.-S. Lin, A. K. Adhikari, C.-N. Ku, C.-L. Chiang and H. Kuo, *International Journal of Hydrogen Energy*, 2012, **37**, 13865-13871.
- 38 J. A. Mason, M. Veenstra and J. R. Long, *Chemical Science*, 2014, **5**, 32-51.
- 39 P. Davydovskaya, A. Ranft, B. V. Lotsch and R. Pohle, *Procedia Engineering*, 2014, **87**, 1433-1436.
- 40 N. B. Pathan, A. M. Rahatgaonkar and M. S. Chorghade, *Catalysis Communications*, 2011, **12**, 1170-1176.

- 41 A. Sachse, R. Ameloot, B. Coq, F. Fajula, B. Coasne, D. De Vos and A. Galarneau, *Chemical Communications*, 2012, **48**, 4749-4751.
- 42 T. R. C. Van Assche, N. Campagnol, T. Muselle, H. Terryn, J. Fransaer and J. F. M. Denayer, *Microporous and Mesoporous Materials*, 2012, **224**, 302-310.
- 43 R. Ameloot, L. Stappers, J. Fransaer, L. Alaerts, B. F. Sels and D. E. De Vos, *Chemistry of Materials*, 2009, **21**, 2580-2582.
- 44 A. Martinez Joaristi, J. Juan-Alcañiz, P. Serra-Crespo, F. Kapteijn and J. Gascon, *Crystal Growth & Design*, 2012, **12**, 3489-3498.
- 45 A. Bétard and R. A. Fischer, *Chemical Reviews*, 2012, **112**, 1055-1083.
- 46 P. N. Bartlett, P. R. Birkin and M. A. Ghanem, *Chemical Communications*, 2000, 1671-1672.
- 47 M. Heim, S. Reculosa, S. Ravaine and A. Kuhn, *Advanced Functional Materials*, 2012, **22**, 538-545.
- 48 T. R. C. Van Assche, G. Desmet, R. Ameloot, D. E. De Vos, H. Terryn and J. F. M. Denayer, *Microporous and Mesoporous Materials*, 2012, **158**, 209-213.
- 49 F. Wang, H. Guo, Y. Chai, Y. Li and C. Liu, *Microporous and Mesoporous Materials*, 2013, **173**, 181-188.
- 50 Y. Mao, L. Shi, H. Huang, W. Cao, J. Li, L. Sun, X. Jin and X. Peng, *Chemical Communications*, 2013, **49**, 5666-5668.
- 51 P. Schäfer, M. A. van der Veen and K. F. Domke, *Chemical Communications*, 2016, **in press**, DOI: 10.1039/C6CC00534A
- 52 S. Yadnum, J. Roche, E. Lebraud, P. Négrier, P. Garrigue, D. Bradshaw, C. Warakulwit, J. Limtrakul and A. Kuhn, *Angewandte Chemie International Edition*, 2014, **53**, 4001-4005.
- 53 P. Falcato, D. Buso, A.J. Hill, C.M. Doherty, *Advanced Materials* 2012, **24**, 3153-3168
- 54 Y. Wu, F. Li, W. Zhu, J. Cui, C. Tao, C. Lin and P. M. Hannam, G. Li, *Angewandte Chemie International Edition*, 2011, **50**, 12518-12522.
- 55 S.T. Meek, J.A. Greathouse and M.D. Allendorf, *Advanced Materials*, **2011**, **23**, 249-267.

The table of contents

Rationally designed MOF materials with hierarchical porosity are prepared via an electrochemical deposition-dissolution technique. First, macroporous copper electrodes with a controlled number of pore layers are obtained by electrodeposition of copper in a colloidal crystal of silica spheres acting as structural template. Their subsequent electrooxidation provides the copper ions for the formation of highly organized hybrid Cu/HKUST-1 layers.

