

Random access actuation of nanowire grid metamaterial

This content has been downloaded from IOPscience. Please scroll down to see the full text.

2016 Nanotechnology 27 485206

(<http://iopscience.iop.org/0957-4484/27/48/485206>)

View [the table of contents for this issue](#), or go to the [journal homepage](#) for more

Download details:

IP Address: 152.78.209.22

This content was downloaded on 08/11/2016 at 09:58

Please note that [terms and conditions apply](#).

You may also be interested in:

[Roadmap on optical metamaterials](#)

Augustine M Urbas, Zubin Jacob, Luca Dal Negro et al.

[Tunable and nonlinear metamaterials: toward functional metadevices](#)

Yuri S Kivshar

[Exploiting metamaterials, plasmonics and nanoantennas concepts in silicon photonics](#)

Francisco J Rodríguez-Fortuño, Alba Espinosa-Soria and Alejandro Martínez

[Recent advances on optical metasurfaces](#)

Yang Zhao, Xing-Xiang Liu and Andrea Alù

[Engineering metallic nanostructures for plasmonics and nanophotonics](#)

Nathan C Lindquist, Prashant Nagpal, Kevin M McPeak et al.

[Electrical characterization of suspended gold nanowire bridges](#)

Zhiwei Zou, Junhai Kai and Chong H Ahn

[Manipulation and TEM characterization of nanostructures using a nanogripper](#)

Alberto Cagliani, Rafal Wierzbicki, Luigi Occhipinti et al.

Random access actuation of nanowire grid metamaterial

Pablo Cencillo-Abad¹, Jun-Yu Ou¹, Eric Plum^{1,3}, João Valente^{1,4} and Nikolay I Zheludev^{1,2,3,5}

¹ Optoelectronics Research Centre and Centre for Photonic Metamaterials, University of Southampton, Highfield, Southampton, SO17 1BJ, UK

² Centre for Disruptive Photonic Technologies, School of Physical and Mathematical Sciences and The Photonics Institute, Nanyang Technological University, Singapore 637371, Singapore

E-mail: erp@orc.soton.ac.uk and niz@orc.soton.ac.uk

Received 26 August 2016, revised 10 October 2016

Accepted for publication 12 October 2016

Published 4 November 2016



CrossMark

Abstract

While metamaterials offer engineered static optical properties, future artificial media with dynamic random-access control over shape and position of meta-molecules will provide arbitrary control of light propagation. The simplest example of such a reconfigurable metamaterial is a nanowire grid metasurface with subwavelength wire spacing. Recently we demonstrated computationally that such a metadvice with individually controlled wire positions could be used as dynamic diffraction grating, beam steering module and tunable focusing element. Here we report on the nanomembrane realization of such a nanowire grid metasurface constructed from individually addressable plasmonic chevron nanowires with a $230 \text{ nm} \times 100 \text{ nm}$ cross-section, which consist of gold and silicon nitride. The active structure of the metadvice consists of 15 nanowires each $18 \mu\text{m}$ long and is fabricated by a combination of electron beam lithography and ion beam milling. It is packaged as a microchip device where the nanowires can be individually actuated by control currents via differential thermal expansion.

 Online supplementary data available from stacks.iop.org/nano/27/485206/mmedia

Keywords: reconfigurable metamaterial, nanowire, metadvice, nanoelectromechanical system

(Some figures may appear in colour only in the online journal)

Full active control over diffraction and focusing of light, beam steering and video holography require dynamic control over amplitude and phase of light with sub-wavelength resolution, i.e. a device where optical properties of points spaced by less than the wavelength of operation can be controlled independently. However, sub-wavelength

pixelation is out of reach for established spatial light modulator technologies based on digital micromirrors or liquid crystal cells that have a characteristic size of $10 \mu\text{m}$ [1–3] as well as deformable mirrors that have a typical actuator pitch of hundreds of microns. Opportunities for fast dynamic control over light with much higher resolution are now emerging in metamaterials, i.e. media that obtain enhanced or unusual optical properties from structuring with characteristic dimensions that are smaller than their wavelength range of operation. Approaches to achieving dynamic control over metamaterial properties can be grouped into three categories. (i) All-optical control over the light–matter interaction using multiple coherent light waves [4, 5], (ii) modification of the materials making up the metamaterial nanostructure, e.g. based on optical nonlinearities [6, 7], phase transitions [8] or electronic doping [9], and (iii) spatial rearrangement of

³ Author to whom any correspondence should be addressed

⁴ Present address: Department of Electronic & Electrical Engineering, University College London, Torrington Place, London, WC1E 7JE, UK.

⁵ Homepage: <http://www.nanophotonics.org.uk>.



Original content from this work may be used under the terms of the [Creative Commons Attribution 3.0 licence](https://creativecommons.org/licenses/by/3.0/). Any further distribution of this work must maintain attribution to the author(s) and the title of the work, journal citation and DOI.

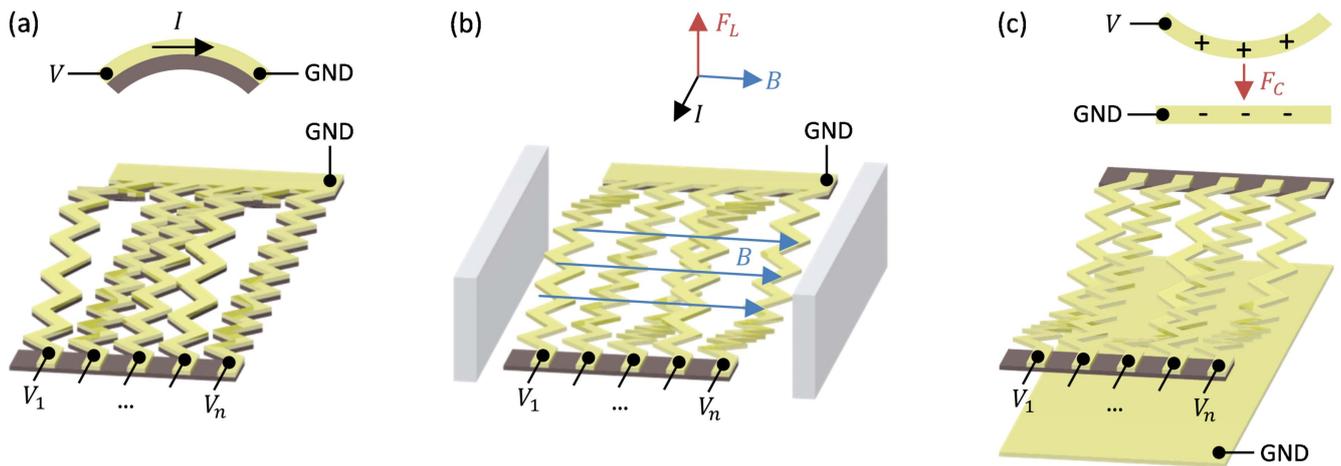


Figure 1. Random-access electrical actuation of reconfigurable nanowire metamaterials. (a) Electrothermal actuation, which is employed here, exploits differential thermal expansion of materials with different thermal expansion coefficients in response to resistive heating by a current I to displace a nanowire. (b) Magnetic actuation uses the Lorentz force F_L on moving charges to actuate a current-carrying metamaterial strip placed in an external magnetic field B . (c) Electrostatic actuation is driven by the Coulomb force F_C between charged nanowires or between a nanowire and a ground plane (GND). V_i indicate nanowire actuation voltages in all cases.

the metamaterial components [10–15]. However, dynamic control over metamaterial properties with sub-wavelength resolution remains a challenge. Spatial resolution of all-optical approaches involving coherent light–matter interactions, optical nonlinearities or phase transitions is limited by the ability to focus light, in contrast, this limitation is avoided by nanoelectromechanically actuated metamaterials, whose pixelation is determined by nanofabrication technology rather than light. It has been predicted that selective actuation of nanowires in nanowire grid metamaterials would enable spatial phase and intensity modulation with one-dimensional sub-wavelength pixelation providing focusing, diffraction and beam steering functionalities on demand [16, 17]. We refer to such metamaterials that allow selective control of each individual element as random access metamaterials.

Here we report the nanofabrication of a random access metadvice consisting of individually addressable plasmonic nanowire actuators. The nanowires are arranged in a grid, forming a metamaterial with a chevron-shaped unit cell. We demonstrate selective electrical actuation of individual nanowires, which allows the metamaterial nanostructure to be controlled with 620 nm pixelation in one dimension.

Reconfigurable metamaterials [14, 18–21] and similar optomechanical nanostructures [22–25] operating in the visible to near infrared part of the spectrum have been developed based on dielectric membranes of nanoscale thickness. Such membranes serve as a flexible support for a plasmonic metal or high index dielectric thin film, which can be structured by standard nanofabrication processes to create metamaterial nanostructures and actuators. Electrical actuation is most easily achieved by cutting a membrane with an electrically conductive layer into freestanding metamaterial strips. Deformation of such nanowires with microsecond scale response times can then be driven by Coulomb or Lorentz forces, or resistive heating, resulting in very large electro-optical and magneto-electro-optical effects [18–20].

Selective electrical actuation of individual nanowires requires the wires to be controlled by independent electrical signals. Bimorph nanowires can be actuated by resistive heating, where the same temperature change of materials with different thermal expansion coefficients causes nanowire deformation due to differential thermal expansion (figure 1(a)). Current-carrying nanowires can be actuated by the magnetic Lorentz force that acts on moving charges in a magnetic field (figure 1(b)). Electrically charged nanowires can be actuated by electrostatic forces due to a nearby plane (or neighboring wires) that has a different electric potential (figure 1(c)). Here we have chosen actuation of bimorph nanowires due to differential thermal expansion in response to resistive heating as this allows simultaneous nanowire observation by scanning electron microscopy. Prior work on electrically actuated nanowire grid metamaterials was limited to equal actuation of every second nanowire controlled by a total of two electrical terminals [18–20]. Here we report independent selective actuation of individual nanowires, which is required to enable spatial light modulation applications. In contrast to prior art, the number of nanoscale electrical terminals scales with the number of nanowires, and we address the resulting increase in complexity by combining multiple nanofabrication processes and introducing standard electronic packaging and standard electronic interfaces, as well as computer control.

We fabricated such an electrically addressable metamaterial nanostructure, starting with a commercially available (Norcada Inc, figure 2(a)) $250 \times 250 \mu\text{m}^2$ low stress silicon nitride membrane of 50 nm thickness. The membrane is supported by a $5 \times 5 \text{ mm}^2$ silicon frame with 32 electrodes and contact pads consisting of 50 nm thick gold with a chromium adhesive layer that were made by standard photolithography, metal deposition and lift-off processes.

In order to create the plasmonic metal film for metamaterial fabrication on the membrane and to transition from the 30 μm electrode spacing at the membrane edge to the sub-

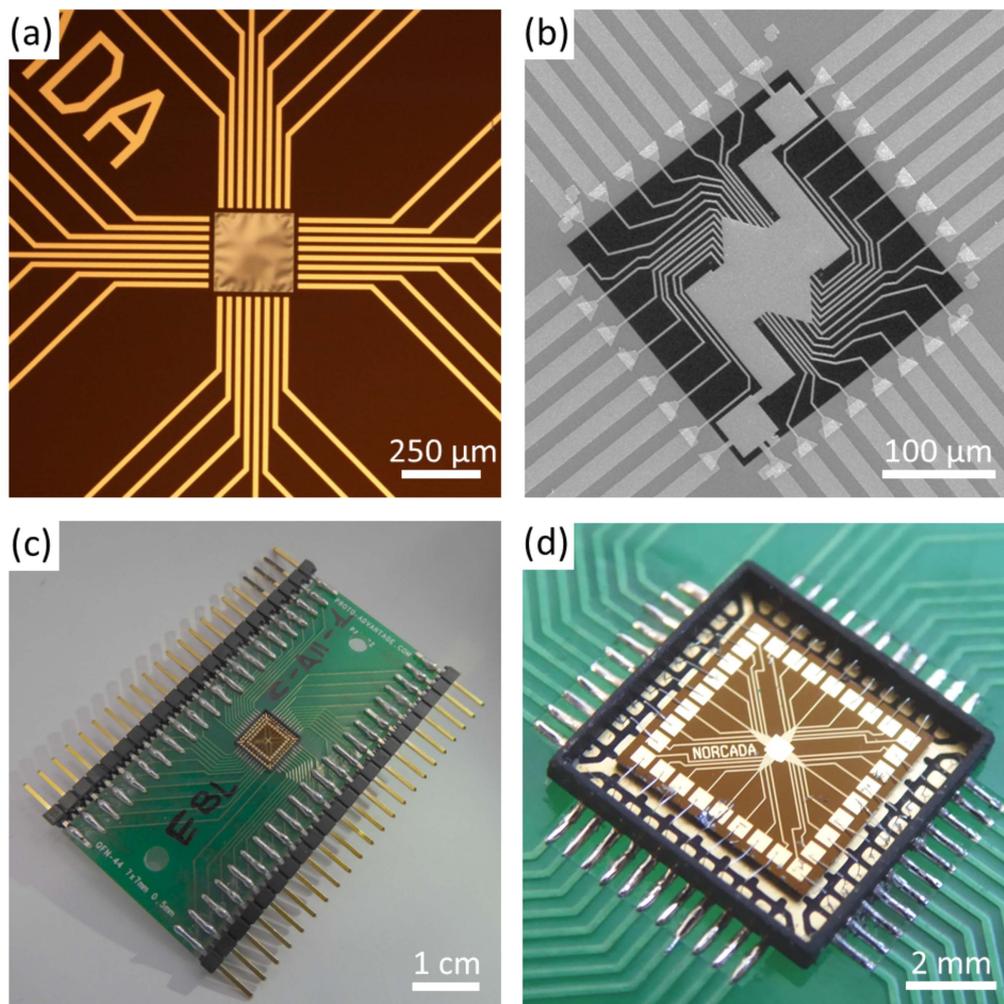


Figure 2. Contacting a nanomembrane. (a) Commercial $250 \times 250 \mu\text{m}^2$ silicon nitride membrane of 50 nm thickness on a $5 \times 5 \text{ mm}$ silicon frame with 32 electrodes. (b) Nanoscale gold contacts and gold areas for testing and metamaterial fabrication made by e-beam lithography. (c) Addressable metamaterial device placed in a standard QFN to DIP package. (d) Close-up image of the metamaterial device in the QFN carrier.

micron electrode spacing that is required at the metamaterial edge, we performed electron beam lithography (figure 2(b)). A $1 \mu\text{m}$ thick layer of poly(methyl methacrylate) e-beam resist was spin-coated onto the membrane chip, then the electrode pattern and areas for metamaterial fabrication were exposed by standard electron beam lithography. The electrode pattern was developed for 60 s in a 1:3 MIBK:IPA solution at room temperature, rinsed with IPA and dried with N_2 , followed by thermal evaporation of 50 nm of gold and subsequent lift-off.

In order to create a reliable and standardized electrical interface for the membrane chip, we used an open QFN (quad flat no-leads) chip carrier that had been surface-mounted by soldering to a QFN to DIP adapter (figure 2(c)). The membrane chip was attached inside the QFN chip carrier and the contact pads on the membrane frame were wire-bonded to the contacts of the chip carrier (figure 2(d)). The resulting chip assembly connects to a 16-way flat ribbon cable.

The metamaterial nanostructure was fabricated by gallium focused ion beam (FIB) milling and positioned relative to the e-beam lithography pattern using standard alignment

techniques (figure 3(a)). Fifteen freestanding $18\text{-}\mu\text{m}$ -long chevron nanowires with a $230 \text{ nm} \times 100 \text{ nm}$ cross-section were created by milling through both the gold and silicon nitride layers. Plasmonic chevron metamaterial strips were chosen for their suitability for electrothermal and magnetic actuation, their spring-like mechanical properties and their optical resonances [19, 20]. The chevron metamaterial unit cell is $600 \times 620 \text{ nm}^2$ in size, corresponding to an active metamaterial area of $18 \mu\text{m} \times 9 \mu\text{m}$ with a one-dimensional metamaterial pixelation of 620 nm (figure 3(b)). Then the electrical connections of the 13 central nanowires to the contacts of the e-beam lithography pattern were separated by manual FIB milling at a reduced dose in order to remove the gold layer while keeping the silicon nitride membrane intact to ensure structural integrity of the device.

In order to realize a computer-controlled ‘programmable’ metamaterial, the reconfigurable metamaterial was connected to a computer using a 16-channel digital-to-analog converter and a protective circuit that provides a $1 \text{ k}\Omega$ series resistor for each nanowire as well as grounding to avoid electrical shock to the nanostructure (figure 4(a)). A LabVIEW interface

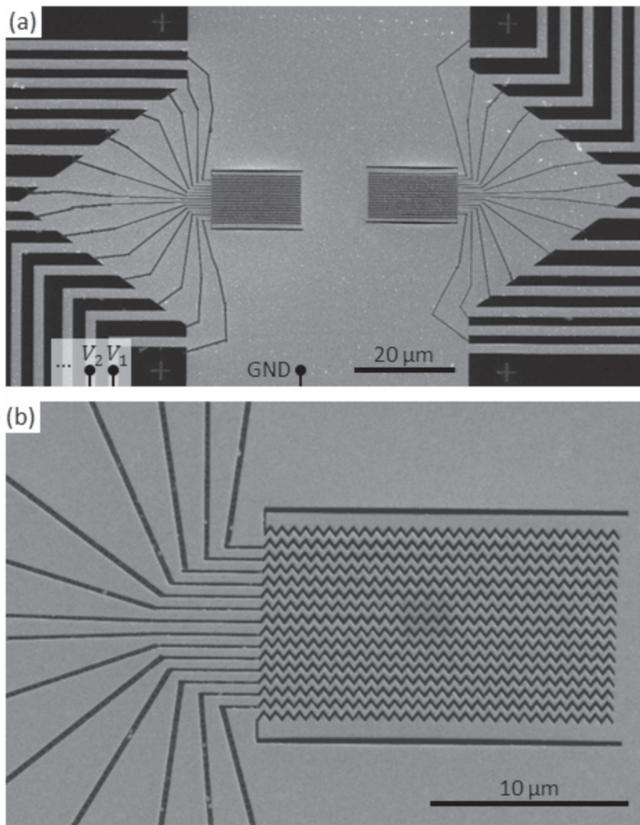


Figure 3. Addressable reconfigurable nanomembrane metadevices. (a) SEM image of the central membrane area with two contacted metadevices and alignment marks for automated FIB milling. V_i indicate electrical terminals for actuation of individual nanowires and GND indicates the common ground terminal. (b) High-resolution image of the nanowire grid metamaterial nanostructure.

allows computer-controlled actuation of individual metamaterial strips by setting the DAC output voltages.

Actuation of individual nanowires is illustrated by figures 4(b)–(d) and the online supplementary video, which show scanning electron micrographs of the central part of the metadvice at a viewing angle of 50° from the normal in order to visualize out-of-plane displacements of individual nanowires. The left and right panels show actuation of the third and fifth nanowires from the bottom with DAC control voltages of 3 V, while the middle panel shows a reference image without applied electrical signals. The nanowire resistance is small compared to the $1\text{ k}\Omega$ protective resistor, therefore, the nanowire actuation current is almost 3 mA, with $<9\text{ mW}$ ($<1\text{ mW}$) power dissipation per metamaterial strip including (excluding) the protective circuit. The movement of the actuated nanowires relative to their neighbors is clearly visible and corresponds to about 100 nm vertical displacement.

The actuation is caused by resistive heating of the nanowires, which leads to differential thermal expansion as the thermal expansion coefficient of gold ($14.2 \times 10^{-6}\text{ K}^{-1}$) is five times larger than that of silicon nitride ($2.8 \times 10^{-6}\text{ K}^{-1}$). Neglecting temperature variation along the wire for simplicity, the resulting displacement is proportional to $\Delta T \Delta \alpha L^2/t$, where the temperature change ΔT is proportional to the

square of the applied current, the difference in thermal expansion coefficients $\Delta \alpha$ depends on the chosen materials, and L and t correspond to nanowire length and thickness, respectively [26]. Therefore, larger nanowire displacements and lower current operation are most easily achieved with longer nanowires or by placing the metadvice in a static magnetic field in order to combine electrothermal actuation with magnetic actuation driven by the Lorentz force. We found in our experiments that currents exceeding 3 mA (about $3 \times 10^{11}\text{ A m}^{-2}$ current density) are likely to damage our metadvice due to reaching the melting point of gold in positions where fabrication imperfections cause the nanowire to have a smaller gold cross-section. The exact nanowire damage threshold depends on the gold film quality, nanofabrication accuracy as well as the nanowire dimensions, see [27] for a detailed study. Therefore, an increased range of nanowire displacement due to a larger temperature range would require higher nanofabrication accuracy, a cooled environment or replacement of gold with a conductive material that has a higher melting point. Potential thermal issues such as heat transfer between nanowires still need to be investigated and the overall current applied to the metadvice may need to be limited to avoid possible overheating during simultaneous actuation of all nanowires. Such thermal issues can be minimized by fabricating the metadvice on a smaller membrane so that the thick supporting frame that acts as a heat sink is located at the nanowire ends. Reducing the size of the membrane will also enhance the mechanical stability of the structure. The device packaging could be improved with a transparent anti-reflection-coated protective lid to create a sealed unit. The speed of the thermal actuation process is determined by the cooling timescale of the nanowires, which is on the order of $10\text{ }\mu\text{s}$ and scales with L^2 according to conductive cooling estimates, while faster actuation could be driven by magnetic and electrostatic forces as illustrated by figures 1(b) and (c).

Potential optical functionalities of such programmable metadevices have been studied numerically by references [16] and [17], which show that similar metadevices can modulate the phase or intensity of reflected light in one dimension by controlling either the optical path length or light absorption separately with each nanowire, enabling functionalities of gratings, phase-gradient metasurfaces and curved mirrors on demand and without unwanted diffracted beams for wavelengths of operation that exceed the nanowire period, here 620 nm. Our metadvice design is intended to operate in the red to infrared band at wavelengths λ longer than the nanowire period, but small compared to the overall size of the nanowire array, i.e. $620\text{ nm} < \lambda \ll 9\text{ }\mu\text{m}$. Beyond photonics, actuation of structured nanowires may also provide opportunities for manipulation of their thermal and phononic properties, which have been shown to depend on nanostructuring and strain [28].

In summary, we report the nanofabrication of an electrically addressable reconfigurable metadvice with 620 nm pixelation in one dimension. We demonstrate selective actuation of individual rows of metamaterial unit cells. Potential applications of such random access metadevices

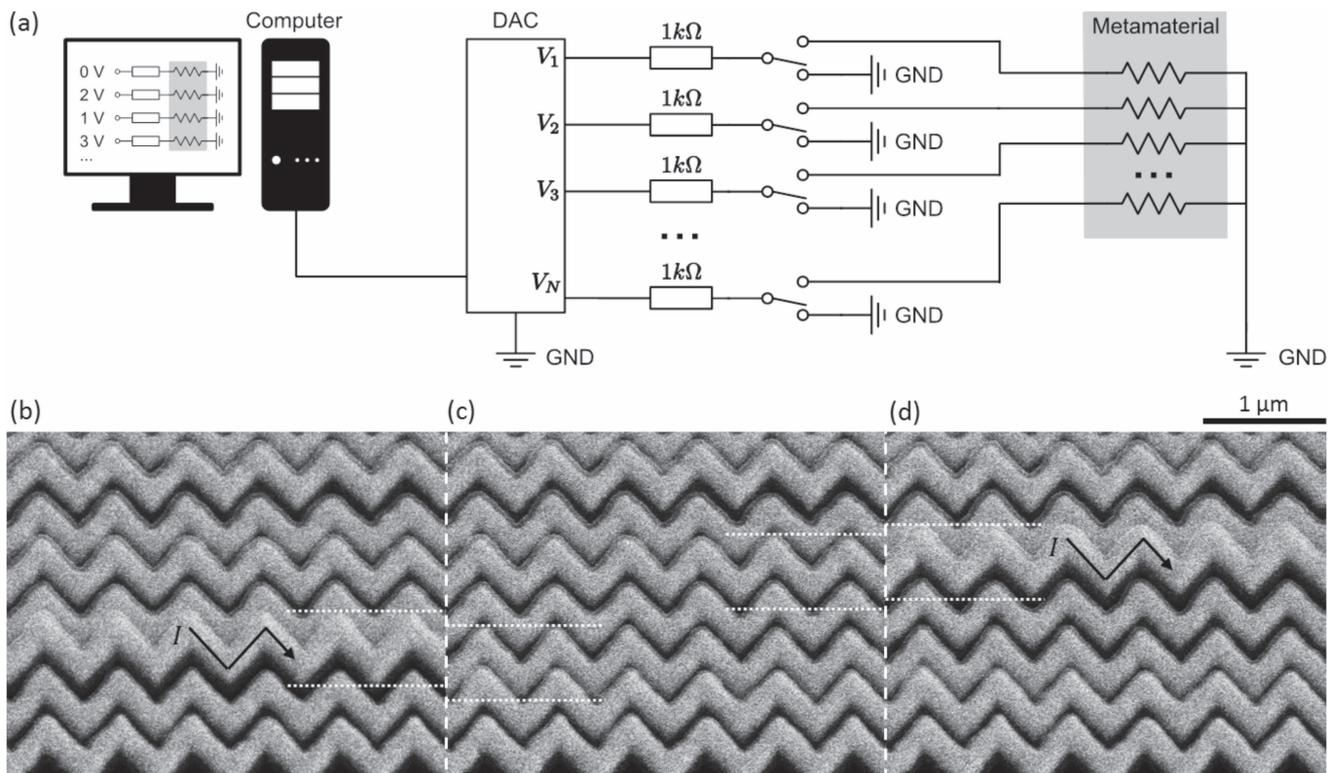


Figure 4. Selective electrical actuation of individual nanowires. (a) Schematic of the computer-controlled actuation circuit, where DAC indicates the digital-to-analog converter and GND indicates ground. (b)–(d) Strip actuation—SEM images showing the nanostructure at a viewing angle of 50° from the normal (b) with $V_3 = 3$ V applied to nanowire 3 from the bottom, (c) without voltage application and (d) with $V_5 = 3$ V applied to nanowire 5 from the bottom.

include spatial light modulators with sub-wavelength pixelation.

Acknowledgments

The authors thank Jeff Hooker for assistance with assembling the electronic interfaces. This work is supported by the Leverhulme Trust, the MOE Singapore (grant MOE2011-T3-1-005) and the UK Engineering and Physical Sciences Research Council (grants EP/G060363/1 and EP/M009122/1). The data from this paper can be obtained from the University of Southampton ePrints research repository: <http://dx.doi.org/10.5258/SOTON/399811>.

References

- [1] Efron U 1994 *Spatial Light Modulator Technology: Materials, Devices, and Applications* (Boca Raton, FL: CRC Press)
- [2] Lazarev G, Hermerschmidt A, Krüger S and Osten S 2012 LCOS spatial light modulators: trends and applications *Optical Imaging and Metrology: Advanced Technologies* (Weinheim: Wiley-VCH) pp 1–29
- [3] Yu H, Park J, Lee K, Yoon J, Kim K, Lee S and Park Y 2015 Recent advances in wavefront shaping techniques for biomedical applications *Curr. Appl. Phys.* **15** 632–41
- [4] Zhang J, MacDonald K F and Zheludev N I 2012 Controlling light-with-light without nonlinearity *Light Sci. Appl.* **1** e18
- [5] Papaioannou M, Plum E, Valente J, Rogers E and Zheludev N 2015 Two-dimensional control of light with light on metasurfaces *Light Sci. Appl.* **5** e16070
- [6] Cho D J, Wu W, Ponizovskaya E, Chaturvedi P, Bratkovsky A M, Wang S Y, Zhang X, Wang F and Shen Y R 2009 Ultrafast modulation of optical metamaterials *Opt. Express* **17** 17652–7
- [7] Dani K M, Ku Z, Upadhyaya P C, Prasankumar R P, Brueck S R J and Taylor A J 2009 Subpicosecond optical switching with a negative index metamaterial *Nano Lett.* **9** 3565–9
- [8] Driscoll T, Kim H T, Chae B G, Kim B J, Lee Y W, Jokerst N M, Palit S, Smith D R, Ventra M D and Basov D N 2009 Memory metamaterials *Science* **325** 1518–21
- [9] Huang Y-W, Lee H W H, Sokhoyan R, Pala R A, Thyagarajan K, Han S, Tsai D P and Atwater H A 2009 Gate-tunable conducting oxide metasurfaces *Nano Lett.* **16** 5319–25
- [10] Lapine M, Powell D, Gorkunov M, Shadrivov I, Marqués R and Kivshar Y 2009 Structural tunability in metamaterials *Appl. Phys. Lett.* **95** 084105
- [11] Tao H, Strikwerda A C, Fan K, Padilla W J, Zhang X and Averitt R D 2009 Reconfigurable terahertz metamaterials *Phys. Rev. Lett.* **103** 147401
- [12] Pryce I M, Aydin K, Kelaita Y A, Briggs R M and Atwater H A 2010 Highly strained compliant optical metamaterials with large frequency tunability *Nano Lett.* **10** 4222–7
- [13] Zhu W M *et al* 2011 Switchable magnetic metamaterials using micromachining processes *Adv. Mater.* **23** 1792–6

- [14] Ou J Y, Plum E, Jiang L and Zheludev N I 2011 Reconfigurable photonic metamaterials *Nano Lett.* **11** 2142–4
- [15] Zheludev N I and Plum E 2016 Reconfigurable nanomechanical photonic metamaterials *Nat. Nanotechnol.* **11** 16–22
- [16] Cencillo-Abad P, Plum E, Rogers E T F and Zheludev N I 2016 Spatial optical phase-modulating metadvice with subwavelength pixelation *Opt. Express* **24** 18790–8
- [17] Cencillo-Abad P, Zheludev N I and Plum E 2016 Metadvice for intensity modulation with sub-wavelength spatial resolution *Sci. Rep.* at press(arXiv:1610.06791)
- [18] Ou J Y, Plum E, Zhang J and Zheludev N I 2013 An electromechanically reconfigurable plasmonic metamaterial operating in the near-infrared *Nat. Nanotechnol.* **8** 252–5
- [19] Valente J, Ou J Y, Plum E, Youngs I J and Zheludev N I 2015 Reconfiguring photonic metamaterials with currents and magnetic fields *Appl. Phys. Lett.* **106** 111905
- [20] Valente J, Ou J Y, Plum E, Youngs I J and Zheludev N I 2015 A magneto-electro-optical effect in a plasmonic nanowire material *Nat. Commun.* **6** 7021
- [21] Karvounis A, Ou J Y, Wu W, MacDonald K F and Zheludev N I 2015 Nano-optomechanical nonlinear dielectric metamaterials *Appl. Phys. Lett.* **107** 191110
- [22] Thijssen R, Verhagen E, Kippenberg T J and Polman A 2013 Plasmon nanomechanical coupling for nanoscale transduction *Nano Lett.* **13** 3293–7
- [23] Thijssen R, Kippenberg T J, Polman A and Verhagen E 2014 Parallel transduction of nanomechanical motion using plasmonic resonators *ACS Photon.* **1** 1181–8
- [24] Yamaguchi K, Fujii M, Okamoto T and Haraguchi M 2014 Electrically driven plasmon chip: active plasmon filter *Appl. Phys. Express* **7** 012201
- [25] Thijssen R, Kippenberg T J, Polman A and Verhagen E 2015 Plasmomechanical resonators based on dimer nanoantennas *Nano Lett.* **15** 3971–6
- [26] Prasanna S and Spearing S M 2007 Materials selection and design of microelectrothermal bimaterial actuators *J. Microelectromech. Syst.* **16** 248–59
- [27] Karim S, Maaz K, Ali G and Ensinger W 2009 Diameter dependent failure current density of gold nanowires *J. Phys. D: Appl. Phys.* **42** 185403
- [28] Zhu T and Ertekin E 2015 Resolving anomalous strain effects on two-dimensional phonon flows: the cases of graphene, boron nitride, and planar superlattices *Phys. Rev. B* **91** 205429