

# **Ten years of severe plastic deformation (SPD) in Iran, part I: equal-channel angular pressing (ECAP)**

**E. Bagherpour<sup>\*1</sup>, M. Reihanian<sup>2</sup>, N. Pardis<sup>1</sup>, R. Ebrahimi<sup>1</sup>, Terence G. Langdon<sup>3,4</sup>**

*1. Department of Materials Science and Engineering, School of Engineering, Shiraz University, Shiraz, Iran*

*2. Department of Materials Science and Engineering, Faculty of Engineering, Shahid Chamran University of Ahvaz, Ahvaz, Iran*

*3- Materials Research Group, Faculty of Engineering and the Environment, University of Southampton, Southampton SO17 1BJ, UK*

*4- Departments of Aerospace & Mechanical Engineering and Materials Science, University of Southern California, Los Angeles, CA 90089-1453, USA*

## **Abstract**

The superior properties of ultrafine-grained materials fabricated by severe plastic deformation (SPD) has attracted the attention of many researchers around the world. Among the top ranked countries that are active in this field, Iran is interesting because of the late beginnings of SPD in this country and, subsequently, the highest rate of growth in the numbers of publications during the last decade. The first Iranian work published in the field of equal-channel angular pressing (ECAP) goes back to 2007 so that SPD research covers a period of only about ten years. Nevertheless, since that time there has been an increasing growth rate in the numbers of Iranian publications dealing with ECAP and especially the introduction of new methods based on ECAP and simulation of the method. The present overview is designed to summarize the main contributions from Iran in the field of ECAP processing.

---

<sup>\*</sup>Corresponding author, ebad. bagherpour@gmail.com; e.bagherpour@semnan.ac.ir

Tel.: +98 71 36133062; fax: +98 71 32307293

**Keywords: Severe plastic deformation; Equal-channel angular pressing; Ultrafine-grained materials; Mechanical properties**

## Contents

1. Introduction
2. ECAP materials in Iran
3. Processing by ECAP
  - 3.1. ECAP as a strain induced melt activation process
  - 3.2. ECAP as a consolidation method
4. Modeling and simulation
5. Special Characterization
  - 5.1. Microstructural non-uniformity during ECAP
  - 5.2. Superplasticity
  - 5.3. Corrosion
7. Summary and conclusions

Acknowledgments

References

## 1. Introduction

In the last 30 years, severe plastic deformation (SPD) has been considered as one of the best methods for fabrication of bulk nanostructured and ultrafine-grained materials [1]. In this period, several methods were introduced for imposing SPD to various materials with a major emphasis on equal-channel angular pressing (ECAP). Based on the Thomson Reuters Web of Science, around 4800 researchers from more than of 70 countries were involved in investigating and developing the various SPD methods. Although the first use of the ECAP technique dates back to 1981 [2], the use of this method among Iranian researchers started only from 2007 [3-5]. Despite the late start of SPD research in Iran, this country now ranks 8<sup>th</sup> in the world, 4<sup>th</sup> in Asia and 1<sup>st</sup> in the Middle East according to the total number of publications (NP). Analysis shows that Iranian scientists have published more than 470 documents (>5.5% of the total documents in this field). The initial work on SPD processing in Iran started with several studies on ECAP at Sharif University of Technology [3-8], Shiraz University [9-12], Tehran University [13-21] and Isfahan University of Technology [22,23]. For ECAP research, the position of Iran during the period of 2007-2017 was 6<sup>th</sup> in the world and 3<sup>rd</sup> in Asia. The sharp rise in the numbers of total publications in the field of SPD by Iranian scholars made this country 4<sup>th</sup> in the world in 2016 regarding the total NP in that year. Today, Iran is regularly ranked as having one of the highest NPs in the field of SPD in the world. Furthermore, the rank of Iran using the total numbers of citation, the average numbers of citation and the h-index is 12<sup>th</sup>, 17<sup>th</sup> and 13<sup>th</sup> in the world, respectively. This low rank of Iran, compared to its rank based on NP, may be due to the somewhat lower importance of research conducted in Iran and/or the low visibility of Iranian studies in SPD. However, it is interesting to note that the fraction of the proceeding papers

published by Iranians is about 200-300% lower than for other countries. Therefore, Iranians, unlike most others, have not widely attended conferences.

Iran also experiences a relatively lower number of collaborations compared with other countries and this can be attributed to two major reasons. The first reason is the low amount of research funding in Iran which is generally insufficient to cover conference fees. The second and most important reason is Iran sanctions which, since 1979, has led to numerous embargos and limitations [24, 25]. The consequence of these sanctions on the Iranian scientific community has been discussed in detail in the literature [26].

Referring to the above statistics and analyses, the importance of a study on the history and achievements in the field of SPD in Iran is needed due to the following factors. First, in 2016, Iran was ranked 4<sup>th</sup>, 2<sup>nd</sup> and 1<sup>st</sup> in the field of SPD (totally), and the specific SPD methods of equal-channel angular pressing (ECAP) [2] and accumulative roll bonding (ARB) [27], respectively. Second, since the collaboration and exchange of results and discussions between Iranian scholars and researchers from other countries is relatively low, at least by comparison with many other countries, an introduction to the flourishing of Iranian science after 10 years of SPD in this country will be of interest for all scientists in the SPD field as well as providing valuable information for scientists in many other disciplines. It is important also to know how a developing country like Iran has had the highest growth rate in a new and advanced field like SPD. Third, some new methods and many combinations and modifications of SPD methods have been invented or introduced by Iranian scholars. Until now, there are no review articles to classify and describe these methods and innovations. In a set of publication in the current journal which will be published sequentially, the critical achievements in the field of SPD

methods will be reviewed with special emphasis on the studies conducted in Iran. Each of these articles is dedicated to an individual topic where the current article concentrates on ECAP.

Equal-channel angular pressing (ECAP), named also as equal-channel angular extrusion (ECAE), was first introduced in 1981 by Segal et al. [2] in the former Soviet Union. The principle of this method is very well described in two reviews [28,29].

The principle of ECAP processing, and especially the overall implications of this processing technique, was reviewed previously by several researchers including in 2006 by Valiev et al. [30], in 2009 by Beyerlein and Tóth [31], in 2012 by Figueiredo and Langdon [32], in 2015 by Kawasaki and Langdon [33] and in 2016 by Valiev et al. [34]. To avoid repetition, the present section is focused specifically on those aspects that have not been sufficiently reviewed to date in an attempt to provide a historical summary of the achievements of Iranian scholars in ECAP with emphasis on the developments and innovations in this field from 2007.

## ***2. ECAPed materials in Iran***

As is apparent from Table 1, in Iran a variety of materials have been deformed by ECAP including aluminum alloys, copper alloys, steels, titanium alloys and magnesium alloys as well as different metal matrix composites. Among all of these materials, aluminum alloys account for about 40% of the publications in this field and they have attracted considerable attention. About 15%, 13%, 11%, 9% and 6% of the publications are focused on metal matrix composites, Mg alloys, steels, Cu alloys, and Ti alloys, respectively.

## ***4. Processing by ECAP***

In this section, we describe some applications of ECAP which are not well described in several earlier review articles [28,29,130-132].

#### ***4.1. ECAP as a strain-induced melt activation process***

Semi-solid metal processing is an alternative for conventional casting routes due to its lower cycle time, the possibility of increasing die life, the potential for a reduction in porosity and solidification shrinkage, improvements in the mechanical properties and so on [133]. Using this method, semi-solid billets with a spheroidal rather than a dendritic microstructure are formed to near net shaped products at the semi-solid temperature, referred to as a temperature between the liquidus and solidus. The first and the most important step in semi-solid processing is the preparation of semi-solid billets. Strain induced and melt activated (SIMA) is a good method to produce feedstocks, especially for active metals. In general, SIMA consists of two steps, a strain-induced step and a melt-activated step. For the strain-induced step, different processes such as rolling, forging, upsetting and extrusion can be used. The main restriction of all of these methods is the limitation in the degree of plastic deformation which is more critical for “hard to deform” materials like Mg and Ti alloys. In order to overcome the difficulties of plastic deformation in conventional methods, Jiang et al.[134] used ECAP as a SIMA process for semi-solid processing and concluded that it was valuable to include a strain-induced step. This new SIMA is a good method to prepare a semi-solid of the AZ91D alloy owing to its desirable microstructure with fine spheroidal grains and its high mechanical properties of formed components at both room and elevated temperatures. Shortly after this research, Liang et al. [135] showed that two passes of ECAP could provide sufficient strain to achieve fine and globular grains for the semi-solid forming of an AZ91 alloy. At the same time, Ashouri et al. [13], investigated the microstructural changes of an aluminum A356 alloy fabricated by semi-solid processing using ECAP. They proposed a model for the semi-solid structure formation of ECAP specimens as shown in Fig. 1.

The initial as-cast dendritic microstructure is changed to an elongated shape with a banded structure after ECAP. During reheating, the dendrites start to disintegrate due to the penetration of the liquid phase into the high-energy grain boundaries. By increasing the holding time, the connected and agglomerated recrystallized microstructure disintegrates and grain spheroidization and coarsening are activated. Due to the Gibbs-Thomson effect, the sharp edges of the deformed dendrites with lower melting points change gradually to globular shapes. It is interesting to note that earlier other Iranian scholars, Meidani et al. [16] had reported the formation of globular structure by ECAP and isothermal treatment of a semi-solid aluminum A356 alloy. Similar reports for semi-solid processing of aluminum A356 alloy, [19,41,43] and aluminum A8006 alloy [66,68] were published by Iranian scholars.

#### ***4.2. ECAP as a consolidation method***

Although ECAP is generally used for microstructural refinement in solid metals, it may be used also for the consolidation of metallic powders. The mechanism for powder consolidation by ECAP is the deformation of the particles which is different from sintering in which the main mechanism is diffusion as shown in Fig. 2 [136]. Usually a layer of oxide that covers the surface of metal particles prevents their bonding to each other. In conventional sintering processes, compacted particles are placed at an elevated temperature varying from some minutes to some hours. Atoms then diffuse through the surface or the interior of the particles to reduce the surface energy and, as a result, the bonding and densification are achieved. Therefore, during sintering a density increment happens because the gap between the particles is filled. Since the material flow is limited during sintering, a complete elimination of pores and full densification are almost impossible. Nevertheless, the oxide layer is fractured during SPD consolidation and this leads to

a direct contact between the metal surfaces. In addition, the material flow fills any gap between the particles and helps to achieve a full density. In this case, no diffusion is required for bonding. Therefore, the processing can be carried out at lower temperatures and consolidation is obtained instantaneously as the particles are deformed.

Xiang et al. [137] were the first researchers to use ECAP for the consolidation of metallic powders and they were able to consolidate an Al-2024 alloy powder by ECAP at 300°C up to a maximum of 3 passes. A pre-cold isostatic pressing (CIP) of the powder was a prerequisite for the process. However, cracks were formed on the specimen surface even by a single pass of ECAP. In 2000, Matsuki et al. [138] showed that the use of a cap (Fig. 3a) prior to ECAP processing prevented the surface cracking after ECAP processing. The CIP sample of Al-2024 alloy powder (18 mm in diameter and 35 mm in length) was put into a 2024Al cap (Fig. 3b) and then consolidated by ECAP at 300°C without surface cracking (Fig. 3c). Successful ECAP consolidation has been performed on several powders including Al [139], 6061 Al [140], 2024 Al [138,141,142], Mg [143,144], AA4032- CNT composite [145], WC+Co[146,147], Ti [139], Ti-6Al-4V [148,149], titanium silicide (Ti<sub>5</sub>Si<sub>3</sub>) [150,151], Cu [152,153], Cu-Ta alloys [154], amorphous Al (Al<sub>89</sub>Gd<sub>7</sub>Ni<sub>3</sub>Fe<sub>1</sub> and Al<sub>85</sub>Ni<sub>10</sub>Y<sub>2.5</sub>La<sub>2.5</sub>) [155], amorphous Cu (Cu<sub>50</sub>Ti<sub>32</sub>Zr<sub>12</sub>Ni<sub>5</sub>Si<sub>1</sub>) [156], carbon nanotube (CNT)-metal matrix composites [157,158], Al-Si [159], Al-Al<sub>2</sub>O<sub>3</sub> [160,161], Al-AlN[162], Vitreloy 106a (Zr<sub>58.5</sub>Nb<sub>2.8</sub>Cu<sub>15.6</sub>Ni<sub>12.8</sub>Al<sub>10.3</sub>)+W [159], Ti-SiC[163], Ti-Al [164,165], Al-Y<sub>2</sub>O<sub>3</sub> composite [166], AA7075-ZrO<sub>2</sub>[167] and Al-Al<sub>2</sub>O<sub>3</sub>[168].

In 2005, Xia and Wu [169] used back-pressure equal-channel angular consolidation (BP-ECAC) to consolidate pure Al particles at a low temperature of 100 °C. They concluded that applying a back-pressure (BP) to the front of the samples on the exit channel of ECAP is preferable to ECAP without back-pressure due to the achievement of full density and the good bonding after

only a single pass. This serves to eliminate the pre-compaction step and can use loose particles. BP was also used in different studies to consolidate a wide range of powders such as Al [136,170-172], Mg [173,174], Al matrix composites [175], Al-Al<sub>2</sub>O<sub>3</sub> composite [176], Al-C nanocomposites[177], Cu+MgB<sub>2</sub>[153,178], Ti [179], Ti-6Al-4V [180,181] and TiN-Ti composites [182]. The application of PB needs some additional equipment, such as a double action pressing machine that has the capability of controlling the forward- and backward-pressure) [183], and the process tends to be time-consuming and expensive.

To overcome these problems, Paydar et al. [123] suggested that the extrusion process designed in the second channel of the ECAP die could provide the required back-pressure to achieve almost fully dense samples. The most important feature of this method, named ECAP-FE, was that two processes, ECAP and FE, were carried out subsequently in a single tool (Fig. 4a) that led to the elimination of additional equipment. These Iranian researchers showed also that the consolidation of pure aluminum powder at 200 °C produced by ECAP-FE with an extrusion ratio of 10 could achieve a density comparable with that of fully dense bulk aluminum. In addition, using an Arrhenius equation, they calculated the self-diffusion coefficient of Al in ECAP and ECAP-FE. In the condition where no load was applied, the back-pressure created during ECAP-FE increased the self-diffusion coefficient of Al by a factor of 3.8 relative to its value during simple ECAP. The increase in the self-diffusion coefficient of Al during ECAP-FE had a significant effect on the pore closure and improved the mechanical properties of the sample.

Another combined method which was used to consolidate powders is torsional-equal channel angular pressing (T-ECAP) [251] this number is out of order which is shown in Fig. 4b. Consolidation of pure Al particles showed that after 3 passes of T-ECAP a maximum density

was achieved. Mani et al. [184] investigated the pore shape change and closure during T-ECAP by using metallographic inspections. It was shown that the shape of the porosities changed from an elongated one in the ECAP stage into a nearly spherical one in the rotating stage during the T-ECAP. Despite the similarities between the T-ECAP and ECAP-FE, there are two main differences between these processes: the repeating possibility of the T-ECAP process and the requirement for using cans in T-ECAP prior to processing. Furthermore, the rotating part of the T-ECAP needs additional equipment which tends to be costly. Therefore, it seems that ECAP-FE is more applicable than T-ECAP but it needs more study to clarify the different aspects of these two processes.

Although ECAP was usually used as an alternative for conventional methods like compaction plus sintering and extrusion to consolidate powders, in some studies it was used as a post-process in order to refine the microstructure and enhance the mechanical properties. In 2008, Paydar et al. [9] consolidated Al particles successfully using ECAP after an extrusion channel in a single die, referred to as forward extrusion-equal channel angular pressing (FE-ECAP) which is shown in Fig. 4c. A good bonding with superior mechanical properties was achieved after FE-ECAP compared to FE. The yield strength for the consolidated air atomized commercially pure aluminum powder with an average particle size of 45  $\mu\text{m}$  was 142 and 124 MPa for the ECAP-FE [9] processes at 200°C, respectively. There was a similar behavior for the ultimate tensile strength and hardness measurements. The fabrication of Al–10 vol%SiC<sub>p</sub> composites by FE and FE-ECAP at 550 °C resulted in an increase in the ultimate tensile strength from 136 MPa for FE to 148 MPa for FE-ECAP [185,186].

In 2010, Nagasekhar et al. [187] compared the deformation flow, strain homogeneity, and load requirements of FE-ECAP and ECAP-FE with those of individual FE and ECAP processes using

finite element analysis. Fig. 5 shows the effective strain variation across the width of a cross-section of the specimen from top to bottom. The effective strain is more uniform in the ECAP process. They also concluded that the strain distribution in the combination processes, FE+ECAP and ECAP+FE, was dominated by the deformation behavior and strain distribution of the FE process. Therefore, by comparing FE-ECAP to ECAP-FE, it can be concluded that ECAP-FE is more effective than FE-ECAP in order to consolidate powders because it imposes higher strains and results in a more uniform strain distribution and better mechanical properties of the product.

## **5. Modeling and simulation**

Material modeling and simulation can help complement experimental results and enable researchers to predict the deformation behavior and the properties of materials. Since the first analytical models [188,189] proposed to estimate the strain in ECAP, several methods have been used to model and to simulate different aspects of the process. These include finite element modeling (FEM) [187,190-229], upper bound (UB) models [10,230-257], visco plastic self-consistent (VPSC) models [205,208,258-279], Monte-Carlo modeling [7,8,280-284] and artificial neural network (ANN) [285-290]. By using these strategies many different characteristics of ECAP and ECA pressed samples were predicted successfully including effective strain and strain homogeneity [188,189,232,247,291-299], processing parameters [10,209,212,230-257,286,300,301], microstructure [8,206,259,302-318], texture [197,208,220,259,261,275,303,311,315,319-333] and mechanical properties [312,322,324,334-343].

Taking a brief look at the publications in the field of ECAP, about 13% of the records are involved in simulation and modeling. As shown in Fig. 6, this value is about 17% among all

documents published in this field by Iranian researchers which represents its highest tendency among Iranian scholars. There can be some factual reasons for this. Firstly, Iran has not signed or ratified any of multilateral international copyright treaties. Therefore, Iranian researchers have access to a wide range of software packages and they have become experts in developing simulations. Secondly, Iran allocates fewer funds to research and has less access to advanced characterization methods so that the easy access to software packages means that simulations are cheaper than experiments.

As summarized in Table 2, most of the modeling and simulations by Iranian researchers were confirmed by experimental evidence. According to Fig. 6, 69% of the documents published by Iranians on simulations and modeling have used FEM for simulation while this amount is 65% for the total documents. This shows that most FEM studies are simply case studies which are relatively easy to confirm. However, it is interesting to note that Iranian scholars are pioneers in both old and new modeling methods. Thus, about 17% of the records of ECAP in this field have used an upper bound (UB) method (a basic analysis method) to investigate deformation behavior during ECAP. On the other hand, only 5% of the total publications in modeling and simulations are based on UB models (Fig. 6). More than 20% of all the research that used UB models to analyze ECAP were published by Iranians.

Parallel to the first theoretical studies in Iran to estimate the strain [4,344], a new configuration of ECAP nominated as the multi-stage ECAP was used to calculate the strain in ECAP and the first UB models to analyze ECAP were presented. In the multi-stage ECAP die, the deformation zone is divided into a number of “sub-dies”, and each of them inserted a shear strain to the material. By this approach the total strain was calculated simply, and interestingly it was the same as the relationship proposed by Alkorta and Sevillano [233]. Eivani and Karimi Taheri,

reference ? applied a UB model in order to investigate the plastic deformation behavior of the material during ECAP. Although there were numerous reports that focused on the UB analysis of ECAP [231,233,235,236,345], before that time none of them considered the effects of all parameters such as friction, die angle and the outer curved corner angle in the mechanics of the process. Thus, these works were the first to consider the effect of all the process parameters simultaneously.

Reihanian et al. [244] in 2009 used, for the first time, a new upper-bound approach based on Avitzur and Pachla [346,347] to analyze the ECAP. The same researchers, also, for the first time proposed a UB approach to analyze ECAP with circular cross-sections [10]. A short time after this work, Eivani et al. [348] proposed another UB model for circular cross-sections which considered the effect of the deformations passes. In 2010, in a contribution between Iranian and Korean researchers, the effects of temperature and strain rate on the mechanics of ECAP at elevated temperatures were investigated by a UB model [250]. For this reason a parameter known as the velocity-modified temperature ( $\bar{T}$ ) to relate temperature and strain rate was utilized. They used the same formulation as that proposed by Paydar et al. [10] but with the consideration of the effect of velocity-modified temperature. By using the UB analysis, the powers dissipated during the process and consequently the processing load of the process could be calculated. Also, it is possible to minimize the processing load by optimizing the processing parameters such as die angles and frictional forces.

One of the most important microstructural features of ECAP samples is their texture that affects other material behaviors such as strength, plastic anisotropy, formability, grain refinement, and fracture. Therefore, the simulation of texture evolution during processing has attracted the attention of many among the materials science community. To study the detail of the

developments in the simulation and modeling of texture, a comprehensice review of this field was published earlier [31]. Despite the wide range of articles on simulations and modeling of texture, there are only a limited number of reports by Iranian researchers [22,351]. Since these works were conducted with contributions from French and Canadian researchers, it suggest that a lack of equipment, such as XRD and EBSD, is the main reason for the lack of studies in the simulation of textures in Iran.

Another aspect, which is important for all researchers, is to predict the mechanical properties of the materials after ECAP. Methods to predict the mechanical responses of materials after SPD processing based on dislocation kinetics are well reviewed by Vinogradov [364]. Regarding the dislocation-based approach, the premature strain localization in UFG metals and alloys manufactured by SPD is intimately related to the dislocation density evolution. In this report it was concluded that the uniform elongation is primarily controlled by the rate of dislocation recovery [364].

## ***6. Special Characterization***

The main objective of ECAP is to refine the microstructure in order to achieve exceptional mechanical and physical properties. Therefore, the first aim of most of researchers is to investigate the microstructure and texture of the processed sample that was reviewed well in numerous reports [29,30,32,130,131,364]. As summarized in Table 1, many different aspects of ECAP samples include microstructure, texture, mechanical properties, fatigue behavior, superplasticity, creep and corrosion. To avoid repeating the reports already published in earlier reviews, it is sufficient only to address some novel achievements in the characterization of ECAP

samples by Iranian researchers. These achievements are those that result in a progress in this field and thereby attract the attention of other scholars.

### ***6.1. Microstructural non-uniformity during ECAP***

When the deformation is ideal during ECAP, the stress exhibits a uniform distribution in the cross-section of the billet and consequently a homogenous strain distribution is expected [365]. Because of the homogeneous strain distribution, a uniformity of microstructure and mechanical properties in ECAP specimens is essential. However, ideal metal flow during ECAP is far from a reality. Therefore, investigations of the microstructural uniformity during ECAP is very important. This research theme was the aim of the first study in Iran on ECAP processing which was conducted on commercially pure Al billets. In this study, the microstructural homogeneity through the section parallel to the pressing direction (transverse direction (TD)) of ECAP-processed samples was investigated from 1 to 8 passes through route Bc [11]. In 2005, Xu et al. [366] investigated the microstructural homogeneity of the ECAP-processed pure Al billets through the perpendicular section to the pressing direction (extrusion direction (ED)) using microhardness measurements and TEM observations. From the TEM observations, they concluded that in the central region, the elongated grains and the equiaxed grains each occupied the same area fractions of  $\sim 50\%$  while the elongated grains were more prevalent in the vicinity of the lower surface occupying an estimated area fraction of  $\sim 90\%$ . For the elongated grains in the central region shown in Fig. 7, the average widths and lengths were  $\sim 1.3$  and  $\sim 5\mu\text{m}$ , respectively. The size of the elongated grains in the periphery was identical to that of the central region. They also reported that the hardness distribution was inhomogeneous after one pass with

a lower hardness in the periphery but the distribution became essentially homogeneous with additional passes.

In 2008, using EBSD scans Reihaniann et al. [11] showed that for all passes (from 1 to 8 passes) the fraction of high-angle boundaries ( $f_{HAGBs}$ ) and the mean misorientation angle ( $\theta_m$ ) had their highest values at the center of the sample through the TD-section while the grain size is the lowest. In addition, by measuring from the center to the periphery, the grain size increased while  $f_{HAGBs}$  and  $\theta_m$  decreased gradually. For example, Fig. 8 shows the orientation color maps and boundary misorientation maps taken from the center and periphery of the TD section. The basic microstructural parameters such as mean boundary spacing including all boundaries ( $d^{All}$ ),  $\theta_m$  and  $f_{HAGBs}$  were measured from the center to the periphery of the 8 passes samples. Therefore, it was concluded that the microstructure after ECAP processing was inhomogeneous through both the ED and TD sections. However, the microstructure became more uniform by increasing the number of passes.

## ***6.2. Superplasticity***

The occurrence of superplasticity, wherein a polycrystalline material deformed in tension at low stresses exhibited neck-free elongations of many hundreds of percent prior to failure, was first reported explicitly by Pearson [367] in 1934 where there was a remarkable tensile elongation of 1950% in a Pb–Sn eutectic alloy. After more than eighty years of research in this field, many aspects of this phenomenon has been clarified as reported in several review articles [368,369]. To achieve superplasticity in conventional polycrystalline metals, a small and stable grain size and a relatively high testing temperature (higher than one-half of the absolute melting temperature) are required [370]. Therefore, ECAP samples are good candidates for superplastic

forming (SPF) [368] in which large volume components with curved and complex shapes are produced due to the very small grain sizes achieved by ECAP. In 2016, Kawasaki and Langdon [371] provided a review to explain the exceptional superplastic flow in a series of UFG aluminum and magnesium alloys after ECAP and HPT. Although more than 400 documents reported the superplastic behavior of UFG materials fabricated by ECAP, the number of publications in this field by Iranians is less than 10 articles. Thus, while superplasticity was the aim of 8% of the total ECAP studies, this value was reduced to 3% for those articles published by Iranian researchers.

Most of the reports on the superplasticity of alloys after ECAP have used conventional tensile tests. However, in 2008 Mahmudi et al. [21] employed localized indentation to investigate the superplastic indentation creep behavior of the fine-grained Sn-1%Bi alloy at room temperature ( $T > 0.6T_m$ ) fabricated by ECAP by measuring the stress exponents and strain rate sensitivity (SRS) indices for the alloy after ECAP. In this respect, they used an equation obtained in 1992 [372] to relate the time dependent hardness ( $H_V(t)$ ) to other parameters as

$$H_V(t) = \frac{\sigma_0}{(\frac{1}{m}C_4\dot{\varepsilon}_0 T)^m} \quad (1)$$

where  $\dot{\varepsilon}_0$  is the strain rate at a reference stress  $\sigma_0$ ,  $m$  denotes SRS index,  $C_4$  is a constant,  $T$  is the temperature and  $t$  is the dwell time. Therefore, by plotting  $\ln(H_V)$  against  $\ln(t)$  at a constant temperature, the SRS index can be calculated.

Another method that was used to measure SRS of ECAP alloys is impression testing techniques [121], a modified version of the indentation creep method. In the impression testing technique, the impression depth is recorded during the dwell time after pushing a flat-bottomed cylindrical punch into the test specimen under a constant load. Consequently, the penetration rate or impression velocity can be obtained. A suitable alternative method for conventional tensile

tests is shear punch testing (SPT). In SPT, the sample is clamped between two die halves and a flat cylindrical punch is driven through it. Mechanical properties, ultimate shear strength and shear elongation values can be obtained by plotting shear stress against normalized displacement obtained by SPT. In 2013, Mahmudi et al. [373] used SPT to evaluate the superplastic behavior for the first time. Based on their proposed procedure it is possible to calculate the SRS index ( $m$ ) through the relationship

$$m = \left( \frac{\partial \ln \tau}{\partial \ln \dot{\gamma}} \right)_T \quad (2)$$

in which  $\tau$  is the shear stress and  $\dot{\gamma}$  is the shear strain rate. Consequently, the slope of a log-log plot of shear stress against shear strain rate gives the SRS index. A summary of superplasticity data for different materials after ECAP investigated by SPT can be found in Table 2 in another report [374]. Comparing SPT with other testing methods, it was shown that SPT provides a convenient method for measuring the SRS indices [373]. The main advantage of SPT is its ability to analyze small thin test pieces such as those usually obtained through SPD processing.

### 6.3. Corrosion

Corrosion in polycrystalline materials is strongly affected by their grain size. In a review on the corrosion of UFG materials produced by SPD, Miyamoto [375] concluded that grain refinement by SPD does not sacrifice the overall corrosion resistance and in many cases, SPD can improve it by comparison with coarse-grained counterparts. For example, it was reported that the corrosion resistance of ultrafine-grained Fe-Cr alloy fabricated by SPD was much higher than that of a conventional grain size [375]. This high corrosion resistance is not only due to the grain size reduction but also due to the formation of non-equilibrium grain boundaries during SPD. For example, in Fe-Cr the Cr diffusion to the surface is accelerated by the high-density non-

equilibrium grain boundaries and it stabilizes passivity in a corrosive environment [376]. Previous studies suggest that the corrosion resistance can be enhanced by SPD for materials with alloying elements of passivity formation such as in Mg-Al, Cu-Al etc. More than 60 reports have been published that investigate the corrosion behavior of different materials after ECAP and it is important to note that Iranian scholars are active in this field. According to Table 1, the corrosion resistance of 6061 Al alloy [23], 316L austenitic stainless steel [89,90] and commercially pure titanium (CP Ti) [91] was investigated by Iranian researchers.

The corrosion resistance of CP Ti was shown to be slightly improved as a result of applying (ECAP. In 2009, Hoseini et al. [91] investigated the effect of texture on the corrosion properties of commercially pure titanium processed by ECAP. They showed that the effect of texture on corrosion is strong because the basal plane is most resistant to corrosion. Earlier, Blawert et al. [377] tried to correlate texture to corrosion properties in magnesium fabricated by Physical Vapour Deposition (PVD). However, the texture change between different deposition processes was too small to be visible in the corrosion behavior. After the work of Hoseini et al. [91], there are some publications that investigate the effect of texture on corrosion behavior in Mg [378-380] and Ti [381]. From all of these publications, it can be concluded that the higher electron working function of atoms in the basal plane due to the high atomic coordination of the basal plane leads to a highest resistance to dissolution. However, it is hard to draw general conclusions on corrosion resistance because of the dependence of the texture to the ECAP processing routes [375].

## **7. Summary and conclusions**

The fabrication of ultrafine-grained materials by ECAP is one of the main and basic topics in the SPD research community. In 2007, the first work on ECAP was published in Iran. Since that time, the contribution of Iran to this research field has increased continuously. The main contribution of Iranian researchers in ECAP is focused on simulation/modelling. This can be attributed to the fewer funds for research and the limited access to advanced characterization methods. In addition, the topics of the published works indicate that there is a remarkable attention of Iranian researchers to introduce new methods of SPD based on ECAP. This tendency has made Iran the first ranked country for developing new SPD methods based on ECAP. There is no doubt that the attention of Iranian researchers will be shifted to other topics of ECAP process in the future if opportunities for Iranian scientist to collaborate with other countries is improved, sufficient funds for characterization are provided and laboratories with advanced characterization tools are constructed in Iran.

## **Acknowledgments**

The financial support of Shahid Chamran University of Ahvaz and Shiraz University is gratefully appreciated. The work of one of us was supported by the European Research Council under ERC Research Grant No. 267464-SPDMETALS (TGL).

## References

1. R.Z. Valiev, R.K. Islamgaliev, I.V. Alexandrov, Bulk nanostructured materials from severe plastic deformation, *Progress in Materials Science*, **45**(2), 103-189 (2000)
2. V. Segal, V. Reznikov, A. Dobryshevshiy, V. Kopylov, Plastic working of metals by simple shear, *Russian Metallurgy (Metally)*, (1), 99-105 (1981)
3. A.R. Eivani, A.K. Taheri, A new method for producing bimetallic rods, *Materials Letters*, **61**(19-20), 4110-4113 (2007)
4. A.R. Eivani, A.K. Taheri, A new method for estimating strain in equal channel angular extrusion, *Journal of Materials Processing Technology*, **183**(1), 148-153 (2007)
5. A.R. Eivani, A.K. Taheri, An upper bound solution of ECAE process with outer curved corner, *Journal of Materials Processing Technology*, **182**(1-3), 555-563 (2007)
6. A.R. Eivani, A.K. Taheri, The effect of dead metal zone formation on strain and extrusion force during equal channel angular extrusion, *Computational Materials Science*, **42**(1), 14-20 (2008)
7. M. Kazeminezhad, Simulation the ultra-fine microstructure evolution during annealing of metal processed by ECAP, *Computational Materials Science*, **43**(2), 309-312 (2008)
8. M. Kazeminezhad, E. Hosseini, Coupling kinetic dislocation model and Monte Carlo algorithm for recrystallized microstructure modeling of severely deformed copper, *Journal of Materials Science*, **43**(18), 6081-6086 (2008)
9. M.H. Paydar, M. Reihanian, E. Bagherpour, M. Sharifzadeh, A. Zarinejad, T.A. Dean, Consolidation of Al particles through forward extrusion-equal channel angular pressing (FE-ECAP), *Materials Letters*, **62**(17-18), 3266-3268 (2008)
10. M.H. Paydar, M. Reihanian, R. Ebrahimi, T.A. Dean, M.M. Moshksar, An upper-bound approach for equal channel angular extrusion with circular cross-section, *Journal of Materials Processing Technology*, **198**(1-3), 48-53 (2008)
11. M. Reihanian, R. Ebrahimi, M.M. Moshksar, D. Terada, N. Tsuji, Microstructure quantification and correlation with flow stress of ultrafine grained commercially pure Al fabricated by equal channel angular pressing (ECAP), *Materials Characterization*, **59**(9), 1312-1323 (2008)
12. M. Reihanian, R. Ebrahimi, N. Tsuji, M.M. Moshksar, Analysis of the mechanical properties and deformation behavior of nanostructured commercially pure Al processed by equal channel angular pressing (ECAP), *Materials Science and Engineering a-Structural Materials Properties Microstructure and Processing*, **473**(1-2), 189-194 (2008)
13. S. Ashouri, M. Nili-Ahmabadi, M. Moradi, M. Iranpour, Semi-solid microstructure evolution during reheating of aluminum A356 alloy deformed severely by ECAP, *Journal of Alloys and Compounds*, **466**(1-2), 67-72 (2008)
14. M.R.M. Garabagh, S.H. Nedjad, M.N. Ahmadabadi, X-ray diffraction study on a nanostructured 18Ni maraging steel prepared by equal-channel angular pressing, *Journal of Materials Science*, **43**(21), 6840-6847 (2008)
15. M.R.M. Garabagh, S.H. Nedjad, H. Shirazi, M.I. Mobarekeh, M.N. Ahmadabadi, X-ray diffraction peak profile analysis aiming at better understanding of the deformation

process and deformed structure of a martensitic steel, *Thin Solid Films*, **516**(22), 8117-8124 (2008)

- 16. H. Meidani, S.H. Nedjad, M.N. Ahmadabadi, A Novel Process for Fabrication of Globular Structure by Equal Channel Angular Pressing and Isothermal Treatment of Semisolid Metal, *Semi-Solid Processing of Alloys and Composites Xed.*, G. Hirt, A. Rassili, A. BuhrigPolaczek, Eds., 2008, p 445-450
- 17. M.I. Mobarake, M. Nili-Ahmabadi, B. Poorganji, A. Fatehi, H. Shirazi, T. Furuhara, H. Parsa, S.H. Nedjad, Microstructural study of an age hardenable martensitic steel deformed by equal channel angular pressing, *Materials Science and Engineering a-Structural Materials Properties Microstructure and Processing*, **491**(1-2), 172-176 (2008)
- 18. M. Moradi, M. Nili-Ahmabadi, B. Heidarian, M.H. Parsa, Study of ECAP Processing Routes on Semi-solid Microstructure Evolution of A356 Alloy, *Semi-Solid Processing of Alloys and Composites Xed.*, G. Hirt, A. Rassili, A. BuhrigPolaczek, Eds., 2008, p 397-402
- 19. S.H. Nedjad, H. Meidana, M.N. Ahmadabadi, Effect of equal channel angular pressing on the microstructure of a semisolid aluminum alloy, *Materials Science and Engineering a-Structural Materials Properties Microstructure and Processing*, **475**(1-2), 224-228 (2008)
- 20. M.H. Parsa, M. Naderi, M. Nili-Ahmabadi, H. Asadpour, The Evolution of Strain during Equal Channel Angular Pressing, *International Journal of Material Forming*, **1**, 93-96 (2008)
- 21. R. Mahmudi, H. Mhjoubi, P. Mehraram, Superplastic indentation creep of fine-grained Sn-1% Bi alloy, *International Journal of Modern Physics B*, **22**(18-19), 2823-2832 (2008)
- 22. M. Hoseini, M. Meratian, H.L. Li, J.A. Szpunar, Texture simulation of aluminum rod during equal channel angular pressing, *Journal of Materials Science*, **43**(13), 4561-4566 (2008)
- 23. M. Hoseini, M. Meratian, M.R. Toroghinejad, J.A. Szpunar, Texture contribution in grain refinement effectiveness of different routes during ECAP, *Materials Science and Engineering a-Structural Materials Properties Microstructure and Processing*, **497**(1-2), 87-92 (2008)
- 24. A. Zirulnick, Sanction Qaddafi? How 5 nations have reacted to sanctions., The Christian Science Monitor., February 24, 2011
- 25. J. Blas, N. Bozorgmehr, Iran struggles to find new oil customers, The Financial TIimes., February 20, 2012
- 26. S. Saeidnia, M. Abdollahi, Consequences of International Sanctions on Iranian Scientists and the Basis of Science, *Hepatitis Monthly*, **13**(9), e14843 (2013)
- 27. Y. Saito, N. Tsuji, H. Utsunomiya, T. Sakai, R.G. Hong, Ultra-fine grained bulk aluminum produced by accumulative roll-bonding (ARB) process, *Scripta Materialia*, **39**(9), 1221-1227 (1998)
- 28. M. Furukawa, M. Nemoto, Z. Horita, T.G. Langdon, Processing of metals by equal-channel angular pressing, *Journal of Materials Science*, **36**, 2835-2843 (2001).
- 29. R.Z. Valiev, T.G. Langdon, Principles of equal-channel angular pressing as a processing tool for grain refinement, *Progress in Materials Science*, **51**(7), 881-981 (2006)

30. R.Z. Valiev, Y. Estrin, Z. Horita, T.G. Langdon, M.J. Zehetbauer, Y.T. Zhu, Producing bulk ultrafine-grained materials by severe plastic deformation, *JOM*, **58**(4), 33-39 (2006)
31. I.J. Beyerlein, L.S. Tóth, Texture evolution in equal-channel angular extrusion, *Progress in Materials Science*, **54**(4), 427-510 (2009)
32. R.B. Figueiredo, T.G. Langdon, Fabricating Ultrafine-Grained Materials through the Application of Severe Plastic Deformation: a Review of Developments in Brazil, *Journal of Materials Research and Technology*, **1**(1), 55-62 (2012)
33. M. Kawasaki, T.G. Langdon, Review: achieving superplastic properties in ultrafine-grained materials at high temperatures, *Journal of Materials Science*, **51**(1), 19-32 (2015)
34. R.Z. Valiev, Y. Estrin, Z. Horita, T.G. Langdon, M.J. Zehetbauer, Y.T. Zhu, Producing bulk ultrafine-grained materials by severe plastic deformation: ten years later, *JOM*, **68**(4), 1216-1226 (2016)
35. B. Tolaminejad, F. Brisset, T. Baudin, Iop, EBSD study of the microstructure evolution in a commercially pure aluminium severely deformed by ECAP, Emas 2011: 12th European Workshop on Modern Developments in Microbeam Analysised., 2012
36. B. Tolaminejad, K. Dehghani, Microstructural characterization and mechanical properties of nanostructured AA1070 aluminum after equal channel angular extrusion, *Materials & Design*, **34**, 285-292 (2012)
37. M. Hoseini, M. Meratian, M.R. Toroghinejad, J.A. Szpunar, The role of grain orientation in microstructure evolution of pure aluminum processed by equal channel angular pressing, *Materials Characterization*, **61**(12), 1371-1378 (2010)
38. F. Djavanroodi, M. Ebrahimi, B. Rajabifar, S. Akramizadeh, Fatigue design factors for ECAPed materials, *Materials Science and Engineering a-Structural Materials Properties Microstructure and Processing*, **528**(2), 745-750 (2010)
39. F. Djavanroodi, B. Omranpour, M. Ebrahimi, M. Sedighi, Designing of ECAP parameters based on strain distribution uniformity, *Progress in Natural Science-Materials International*, **22**(5), 452-460 (2012)
40. F. Djavanroodi, H. Ahmadian, K. Koohkan, R. Naseri, Ultrasonic assisted-ECAP, *Ultrasonics*, **53**(6), 1089-1096 (2013)
41. M. Moradi, M. Nili-Ahmabadi, B. Poorganji, B. Heidarian, M.H. Parsa, T. Furuhara, Recrystallization behavior of ECAPed A356 alloy at semi-solid reheating temperature, *Materials Science and Engineering a-Structural Materials Properties Microstructure and Processing*, **527**(16-17), 4113-4121 (2010)
42. M. Moradi, M. Nili-Ahmabadi, B. Heidarian, IMPROVEMENT OF MECHANICAL PROPERTIES OF AL (A356) CAST ALLOY PROCESSED BY ECAP WITH DIFFERENT HEAT TREATMENTS, *International Journal of Material Forming*, **2**, 85-88 (2009)
43. M. Moradi, M. Nili-Ahmabadi, B. Poorganji, B. Heidarian, T. Furuhara, EBSD and DTA Characterization of A356 Alloy Deformed by ECAP During Reheating and Partial Re-melting, *Metallurgical and Materials Transactions a-Physical Metallurgy and Materials Science*, **45A**(3), 1540-1551 (2014)
44. M.R. Roshan, S.A.J. Jahromi, R. Ebrahimi, Predicting the critical pre-aging time in ECAP processing of age-hardenable aluminum alloys, *Journal of Alloys and Compounds*, **509**(30), 7833-7839 (2011)

45. M.H. Goodarzy, H. Arabi, M.A. Bouterabi, S.H. Seyedehin, S.H.H. Najafabadi, The effects of room temperature ECAP and subsequent aging on mechanical properties of 2024 Al alloy, *Journal of Alloys and Compounds*, **585**, 753-759 (2014)

46. M. Vaseghi, A.K. Taheri, H.S. Kim, An electron back-scattered diffraction study on the microstructure evolution of severely deformed aluminum Al6061 alloy, 6th International Conference on Nanomaterials by Severe Plastic Deformationed., B. Beausir, O. Bouaziz, E. Bouzy, T. Grosdidier, L.S. Toth, Eds., 2014

47. M. Vaseghi, A.K. Taheri, S.I. Hong, H.S. Kim, Dynamic ageing and the mechanical response of Al-Mg-Si alloy through equal channel angular pressing, *Materials & Design*, **31**(9), 4076-4082 (2010)

48. A. Shokuhfar, O. Nejadseyfi, The Influence of Friction on the Processing of Ultrafine-Grained/Nanostructured Materials by Equal-Channel Angular Pressing, *Journal of Materials Engineering and Performance*, **23**(3), 1038-1048 (2014)

49. O. Nejadseyfi, A. Shokuhfar, A. Dabiri, A. Azimi, Combining equal-channel angular pressing and heat treatment to obtain enhanced corrosion resistance in 6061 aluminum alloy, *Journal of Alloys and Compounds*, **648**, 912-918 (2015)

50. A. Shokuhfar, O. Nejadseyfi, A comparison of the effects of severe plastic deformation and heat treatment on the tensile properties and impact toughness of aluminum alloy 6061, *Materials Science and Engineering a-Structural Materials Properties Microstructure and Processing*, **594**, 140-148 (2014)

51. O. Nejadseyfi, A. Shokuhfar, A. Azimi, M. Shamsborhan, Improving homogeneity of ultrafine-grained/nanostructured materials produced by ECAP using a bevel-edge punch, *Journal of Materials Science*, **50**(3), 1513-1522 (2015)

52. A.A. Khamei, K. Dehghani, Hot Ductility of Severe Plastic Deformed AA6061 Aluminum Alloy, *Acta Metallurgica Sinica-English Letters*, **28**(3), 322-330 (2015)

53. A.A. Khamei, K. Dehghani, R. Mahmudi, Modeling the Hot Ductility of AA6061 Aluminum Alloy After Severe Plastic Deformation, *JOM*, **67**(5), 966-972 (2015)

54. M. Vaseghi, H.S. Kim, A.K. Taheri, A. Momeni, Inhomogeneity Through Warm Equal Channel Angular Pressing, *Journal of Materials Engineering and Performance*, **22**(6), 1666-1671 (2013)

55. H. Alihosseini, M.A. Zaeem, K. Dehghani, G. Faraji, Producing high strength aluminum alloy by combination of equal channel angular pressing and bake hardening, *Materials Letters*, **140**, 196-199 (2015)

56. Y.B. Asl, M. Meratian, A. Emamikhah, R.M. Homami, A. Abbasi, Mechanical properties and machinability of 6061 aluminum alloy produced by equal-channel angular pressing, *Proceedings of the Institution of Mechanical Engineers Part B-Journal of Engineering Manufacture*, **229**(8), 1302-1313 (2015)

57. B. Mirzakhani, Y. Payandeh, Combination of sever plastic deformation and precipitation hardening processes affecting the mechanical properties in Al-Mg-Si alloy, *Materials & Design*, **68**, 127-133 (2015)

58. J. Nemati, G.H. Majzoobi, S. Sulaiman, B. Baharudin, M.A.A. Hanim, Effect of equal channel angular extrusion on Al-6063 bending fatigue characteristics, *International Journal of Minerals Metallurgy and Materials*, **22**(4), 395-404 (2015)

59. S. Dadbakhsh, A.K. Taheri, C.W. Smith, Strengthening study on 6082 Al alloy after combination of aging treatment and ECAP process, *Materials Science and Engineering*

*a-Structural Materials Properties Microstructure and Processing*, **527**(18-19), 4758-4766 (2010)

- 60. M. Vaseghi, H.S. Kim, A combination of severe plastic deformation and ageing phenomena in Al-Mg-Si Alloys, *Materials & Design*, **36**, 735-740 (2012)
- 61. S. Mohammadi, M. Irani, A.K. Taheri, The effects of combination of severe plastic deformation and Shot Peening surface treatment on fatigue behavior of 6082 aluminum alloy, *Russian Journal of Non-Ferrous Metals*, **56**(2), 206-211 (2015)
- 62. M.H. Shaeri, M.T. Salehi, S.H. Seyyedein, M.R. Abutalebi, J.K. Park, Characterization of microstructure and deformation texture during equal channel Angular pressing of Al-Zn-Mg-Cu alloy, *Journal of Alloys and Compounds*, **576**, 350-357 (2013)
- 63. M.H. Shaeri, M.T. Salehi, S.H. Seyyedein, M.R. Abutalebi, J.K. Park, Microstructure and mechanical properties of Al-7075 alloy processed by equal channel angular pressing combined with aging treatment, *Materials & Design*, **57**, 250-257 (2014)
- 64. M.H. Shaeri, M. Shaeri, M.T. Salehi, S.H. Seyyedein, M.R. Abutalebi, Effect of equal channel angular pressing on aging treatment of Al-7075 alloy, *Progress in Natural Science-Materials International*, **25**(2), 159-168 (2015)
- 65. M.H. Shaeri, M. Shaeri, M.T. Salehi, S.H. Seyyedein, F. Djavanroodi, Microstructure and texture evolution of Al-7075 alloy processed by equal channel angular pressing, *Transactions of Nonferrous Metals Society of China*, **25**(5), 1367-1375 (2015)
- 66. D. Azimi-Yancheshmeh, M. Aghaie-Khafri, Study of Semisolid and ECAP Processes on Al-Fe-Si Alloy - Microstructure and Kinetic Grain growth, Diffusion in Solids and Liquids Vi, Pts 1 and 2ed., A. Ochsner, G.E. Murch, J.M.P. Delgado, Eds., 2011, p 166-171
- 67. N. Tabatabaei, A.K. Taheri, M. Vaseghi, Dynamic strain aging of a commercial Al-Mg-Si-Cu alloy during equal channel angular extrusion process, *Journal of Alloys and Compounds*, **502**(1), 59-62 (2010)
- 68. M. Aghaie-Khafri, D. Azimi-Yancheshmeh, The Study of an Al-Fe-Si Alloy After Equal-Channel Angular Pressing (ECAP) and Subsequent Semisolid Heating, *Jom*, **64**(5), 585-592 (2012)
- 69. G. Khalaj, M.J. Khalaj, A. Nazari, Microstructure and hot deformation behavior of AlMg6 alloy produced by equal-channel angular pressing, *Materials Science and Engineering a-Structural Materials Properties Microstructure and Processing*, **542**, 15-20 (2012)
- 70. R. Haghayeghi, P. Kapranos, An investigation on work hardening of Al-1%Mg processed by Equal Channel Angular Pressing, *Materials Letters*, **129**, 182-184 (2014)
- 71. S.R. Bahadori, K. Dehghani, F. Bakhshandeh, Microstructural homogenization of ECAPed copper through post-rolling, *Materials Science and Engineering a-Structural Materials Properties Microstructure and Processing*, **588**, 260-264 (2013)
- 72. S.R. Bahadori, K. Dehghani, F. Bakhshandeh, Microstructure, texture and mechanical properties of pure copper processed by ECAP and subsequent cold rolling, *Materials Science and Engineering a-Structural Materials Properties Microstructure and Processing*, **583**, 36-42 (2013)
- 73. S.R. Bahadori, K. Dehghani, Influence of Intermediate Annealing on the Nanostructure and Mechanical Properties of Pure Copper Processed by Equal Channel Angular Pressing and Cold Rolling, *Metallurgical and Materials Transactions a-Physical Metallurgy and Materials Science*, **46A**(7), 2796-2802 (2015)

74. S.R. Bar Bahadori, K. Dehghani, S. Mousavi, Comparison of microstructure and mechanical properties of pure copper processed by twist extrusion and equal channel angular Pressing, *Materials Letters*, **152**, 48-52 (2015)

75. J. Nemati, G.H. Majzoobi, S. Sulaiman, B. Baharudin, M.A.A. Hanim, Finite element and metallurgical study of properties of deformed pure copper by ECAE at various strain rates, *Proceedings of the Institution of Mechanical Engineers Part C-Journal of Mechanical Engineering Science*, **228**(9), 1461-1473 (2014)

76. J. Nemati, G.H. Majzoobi, S. Sulaiman, B. Baharudin, M.A.A. Hanim, Improvements in the microstructure and fatigue behavior of pure copper using equal channel angular extrusion, *International Journal of Minerals Metallurgy and Materials*, **21**(6), 569-576 (2014)

77. F. Salimyanfard, M.R. Toroghinejad, F. Ashrafizadeh, M. Hoseini, J.A. Szpunar, Textural evaluation of copper produced by equal channel angular pressing with routes A and B-30, *Materials Science and Engineering a-Structural Materials Properties Microstructure and Processing*, **527**(23), 6260-6269 (2010)

78. F. Salimyanfard, M.R. Toroghinejad, F. Ashrafizadeh, M. Hoseini, J.A. Szpunar, Investigation of texture and mechanical properties of copper processed by new route of equal channel angular pressing, *Materials & Design*, **44**, 374-381 (2013)

79. F. Salimyanfard, M.R. Toroghinejad, F. Ashrafizadeh, M. Jafari, EBSD analysis of nano-structured copper processed by ECAP, *Materials Science and Engineering a-Structural Materials Properties Microstructure and Processing*, **528**(16-17), 5348-5355 (2011)

80. O. Nejadseyfi, A. Shokuhfar, V. Moodi, Segmentation of copper alloys processed by equal-channel angular pressing, *Transactions of Nonferrous Metals Society of China*, **25**(8), 2571-2580 (2015)

81. S.H. Nedjad, F.H. Nasab, M.R.M. Garabagh, S.R. Damadi, M.N. Ahmadabadi, X-Ray Diffraction Study on the Strain Anisotropy and Dislocation Structure of Deformed Lath Martensite, *Metallurgical and Materials Transactions a-Physical Metallurgy and Materials Science*, **42A**(8), 2493-2497 (2011)

82. F. Hajiakbari, M. Nili-Ahmabadi, B. Poorganji, T. Furuhara, Control of austenite to martensite transformation through equal channel angular pressing aided by thermodynamic calculations, *Acta Materialia*, **58**(8), 3073-3078 (2010)

83. M. Nili-Ahmabadi, F.H. Akbari, F. Rad, Z. Karimi, M. Iranpour, B. Poorganji, T. Furuhara, Microstructural Evolution of Bainitic Steel Severely Deformed by Equal Channel Angular Pressing, *Journal of Nanoscience and Nanotechnology*, **10**(9), 5986-5993 (2010)

84. M. Nili-Ahmabadi, H. Shirazi, M.I. Mobarake, B. Poorganji, S.H. Nedjad, T. Furuhara, Mechanical Properties Evaluations of an Age Hardenable Martensitic Steel Deformed by Equal Channel Angular Pressing, *Journal of Nanoscience and Nanotechnology*, **10**(9), 6182-6185 (2010)

85. H. Shirazi, M. Nili-Ahmabadi, A. Fatehi, S.H. Nedjad, Effect of Severe Plastic Deformation on Mechanical Properties of Fe-Ni-Mn High Strength Steel, Advances in Materials and Processing Technologies, Pts 1 and 2ed., M.S.J. Hashmi, B.S. Yilbas, S. Naher, Eds., 2010, p 16-23

86. E. Bagherpour, M. Reihanian, R. Ebrahimi, On the capability of severe plastic deformation of twining induced plasticity (TWIP) steel, *Materials & Design*, **36**, 391-395 (2012)

87. N. Forouzanmehr, N. Nili-Ahmadabadi, On the atomic force microscopy characterization of void evolution in severely plastic deformed pure iron, 6th International Conference on Nanomaterials by Severe Plastic Deformationed., B. Beausir, O. Bouaziz, E. Bouzy, T. Grosdidier, L.S. Toth, Eds., 2014

88. M. Toofaninejad, M.N. Ahmadabadi, Effect of equal channel angular pressing on the microstructure and mechanical properties of AISI type 304 austenitic stainless steel, Ultrafine Grained and Nano-Structured Materials Ived., M.H. Parsa, Ed., 2014, p 86-90

89. K. Hajizadeh, H. Maleki-Ghaleh, A. Arabi, Y. Behnamian, E. Aghaie, A. Farrokhi, M.G. Hosseini, M.H. Fathi, Corrosion and biological behavior of nanostructured 316L stainless steel processed by severe plastic deformation, *Surface and Interface Analysis*, **47**(10), 978-985 (2015)

90. H. Maleki-Ghaleh, K. Hajizadeh, E. Aghaie, S.G. Alamdar, M.G. Hosseini, M.H. Fathi, K. Ozaltin, K.J. Kurzydlowski, Effect of Equal Channel Angular Pressing Process on the Corrosion Behavior of Type 316L Stainless Steel in Ringer's Solution, *Corrosion*, **71**(3), 367-375 (2015)

91. M. Hoseini, A. Shahryari, S. Omanovic, J.A. Szpunar, Comparative effect of grain size and texture on the corrosion behaviour of commercially pure titanium processed by equal channel angular pressing, *Corrosion Science*, **51**(12), 3064-3067 (2009)

92. K. Hajizadeh, B. Eghbali, K. Topolski, K.J. Kurzydlowski, Ultra-fine grained bulk CP-Ti processed by multi-pass ECAP a warm deformation region, *Materials Chemistry and Physics*, **143**(3), 1032-1038 (2014)

93. K. Hajizadeh, S.G. Alamdar, B. Eghbali, Stored energy and recrystallization kinetics of ultrafine grained titanium processed by severe plastic deformation, *Physica B-Condensed Matter*, **417**, 33-38 (2013)

94. K. Hajizadeh, B. Eghbali, Effect of two-step severe plastic deformation on the microstructure and mechanical properties of commercial purity titanium, *Metals and Materials International*, **20**(2), 343-350 (2014)

95. H. Maleki-Ghaleh, K. Hajizadeh, A. Hadjizadeh, M.S. Shakeri, S.G. Alamdar, S. Masoudfar, E. Aghaie, M. Javidi, J. Zdunek, K.J. Kurzydlowski, Electrochemical and cellular behavior of ultrafine-grained titanium in vitro, *Materials Science & Engineering C-Materials for Biological Applications*, **39**, 299-304 (2014)

96. C. Gode, S. Attarilar, B. Eghbali, M. Ebrahimi, Electrochemical Behavior of Equal Channel Angular Pressed Titanium for Biomedical Application, 4th International Congress in Advances in Applied Physics and Materials Scienceed., A.Y. Oral, Z.B. Bahsi, M. Ozer, M. Sezer, M.E. Akoz, Eds., 2015

97. F. Ahmadi, M. Farzin, M. Meratian, S.M. Loeian, M.R. Forouzan, Improvement of ECAP process by imposing ultrasonic vibrations, *International Journal of Advanced Manufacturing Technology*, **79**(1-4), 503-512 (2015)

98. S.M. Masoudpanah, R. Mahmudi, Effects of rare-earth elements and Ca additions on the microstructure and mechanical properties of AZ31 magnesium alloy processed by ECAP, *Materials Science and Engineering a-Structural Materials Properties Microstructure and Processing*, **526**(1-2), 22-30 (2009)

99. S.M. Masoudpanah, R. Mahmudi, Effects of rare earth elements and Ca additions on high temperature mechanical properties of AZ31 magnesium alloy processed by ECAP, *Materials Science and Engineering a-Structural Materials Properties Microstructure and Processing*, **527**(16-17), 3685-3689 (2010)

100. S.M. Masoudpanah, R. Mahmudi, The microstructure, tensile, and shear deformation behavior of an AZ31 magnesium alloy after extrusion and equal channel angular pressing, *Materials & Design*, **31**(7), 3512-3517 (2010)
101. Y. Radi, R. Mahmudi, Effect of Al<sub>2</sub>O<sub>3</sub> nano-particles on the microstructural stability of AZ31 Mg alloy after equal channel angular pressing, *Materials Science and Engineering a-Structural Materials Properties Microstructure and Processing*, **527**(10-11), 2764-2771 (2010)
102. S.M. Masoudpanah, R. Mahmudi, T.G. Langdon, Correlation between shear punch and tensile measurements for an AZ31 Mg alloy processed by equal-channel angular pressing, *Kovove Materialy-Metallic Materials*, **49**(1), 43-50 (2011)
103. S.A. Torbati-Sarraf, R. Mahmudi, Microstructure and mechanical properties of extruded and ECAPed AZ31 Mg alloy, grain refined with Al-Ti-C master alloy, *Materials Science and Engineering a-Structural Materials Properties Microstructure and Processing*, **527**(15), 3515-3520 (2010)
104. F. Fereshteh-Sanee, F. Akbaripanah, H.K. Kim, R. Mahmudi, Effects of extrusion and equal channel angular pressing on the microstructure, tensile and fatigue behaviour of the wrought magnesium alloy AZ80, *Fatigue & Fracture of Engineering Materials & Structures*, **35**(12), 1167-1172 (2012)
105. F. Akbaripanah, F. Fereshteh-Sanee, R. Mahmudi, H.K. Kim, The influences of extrusion and equal channel angular pressing (ECAP) processes on the fatigue behavior of AM60 magnesium alloy, *Materials Science and Engineering a-Structural Materials Properties Microstructure and Processing*, **565**, 308-316 (2013)
106. F. Akbaripanah, F. Fereshteh-Sanee, R. Mahmudi, H.K. Kim, Microstructural homogeneity, texture, tensile and shear behavior of AM60 magnesium alloy produced by extrusion and equal channel angular pressing, *Materials & Design*, **43**, 31-39 (2013)
107. R. Jahadi, M. Sedighi, H. Jahed, ECAP effect on the micro-structure and mechanical properties of AM30 magnesium alloy, *Materials Science and Engineering a-Structural Materials Properties Microstructure and Processing*, **593**, 178-184 (2014)
108. M. Karami, R. Mahmudi, Shear punch superplasticity in equal-channel angularly pressed Mg-12Li-1Zn alloy, *Materials Science and Engineering a-Structural Materials Properties Microstructure and Processing*, **576**, 156-159 (2013)
109. M. Sarebanzadeh, R. Roumina, R. Mahmudi, G.H. Wu, H.R.J. Nodooshan, Enhancement of superplasticity in a fine-grained Mg-3Gd-1Zn alloy processed by equal-channel angular pressing, *Materials Science and Engineering a-Structural Materials Properties Microstructure and Processing*, **646**, 249-253 (2015)
110. S.R. Motlagh, M.H. Maghsoudi, S. Serajzadeh, Softening behaviour of alumina reinforced copper processed by equal channel angular pressing, *Materials Science and Technology*, **30**(2), 220-226 (2014)
111. H. Monshat, S. Serajzadeh, J.M. Akhgar, A. Kamankesh, Effect of strain path change on mechanical properties and final microstructure of Cu-Al<sub>2</sub>O<sub>3</sub> in equal channel angular pressing, *Materials Science and Technology*, **29**(2), 210-218 (2013)
112. R. Derakhshandeh, A.J. Jahromi, An investigation on the capability of equal channel angular pressing for consolidation of aluminum and aluminum composite powder, *Materials & Design*, **32**(6), 3377-3388 (2011)

113. R.D. Haghghi, S.A.J. Jahromi, A. Moresedgh, M.T. Khorshid, A Comparison Between ECAP and Conventional Extrusion for Consolidation of Aluminum Metal Matrix Composite, *Journal of Materials Engineering and Performance*, **21**(9), 1885-1892 (2012)
114. R.D. Haghghi, Effect of ECAP and extrusion on particle distribution in Al-nano-Al<sub>2</sub>O<sub>3</sub> composite, *Bulletin of Materials Science*, **38**(5), 1205-1212 (2015)
115. A. Hassani, M. Zabihi, High strain rate superplasticity in a nano-structured Al-Mg/SiCP composite severely deformed by equal channel angular extrusion, *Materials & Design*, **39**, 140-150 (2012)
116. I. Sadeghi, S. Serajzadeh, Mechanical behavior during aging of plastically deformed AA6061-SiCp composite in different temperatures, *Proceedings of the Institution of Mechanical Engineers Part L-Journal of Materials-Design and Applications*, **226**(L4), 322-329 (2012)
117. S. Mirab, M. Nili-Ahmabadi, On the flow and mechanical behavior of Al matrix composite reinforced by nickel based (90% Ni-10% Cr) wires during equal channel angular pressing, *Materials Science and Engineering a-Structural Materials Properties Microstructure and Processing*, **583**, 43-51 (2013)
118. P. Eslami, A.K. Taheri, An investigation on diffusion bonding of aluminum to copper using equal channel angular extrusion process, *Materials Letters*, **65**(12), 1862-1864 (2011)
119. M. Zebardast, A.K. Taheri, The cold welding of copper to aluminum using equal channel angular extrusion (ECAE) process, *Journal of Materials Processing Technology*, **211**(6), 1034-1043 (2011)
120. P. Eslami, A.K. Taheri, M. Zebardast, A Comparison Between Cold-Welded and Diffusion-Bonded Al/Cu Bimetallic Rods Produced by ECAE Process, *Journal of Materials Engineering and Performance*, **22**(10), 3014-3023 (2013)
121. R. Mahmudi, R. Alizadeh, A.R. Geranmayeh, Enhanced superplasticity in equal-channel angularly pressed Sn-5Sb alloy, *Scripta Materialia*, **64**(6), 521-524 (2011)
122. R. Mahmudi, R. Alizadeh, S. Azhari, Strain rate sensitivity of equal-channel angularly pressed Sn-5Sb alloy determined by shear punch test, *Materials Letters*, **97**, 44-46 (2013)
123. M.H. Paydar, M. Reihanian, E. Bagherpour, M. Sharifzadeh, M. Zarinejad, T.A. Dean, Equal channel angular pressing-forward extrusion (ECAP-FE) consolidation of Al particles, *Materials & Design*, **30**(3), 429-432 (2009)
124. H. Shahmir, M. Nili-Ahmabadi, M. Mansouri-Arani, T.G. Langdon, The processing of NiTi shape memory alloys by equal-channel angular pressing at room temperature, *Materials Science and Engineering a-Structural Materials Properties Microstructure and Processing*, **576**, 178-184 (2013)
125. H. Shahmir, M. Nili-Ahmabadi, T.G. Langdon, Shape memory effect of NiTi alloy processed by equal-channel angular pressing followed by post deformation annealing, *IOP Conference Series: Materials Science and Engineering*, **63**, 012111 (2014)
126. H. Shahmir, M. Nili-Ahmabadi, M. Mansouri-Arani, A. Khajezade, T.G. Langdon, Evaluating a New Core-Sheath Procedure for Processing Hard Metals by Equal-Channel Angular Pressing, *Advanced Engineering Materials*, **16**(7), 918-926 (2014)
127. H. Shahmir, M. Nili-Ahmabadi, M. Mansouri-Arani, A. Khajezade, T.G. Langdon, Evaluating the Room Temperature ECAP Processing of a NiTi Alloy via Simulation and Experiments, *Advanced Engineering Materials*, **17**(4), 532-538 (2015)

128. H. Shahmir, M. Nili-Ahmabadi, A. Razzaghi, M. Mohammadi, C.T. Wang, J.M. Jung, H.S. Kim, T.G. Langdon, Using dilatometry to study martensitic stabilization and recrystallization kinetics in a severely deformed NiTi alloy, *Journal of Materials Science*, **50**(11), 4003-4011 (2015)

129. H. Shahmir, M. Nili-Ahmabadi, C.T. Wang, J.M. Jung, H.S. Kim, T.G. Langdon, Annealing behavior and shape memory effect in NiTi alloy processed by equal-channel angular pressing at room temperature, *Materials Science and Engineering a-Structural Materials Properties Microstructure and Processing*, **629**, 16-22 (2015)

130. A.Q. Fan, L.Y. Zhou, C.H. Deng, L.Y. Zhu, Research and development of ultra-fine grain technology with equal channel angular extrusion processing, *Journal of Iron and Steel Research*, **24**(7), (2012)

131. L.M. Lei, X. Huang, R. Duan, C.X. Cao, Progress in equal channel angular extrusion process, *Cailiao Gongcheng/Journal of Materials Engineering*, (5), 76-80 (2009)

132. R.Z. Valiev, Y. Estrin, Z. Horita, T.G. Langdon, M.J. Zehetbauer, Y.T. Zhu, Fundamentals of superior properties in bulk nanoSPD materials, *Materials Research Letters*, **4**(1), 1-21 (2016)

133. C.P. Hong, J. Kim, Development of an advanced rheocasting process and its applications, *Solid State Phenomena*, **116-117**, 44-53 (2006)

134. J. Jiang, Y. Wang, S. Luo, Application of equal channel angular extrusion to semi-solid processing of magnesium alloy, *Materials Characterization*, **58**(2), 190-196 (2007)

135. S. Liang, R.S. Chen, E.H. Han, Semisolid microstructural evolution of equal channel angular extruded Mg-Al alloy during partial remelting, *Solid State Phenomena*, **141-143**, 557-562 (2008)

136. M. Kubota, X. Wu, W. Xu, K. Xia, Mechanical properties of bulk aluminium consolidated from mechanically milled particles by back pressure equal channel angular pressing, *Materials Science and Engineering: A*, **527**(24–25), 6533-6536 (2010)

137. S. XIANG, K. MATSUKI, N. TAKATSUJI, M. TOKIZAWA, T. YOKOTE, J. KUSUI, K. YOKOE, Microstructure and mechanical properties of PM 2024Al-3Fe-5Ni alloy consolidated by a new process, equal channel angular pressing, *Journal of Materials Science Letters*, **16**(21), 1725-1727 (1997)

138. K. Matsuki, T. Aida, T. Takeuchi, J. Kusui, K. Yokoe, Microstructural characteristics and superplastic-like behavior in aluminum powder alloy consolidated by equal-channel angular pressing, *Acta Materialia*, **48**(10), 2625-2632 (2000)

139. X.L. Wu, K. Xia, Synthesis of bulk materials by equal channel angular consolidation of particles, Materials Science Forum, 2006, Trans Tech Publ, pp 233-238

140. K.T. Hartwig, H. Zapata, A. Parasiris, S.N. Mathaudhu, Consolidation of metallic powders by equal channel angular extrusion, Powder Materials: Current Research and Industrial Practices, 2001, pp 211-221

141. K. Matsuki, T. Aida, T. Takeuchi, J. Kusui, Microstructure and mechanical properties of 2024Al-Fe-Ni PM alloys consolidated by equal channel angular pressing, *Materials Science Forum*, **331-337**, 1215-1220 (2000)

142. K.I. Elkhodary, H.G. Salem, M.A. Zikry, Equal Channel Angular Pressing of Canned 2124-Al Compacts: Processing, Experiments, and Modeling, *Metallurgical and Materials Transactions A*, **39**(9), 2184-2192 (2008)

143. I. Baker, D. Iliescu, Y. Liao, Containerless consolidation of Mg powders using ECAE, *Materials and Manufacturing Processes*, **25**(12), 1381-1384 (2010)

144. H.C. Lee, C.G. Chao, T.F. Liu, C.Y. Lin, H.C. Wang, Effect of temperature and extrusion pass on the consolidation of magnesium powders using equal channel angular extrusion, *Materials Transactions*, **54**(5), 765-768 (2013)

145. M.S.S. Saravanan, S.P.K. Babu, K. Sivaprasad, B. Ravisankar, P. Susila, B.S. Murty, Consolidation of CNT-reinforced AA4032 nanocomposites by ECAP, *International Journal of Nanoscience*, **10**(1-2), 233-236 (2011)

146. A. Parasiris, K.T. Hartwig, Consolidation of advanced WC–Co powders, *International Journal of Refractory Metals and Hard Materials*, **18**(1), 23-31 (2000)

147. A. Parasiris, K. Hartwig, M. Srinivasan, Formation/consolidation of WC-Co cermets by simple shear, *Scripta Materialia*, **42**(9), 875-880 (2000)

148. C. Haase, R. Lapovok, H.P. Ng, Y. Estrin, Production of Ti–6Al–4V billet through compaction of blended elemental powders by equal-channel angular pressing, *Materials Science and Engineering: A*, **550**, 263-272 (2012)

149. H.P. Ng, C. Haase, R. Lapovok, Y. Estrin, Improving sinterability of Ti–6Al–4V from blended elemental powders through equal channel angular pressing, *Materials Science and Engineering: A*, **565**, 396-404 (2013)

150. X. Kaculi, M.N. Srinivasan, K.T. Hartwig, Use of High Intensity Milling and Equal Channel Angular Extrusion to Produce and Consolidate Nanostructured Titanium Silicide, (37149), 871-877 (2003) Journal?

151. X.T. Kaculi, M. Srinivasan, K. Hartwig, Use of mechanical alloying and equal channel angular extrusion to produce nanostructured titanium silicide, Proceedings of IMECE, 2003 ASME International Mechanical Engineering Congress & Exposition Washington, DC, 2003

152. M. Haouaoui, I. Karaman, Nanostructured Bulk Cu Obtained by Consolidation of Cu Particles Using Equal Channel Angular Extrusion, Powder Materials: Current Research and Industrial Practices IIIed., John Wiley & Sons, Inc., 2010, p 125-138

153. A.V. Nagasekhar, Y. Tick-Hon, K.S. Ramakanth, Mechanics of single pass equal channel angular extrusion of powder in tubes, *Applied Physics A*, **85**(2), 185-194 (2006)

154. K.A. Darling, M.A. Tschopp, R.K. Guduru, W.H. Yin, Q. Wei, L.J. Kecske, Microstructure and mechanical properties of bulk nanostructured Cu–Ta alloys consolidated by equal channel angular extrusion, *Acta Materialia*, **76**, 168-185 (2014)

155. O. Senkov, J. Scott, S. Senkova, D. Miracle, ECAE consolidation of amorphous aluminum alloy powders, International Symposium on Processing and Fabrication of Advanced Materials XII, TS Srivatsan and RA Varin (Eds.) ASM International, Materials Park, OH, 2004, pp 346-357

156. J. Robertson, J.T. Im, I. Karaman, K.T. Hartwig, I.E. Anderson, Consolidation of amorphous copper based powder by equal channel angular extrusion, *Journal of Non-Crystalline Solids*, **317**(1–2), 144-151 (2003)

157. P. Quang, Y.G. Jeong, S.C. Yoon, S.H. Hong, H.S. Kim, Consolidation of 1 vol.% carbon nanotube reinforced metal matrix nanocomposites via equal channel angular pressing, *Journal of Materials Processing Technology*, **187–188**, 318-320 (2007)

158. Q. Pham, Y.G. Jeong, S.H. Hong, H.S. Kim, Equal channel angular pressing of carbon nanotube reinforced metal matrix nanocomposites, *Key Engineering Materials*, **326-328**, 325-328 (2006)

159. S.C. Yoon, H.S. Kim, Equal channel angular pressing of metallic powders for nanostructured materials, *Materials Science Forum*, **503-504**, 221-226 (2006)

160. R.D. Haghghi, Effect of ECAP and extrusion on particle distribution in Al-nano-Al<sub>2</sub>O<sub>3</sub> composite, *Bulletin of Materials Science*, **38**(5), 1205-1212 (2015)
161. R. Casati, A. Fabrizi, A. Tuissi, K. Xia, M. Vedani, ECAP consolidation of Al matrix composites reinforced with in-situ  $\gamma$ -Al<sub>2</sub>O<sub>3</sub> nanoparticles, *Materials Science and Engineering: A*, **648**, 113-122 (2015)
162. M. Balog, P. Yu, M. Qian, M. Behulova, P. Svec Sr, R. Cicka, Nanoscaled Al-AlN composites consolidated by equal channel angular pressing (ECAP) of partially in situ nitrided Al powder, *Materials Science and Engineering: A*, **562**, 190-195 (2013)
163. C. Poletti, M. Balog, T. Schubert, V. Liedtke, C. Edtmaier, Production of titanium matrix composites reinforced with SiC particles, *Composites Science and Technology*, **68**(9), 2171-2177 (2008)
164. E.W. Lui, W. Xu, K. Xia, Nanostructured dual phase Ti-Al through consolidation of particles by severe plastic deformation, *Materials Science Forum*, 2011 63-68
165. E.W. Lui, W. Xu, X. Wu, K. Xia, Multiscale two-phase Ti-Al with high strength and plasticity through consolidation of particles by severe plastic deformation, *Scripta Materialia*, **65**(8), 711-714 (2011)
166. R. Yarra, P. Venkatachalam, S. Ramesh Kumar, B. Ravisankar, K. Jayasankar, P.S. Mukherjee, Densification of Al-Y<sub>2</sub>O<sub>3</sub> composite powder by equal channel angular pressing, *Transactions of the Indian Institute of Metals*, **63**(5), 813-817 (2010)
167. S.E. Hernández-Martínez, J.J. Cruz-Rivera, R. Martínez-Sánchez, C.G. Garay-Reyes, J.A. Muñoz-Bolaños, J.M. Cabrera, J.L. Hernández-Rivera, Consolidation of AA 7075-2 wt% ZrO<sub>2</sub> Composite Powders by Severe Plastic Deformation via ECAP, *Acta Metallurgica Sinica (English Letters)*, **29**(10), 895-901 (2016)
168. R. Derakhshandeh-Haghghi, S.A. Jenabali Jahromi, The Effect of Multi-pass Equal-Channel Angular Pressing (ECAP) for Consolidation of Aluminum-Nano Alumina Composite Powder on Wear Resistance, *Journal of Materials Engineering and Performance*, **25**(2), 687-696 (2016)
169. K. Xia, X. Wu, Back pressure equal channel angular consolidation of pure Al particles, *Scripta Materialia*, **53**(11), 1225-1229 (2005)
170. K. Xia, X. Wu, T. Honma, S.P. Ringer, Ultrafine pure aluminium through back pressure equal channel angular consolidation (BP-ECAC) of particles, *Journal of Materials Science*, **42**(5), 1551-1560 (2007)
171. M. Kubota, X. Wu, W. Xu, K. Xia, Bulk Al materials from back pressure equal channel angular consolidation of mechanically milled particles, *Materials Science Forum*, 2008, p 428-433
172. X. Wu, W. Xu, K. Xia, Pure aluminum with different grain size distributions by consolidation of particles using equal-channel angular pressing with back pressure, *Materials Science and Engineering A*, **493**(1-2), 241-245 (2008)
173. M. Moss, R. Lapovok, C.J. Bettles, The equal channel angular pressing of magnesium and magnesium alloy powders, *JOM*, **59**(8), 54-57 (2007)
174. X. Wu, W. Xu, M. Kubota, K. Xia, Bulk Mg produced by back pressure equal channel angular consolidation (BP- ECAC), *Materials Science Forum*, **584-586**, 114-118 (2008)
175. X. Wu, K. Xia, Back pressure equal channel angular consolidation—Application in producing aluminium matrix composites with fine flyash particles, *Journal of Materials Processing Technology*, **192-193**, 355-359 (2007)

176. W. Xu, X. Wu, T. Honma, S.P. Ringer, K. Xia, Nanostructured Al-Al<sub>2</sub>O<sub>3</sub> composite formed in situ during consolidation of ultrafine Al particles by back pressure equal channel angular pressing, *Acta Materialia*, **57**(14), 4321-4330 (2009)

177. S. Goussous, W. Xu, X. Wu, K. Xia, Al-C nanocomposites consolidated by back pressure equal channel angular pressing, *Composites Science and Technology*, **69**(11–12), 1997-2001 (2009)

178. A.V. Nagasekhar, Y. Tick-Hon, H.P. Seow, Influence of equal channel angular extrusion processing routes on consolidation of intermetallics, TMS Annual Meeting, 2006, pp 203-208

179. W. Xu, X. Wu, D. Sadedin, K. Xia, Equal channel angular consolidation and deformation of titanium based alloys, *Materials Forum*, **32**, 29-34 (2007)

180. R. Lapovok, D. Tomus, C. Bettles, Shear deformation with imposed hydrostatic pressure for enhanced compaction of powder, *Scripta Materialia*, **58**(10), 898-901 (2008)

181. R. Lapovok, D. Tomus, B.C. Muddle, Low-temperature compaction of Ti-6Al-4V powder using equal channel angular extrusion with back pressure, *Materials Science and Engineering: A*, **490**(1–2), 171-180 (2008)

182. W. Xu, X. Wu, X. Wei, E.W. Lui, K. Xia, Nanostructured multi-phase titanium-based particulate composites consolidated by Severe plastic deformation, *International Journal of Powder Metallurgy*, **50**(1), 49-56 (2014)

183. R.Y. Lapovok, The role of back-pressure in equal channel angular extrusion, *Journal of Materials Science*, **40**(2), 341-346 (2005)

184. B. Mani, M. Jahedi, M.H. Paydar, Consolidation of commercial pure aluminum powder by torsional-equal channel angular pressing (T-ECAP) at room temperature, *Powder Technology*, **219**, 1-8 (2012)

185. B. Mani, M.H. Paydar, Application of forward extrusion-equal channel angular pressing (FE-ECAP) in fabrication of aluminum metal matrix composites, *Journal of Alloys and Compounds*, **492**(1-2), 116-121 (2010)

186. B. Mani, M.H. Paydar, Application of forward extrusion-equal channel angular pressing (FE-ECAP) in fabrication of aluminum metal matrix composites, Proceedings of the World Powder Metallurgy Congress and Exhibition, World PM 2010, 2010

187. A.V. Nagasekhar, S.C. Yoon, J.H. Yoo, S.Y. Kang, S.C. Baik, M.I.A. El Aal, H.S. Kim, Plastic flow and strain homogeneity of an equal channel angular pressing process enhanced through forward extrusion, *Materials Transactions*, **51**(5), 977-981 (2010)

188. V.M. Segal, Materials processing by simple shear, *Materials Science and Engineering: A*, **197**(2), 157-164 (1995)

189. Y. Iwahashi, J. Wang, Z. Horita, M. Nemoto, T.G. Langdon, Principle of equal-channel angular pressing for the processing of ultra-fine grained materials, *Scripta Materialia*, **35**(2), 143-146 (1996)

190. P.B. Prangnell, C. Harris, S.M. Roberts, Finite element modelling of equal channel angular extrusion, *Scripta Materialia*, **37**(7), 983-989 (1997)

191. D.P. DeLo, S.L. Semiatin, Finite-element modeling of nonisothermal equal-channel angular extrusion, *Metallurgical and Materials Transactions A: Physical Metallurgy and Materials Science*, **30**(5), 1391-1402 (1999)

192. S.L. Semiatin, D.P. Delo, E.B. Shell, Effect of material properties and tooling design on deformation and fracture during equal channel angular extrusion, *Acta Materialia*, **48**(8), 1841-1851 (2000)

193. H.S. Kim, Finite element analysis of equal channel angular pressing using a round corner die, *Materials Science and Engineering A*, **315**(1-2), 122-128 (2001)
194. H.S. Kim, M.H. Seo, S.I. Hong, Plastic deformation analysis of metals during equal channel angular pressing, *Journal of Materials Processing Technology*, **113**(1-3), 622-626 (2001)
195. R. Srinivasan, Computer simulation of the equichannel angular extrusion (ECAE) process, *Scripta Materialia*, **44**(1), 91-96 (2001)
196. J.Y. Suh, H.S. Kim, J.W. Park, J.Y. Chang, Finite element analysis of material flow in equal channel angular pressing, *Scripta Materialia*, **44**(4), 677-681 (2001)
197. S.C. Balk, Y. Estrin, H.S. Kim, H.T. Jeong, R.J. Hellmig, Calculation of deformation behavior and texture evolution during equal channel angular pressing of IF steel using dislocation based modeling of strain hardening, *Materials Science Forum*, **408-412**, 697-702 (2002)
198. H.S. Kim, Evaluation of strain rate during equal-channel angular pressing, *Journal of Materials Research*, **17**(1), 172-179 (2002)
199. H.S. Kim, Finite element analysis of deformation behaviour of metals during equal channel multi-angular pressing, *Materials Science and Engineering A*, **328**(1), 317-323 (2002)
200. H.S. Kim, M.H. Seo, S.I. Hong, Finite element analysis of equal channel angular pressing of strain rate sensitive metals, *Journal of Materials Processing Technology*, **130-131**, 497-503 (2002)
201. H.S. Kim, M.H. Seo, C.S. Oh, S.J. Kim, Equal Channel Angular Pressing of Metallic Powders, *Materials Science Forum*, 2003, p 89-92
202. Q.X. Pei, B.H. Hu, C. Lu, Y.Y. Wang, A finite element study of the temperature rise during equal channel angular pressing, *Scripta Materialia*, **49**(4), 303-308 (2003)
203. J.H. Lee, I.H. Son, Y.T. Im, Finite element investigation of equal channel angular extrusion process, *Materials Transactions*, **45**(7), 2165-2171 (2004)
204. S.C. Lee, S.Y. Ha, K.T. Kim, S.M. Hwang, L.M. Huh, H.S. Chung, Finite element analysis for deformation behavior of an aluminum alloy composite containing SiC particles and porosities during ECAP, *Materials Science and Engineering A*, **371**(1-2), 306-312 (2004)
205. S. Li, I.J. Beyerlein, C.T. Necker, D.J. Alexander, M. Bourke, Heterogeneity of deformation texture in equal channel angular extrusion of copper, *Acta Materialia*, **52**(16), 4859-4875 (2004)
206. H.S. Kim, Y. Estrin, Microstructural modelling of equal channel angular pressing for producing ultrafine grained materials, *Materials Science and Engineering A*, **410-411**, 285-289 (2005)
207. W.J. Zhao, H. Ding, Y.P. Ren, S.M. Hao, J. Wang, J.T. Wang, Finite element simulation of deformation behavior of pure aluminum during equal channel angular pressing, *Materials Science and Engineering A*, **410-411**, 348-352 (2005)
208. A.A. Gazder, S. Li, F.H. Dalla Torre, I.J. Beyerlein, C.F. Gu, C.H.J. Davies, E.V. Pereloma, Progressive texture evolution during equal channel angular extrusion, *Materials Science and Engineering A*, **437**(2), 259-267 (2006)
209. I.V. Alexandrov, I.N. Budilov, G. Krallics, H.S. Kim, S.C. Yoon, A.A. Smolyakov, A.I. Korshunov, V.P. Solovyev, Simulation of equal-channel angular extrusion pressing, *Materials Science Forum*, **503-504**, 201-208 (2006)

210. P.D. Wu, Y. Huang, D.J. Lloyd, Studying grain fragmentation in ECAE by simulating simple shear, *Scripta Materialia*, **54**(12), 2107-2112 (2006)

211. S.C. Yoon, M.H. Seo, H.S. Kim, Preform effect on the plastic deformation behavior of workpieces in equal channel angular pressing, *Scripta Materialia*, **55**(2), 159-162 (2006)

212. R.B. Figueiredo, P.R. Cetlin, T.G. Langdon, The processing of difficult-to-work alloys by ECAP with an emphasis on magnesium alloys, *Acta Materialia*, **55**(14), 4769-4779 (2007)

213. C. Xu, K. Xia, T.G. Langdon, The role of back pressure in the processing of pure aluminum by equal-channel angular pressing, *Acta Materialia*, **55**(7), 2351-2360 (2007)

214. T. Inoue, Z. Horita, H. Somekawa, K. Ogawa, Effect of initial grain sizes on hardness variation and strain distribution of pure aluminum severely deformed by compression tests, *Acta Materialia*, **56**(20), 6291-6303 (2008)

215. A. Mishra, M. Martin, N.N. Thadhani, B.K. Kad, E.A. Kenik, M.A. Meyers, High-strain-rate response of ultra-fine-grained copper, *Acta Materialia*, **56**(12), 2770-2783 (2008)

216. A.V. Nagasekhar, H.S. Kim, Plastic deformation characteristics of cross-equal channel angular pressing, *Computational Materials Science*, **43**(4), 1069-1073 (2008)

217. S.C. Yoon, M.H. Seo, A. Krishnaiah, H.S. Kim, Finite element analysis of rotary-die equal channel angular pressing, *Materials Science and Engineering A*, **490**(1-2), 289-292 (2008)

218. H.S. Kim, Multi-scale finite element simulation of severe plastic deformation, *International Journal of Modern Physics B*, **23**(6-7), 1621-1626 (2009)

219. I. Balasundar, T. Raghu, Effect of friction model in numerical analysis of equal channel angular pressing process, *Materials and Design*, **31**(1), 449-457 (2010)

220. C. Lu, G.Y. Deng, A.K. Tieu, L.H. Su, H.T. Zhu, X.H. Liu, Crystal plasticity modeling of texture evolution and heterogeneity in equal channel angular pressing of aluminum single crystal, *Acta Materialia*, **59**(9), 3581-3592 (2011)

221. S. Xu, C. Jing, G. Ren, P. Liu, Finite element simulation of die design for warm equal channel angular extrusion process of AZ31 alloy and its experimental investigation, *Materials Science Forum*, **667-669**, 75-79 (2011)

222. S.H. Joo, S.C. Yoon, H.G. Jeong, S. Lee, H.S. Kim, Deformation behavior of consecutive workpieces in equal channel angular pressing of solid dies, *Journal of Materials Science*, **47**(22), 7877-7882 (2012)

223. M.S. Ghazani, B. Eghbali, Finite element simulation of cross equal channel angular pressing, *Computational Materials Science*, **74**, 124-128 (2013)

224. A. Sahai, R.S. Sharma, K. Hansraj, Evolution of strain in multipass hybrid equal channel angular pressing using 3D finite element analysis, *Materials Science Forum*, 2013, p 283-288

225. M. Sedighi, M. Mahmoodi, Residual stresses evaluation in equal channel angular rolled al 5083 by IHD technique: Investigation of two calculation methods, *Materials and Manufacturing Processes*, **28**(1), 85-90 (2013)

226. V. Bratov, E.N. Borodin, Comparison of dislocation density based approaches for prediction of defect structure evolution in aluminium and copper processed by ECAP, *Materials Science and Engineering A*, **631**, 10-17 (2015)

227. S. Bagherzadeh, K. Abrinia, Q. Han, Ultrasonic assisted equal channel angular extrusion (UAE) as a novel hybrid method for continuous production of ultra-fine grained metals, *Materials Letters*, **169**, 90-94 (2016)

228. F. Liu, Y. Liu, J. Wang, Estimation of average strain rate during equal-channel angular pressing, *Materials Science Forum*, 2016, p 419-425

229. I. Watanabe, D. Setoyama, Multiscale characterization of a polycrystalline aggregate subjected to severe plastic deformation with the finite element method, *Materials Transactions*, **57**(9), 1404-1410 (2016)

230. D.N. Lee, An upper-bound solution of channel angular deformation, *Scripta Materialia*, **43**(2), 115-118 (2000)

231. D.N. Lee, Upper-bound solution of channel angular deformation, *Scripta Materialia*, **43**(2), 115-118 (2000)

232. T. Aida, K. Matsuki, Z. Horita, T.G. Langdon, Estimating the equivalent strain in equal-channel angular pressing, *Scripta Materialia*, **44**(4), 575-579 (2001)

233. J. Alkorta, J. Gil Sevillano, A comparison of FEM and upper-bound type analysis of equal-channel angular pressing (ECAP), *Journal of Materials Processing Technology*, **141**(3), 313-318 (2003)

234. Y.H. Kim, X. Ma, P.D. Hodgson, M.R. Barnett, Multi equal channel angular pressing with rotational dies, *Materials Science Forum*, **426-432**, 2777-2782 (2003)

235. C.J. Luis Pérez, Upper bound analysis and FEM simulation of equal fillet radii angular pressing, *Modelling and Simulation in Materials Science and Engineering*, **12**(2), 205-214 (2004)

236. B.S. Altan, G. Purcek, I. Miskioglu, An upper-bound analysis for equal-channel angular extrusion, *Journal of Materials Processing Technology*, **168**(1), 137-146 (2005)

237. W. Wei, G. Chen, An upper bound solution analysis of equal channel angular pressing, *Journal of Metastable and Nanocrystalline Materials*, **23**, 109-112 (2005)

238. A.R. Eivani, A. Karimi Taheri, An upper bound solution of ECAE process with outer curved corner, *Journal of Materials Processing Technology*, **182**(1-3), 555-563 (2007)

239. A.R. Eivani, A. Karimi Taheri, The effect of dead metal zone formation on strain and extrusion force during equal channel angular extrusion, *Computational Materials Science*, **42**(1), 14-20 (2008)

240. C.J. Luis Pérez, R. Luri, Study of the ECAE process by the upper bound method considering the correct die design, *Mechanics of Materials*, **40**(8), 617-628 (2008)

241. R. Luri, C.J.L. Pérez, Upper bound analysis of the ECAE process by considering strain hardening materials and three-dimensional rectangular dies, *Journal of Manufacturing Science and Engineering, Transactions of the ASME*, **130**(5), 0510061-05100612 (2008)

242. A.R. Eivani, S. Ahmadi, E. Emadoddin, S. Valipour, A. Karimi Taheri, The effect of deformations passes on the extrusion pressure in axi-symmetric equal channel angular extrusion, *Computational Materials Science*, **44**(4), 1116-1125 (2009)

243. A.V. Perig, A.M. Laptev, P.A. Kakavas, Upper bound analysis of equal channel angular extrusion: Two-parameter rigid blocks approach and numerical verification, *Computational Plasticity X - Fundamentals and Applications*, 2009

244. M. Reihanian, R. Ebrahimi, M.M. Moshksar, Upper-bound analysis of equal channel angular extrusion using linear and rotational velocity fields, *Materials and Design*, **30**(1), 28-34 (2009)

245. K. Abrinia, M.J. Mirnia, A new generalized upper-bound solution for the ECAE process, *International Journal of Advanced Manufacturing Technology*, **46**(1-4), 411-421 (2010)

246. N. Medeiros, L.P. Moreira, J.D. Bressan, J.F.C. Lins, J.P. Gouvêa, Upper-bound sensitivity analysis of the ECAE process, *Materials Science and Engineering A*, **527**(12), 2831-2844 (2010)

247. K. Naroei, A. Karimi Taheri, A new model for prediction the strain field and extrusion pressure in ECAE process of circular cross section, *Applied Mathematical Modelling*, **34**(7), 1901-1917 (2010)

248. C.J.L. Pérez, R. Luri, Upper bound analysis of the ECAE process by considering circular cross-section and strain hardening materials, *Journal of Manufacturing Science and Engineering, Transactions of the ASME*, **132**(4), 0410031-04100314 (2010)

249. C. Şimşir, P. Karpuz, C.H. Gür, Quantitative analysis of the influence of strain hardening on equal channel angular pressing process, *Computational Materials Science*, **48**(3), 633-639 (2010)

250. M. Vaseghi, A.K. Taheri, H.S. Kim, Upper bound analysis of deformation and dynamic ageing behavior in elevated temperature equal channel angular pressing of Al-Mg-Si alloys, *Metals and Materials International*, **16**(3), 363-369 (2010)

251. Y.Z. Li, K.M. Xue, P. Li, An upper-bound solution to extrusion force of equal channel angular pressing with back pressure, *Suxing Gongcheng Xuebao/Journal of Plasticity Engineering*, **18**(2), 28-32 (2011)

252. R. Luri, C.J. Luis Pérez, Modeling of the processing force for performing ECAP of circular cross-section materials by the UBM, *International Journal of Advanced Manufacturing Technology*, **58**(9-12), 969-983 (2012)

253. F.R.F. Silva, N. Medeiros, L.P. Moreira, J.F.C. Lins, J.P. Gouvêa, Upper-bound and finite-element analyses of non-isothermal ECAP, *Materials Science and Engineering A*, **546**, 180-188 (2012)

254. A.M. Laptev, A.V. Perig, O.Y. Vyal, Analysis of equal channel angular extrusion by upper bound method and rigid block model, *Materials Research*, **17**(2), 359-366 (2014)

255. N. Medeiros, L.P. Moreira, Upper-bound analysis of die corner gap formation for strain-hardening materials in ECAP process, *Computational Materials Science*, **91**, 350-358 (2014)

256. A.V. Perig, 2D upper bound analysis of ecae through 20-Dies for a range of channel angles, *Materials Research*, **17**(5), 1226-1237 (2014)

257. K. Wei, P. Liu, Z. Ma, W. Wei, I.V. Alexandrov, J. Hu, An upper bound analysis of t-shaped equal channel angular pressing, *Acta Metallurgica Slovaca*, **21**(1), 4-12 (2015)

258. I. Beyerlein, R. Lebensohn, C. Tomé, Polycrystal constitutive modeling of ECAP: Texture and microstructural evolution, *Ultrafine Grained Materials*, **3**, 585-594 (2002)

259. I.J. Beyerlein, R.A. Lebensohn, C.N. Tomé, Polycrystal constitutive modeling of ECAP: Texture and microstructural evolution, TMS Annual Meeting, 2002, pp 585-594

260. S.C. Vogel, I.J. Beyerlein, M.A.M. Bourke, C.N. Tomé, P. Rangaswamy, C. Xu, T.G. Langdon, Texture in equal-channel angular pressed aluminum and nickel, *Materials Science Forum*, **408-412**, 673-678 (2002)

261. S. Li, I.J. Beyerlein, Modelling texture evolution in equal channel angular extrusion of bcc materials: Effects of processing route and initial texture, *Modelling and Simulation in Materials Science and Engineering*, **13**(4), 509-530 (2005)

262. S. Li, S.R. Kalidindi, I.J. Beyerlein, A crystal plasticity finite element analysis of texture evolution in equal channel angular extrusion, *Materials Science and Engineering A*, **410-411**, 207-212 (2005)

263. A.A. Nazarov, I.V. Alexandrov, I.J. Beyerlein, N.A. Enikeev, T.S. Orlova, A.E. Romanov, R.Z. Valiev, Modeling of grain refinement and texture evolution during equal-channel angular pressing by means of a combined visco-plastic self consistent/disclination model, *TMS Annual Meeting*, 2006, pp 215-220

264. I.J. Beyerlein, D.J. Alexander, C.N. Tomé, Plastic anisotropy in aluminum and copper pre-strained by equal channel angular extrusion, *Journal of Materials Science*, **42**(5), 1733-1750 (2007)

265. N.A. Enikeev, M.F. Abdullin, A.A. Nazarov, I.J. Beyerlein, Modelling grain refinement in fcc metals during equal-channel angular pressing by route "C", *International Journal of Materials Research*, **98**(3), 167-171 (2007)

266. I.V. Alexandrov, V.D. Sittikov, Crystallographic texture development in CP Ti subjected to ECAP, *Materials Science Forum*, **584-586**, 765-770 (2008)

267. M. Hoseini, M. Meratian, H. Li, J. Szpunar, Simulation of texture development in pure aluminum deformed by equal channel angular pressing, *Ceramic Transactions*, 2008, p 713-720

268. M. Hoseini, M. Meratian, H. Li, J.A. Szpunar, Texture simulation of aluminum rod during equal channel angular pressing, *Journal of Materials Science*, **43**(13), 4561-4566 (2008)

269. M. Kawasaki, I.J. Beyerlein, S.C. Vogel, T.G. Langdon, Characterization of creep properties and creep textures in pure aluminum processed by equal-channel angular pressing, *Acta Materialia*, **56**(10), 2307-2317 (2008)

270. S. Li, B.R. Donohue, S.R. Kalidindi, A crystal plasticity finite element analysis of cross-grain deformation heterogeneity in equal channel angular extrusion and its implications for texture evolution, *Materials Science and Engineering A*, **480**(1-2), 17-23 (2008)

271. G.G. Yapici, C.N. Tomé, I.J. Beyerlein, I. Karaman, S.C. Vogel, C. Liu, Plastic flow anisotropy of pure zirconium after severe plastic deformation at room temperature, *Acta Materialia*, **57**(16), 4855-4865 (2009)

272. M. Al-Maharbi, D. Foley, I. Karaman, I. Beyerlein, K.T. Hartwig, L.J. Kecske, S. Mathaudhu, Importance of crystallographic texture of AZ31B on flow stress anisotropy and tension-compression asymmetry, *Magnesium Technology*, 2010, pp 445-450

273. R.B. Figueiredo, I.J. Beyerlein, A.P. Zhilyaev, T.G. Langdon, Evolution of texture in a magnesium alloy processed by ECAP through dies with different angles, *Materials Science and Engineering A*, **527**(7-8), 1709-1718 (2010)

274. S. Li, Grain refinement efficiency in equal channel angular extrusion of FCC metals inferred from crystal plasticity simulations of slip activities, *Materials Science Forum*, **638-642**, 1971-1976 (2010)

275. C.F. Gu, L.S. Tóth, The origin of strain reversal texture in equal channel angular pressing, *Acta Materialia*, **59**(14), 5749-5757 (2011)

276. A. Ostapovets, P. Šedá, A. Jäger, P. Lejček, New misorientation scheme for a visco-plastic self-consistent model: Equal channel angular pressing of magnesium single crystals, *International Journal of Plasticity*, **29**(1), 1-12 (2012)

277. P. Šedá, A. Ostapovets, A. Jäger, P. Lejček, Texture evolution in oriented magnesium single crystals processed by equal channel angular pressing, *Philosophical Magazine*, **92**(10), 1223-1237 (2012)

278. A. Ostapovets, P. Molnár, A. Jäger, Visco-plastic self-consistent modelling of a grain boundary misorientation distribution after equal-channel angular pressing in an AZ31 magnesium alloy, *Journal of Materials Science*, **48**(5), 2123-2134 (2013)

279. C.F. Gu, M. Hoffman, L.S. Toth, Y.D. Zhang, Grain size dependent texture evolution in severely rolled pure copper, *Materials Characterization*, **101**, 180-188 (2015)

280. H.S. Ryoo, S.H. Yu, K.H. Oh, S.K. Hwang, Monte Carlo simulation of grain growth in ZR processed by ECAP, *Materials Science Forum*, **408-412**, 655-660 (2002)

281. S.H. Yu, H.S. Ryoo, S.K. Hwang, D.H. Shin, Monte-Carlo Modeling of Grain Growth in Zr Equal Channel Angular Pressed and Recrystallized, *Metals and Materials International*, **9**(2), 107-114 (2003)

282. S.H. Yu, D.H. Shin, S.K. Hwang, Evolution of grain boundary character distribution in eca-pressed pure titanium, *Ultrafine Grained Materials III*, 2004, pp 227-234

283. S.H. Yu, Y.B. Chun, S.K. Hwang, D.H. Shin, Texture development and Monte-Carlo simulation of microstructure evolution in pure Zr grain-refined by equal channel angular pressing, *Philosophical Magazine*, **85**(2-3 SPEC. ISS.), 345-371 (2005)

284. X.w. Nie, S. Xie, H. Xu, Y. Du, Simulation of the ultra-fine microstructure evolution during annealing of AZ31 processed by ECAP, *Physica B: Condensed Matter*, **405**(8), 1969-1972 (2010)

285. M. Esmailzadeh, M. Aghaie-Khafri, Finite element and artificial neural network analysis of ECAP, *Computational Materials Science*, **63**, 127-133 (2012)

286. F. Djavanroodi, B. Omranpour, M. Sedighi, Artificial neural network modeling of ECAP process, *Materials and Manufacturing Processes*, **28**(3), 276-281 (2013)

287. D. Salcedo, C.J. Luis, I. Puertas, J. León, R. Luri, J.P. Fuertes, FEM modelling and experimental analysis of an AA5083 turbine blade from ECAP processed material, *Materials and Manufacturing Processes*, **29**(4), 434-441 (2014)

288. D. Salcedo, C.J. Luis, J. León, I. Puertas, J.P. Fuertes, R. Luri, Simulation and analysis of isothermal forging of AA6063 obtained from material processed by equal channel angular pressing severe plastic deformation, *Proceedings of the Institution of Mechanical Engineers, Part B: Journal of Engineering Manufacture*, **229**(5), 727-743 (2015)

289. F. Fereshteh-Saniee, A. Sepahi-Boroujeni, S. Sepahi-Boroujeni, Optimized tool design for expansion equal channel angular extrusion (Exp-ECAE) process using FE-based neural network and genetic algorithm, *International Journal of Advanced Manufacturing Technology*, **86**(9-12), 3471-3482 (2016)

290. M. Mahmoodi, A. Naderi, Applicability of artificial neural network and nonlinear regression to predict mechanical properties of equal channel angular rolled Al5083 sheets, *Latin American Journal of Solids and Structures*, **13**(8), 1515-1525 (2016)

291. V.M. Segal, Equal channel angular extrusion: from macromechanics to structure formation, *Materials Science and Engineering: A*, **271**(1-2), 322-333 (1999)

292. S. Li, Effect of strain path change on the plastic responses during uniaxial loading of materials pre-deformed by equal channel angular extrusion, *Scripta Materialia*, **56**(6), 445-448 (2007)

293. A.V. Nagasekhar, Y. Tick-Hon, H.P. Seow, Deformation behavior and strain homogeneity in equal channel angular extrusion/pressing, *Journal of Materials Processing Technology*, **192-193**, 449-452 (2007)

294. P. Leo, E. Cerri, P.P. De Marco, H.J. Roven, Properties and deformation behaviour of severe plastic deformed aluminium alloys, *Journal of Materials Processing Technology*, **182**(1-3), 207-214 (2007)

295. K. Naroei, A.K. Taheri, USING OF BEZIER FORMULATION FOR CALCULATION OF STREAMLINE, STRAIN DISTRIBUTION AND EXTRUSION LOAD IN RECTANGULAR CROSS SECTION OF ECAE PROCESS, *International Journal of Computational Methods*, **10**(3), 1350005, (2013)

296. B. Aour, F. Zaïri, M. Naït-Abdelaziz, J.M. Gloaguen, O. Rahmani, J.M. Lefebvre, A computational study of die geometry and processing conditions effects on equal channel angular extrusion of a polymer, *International Journal of Mechanical Sciences*, **50**(3), 589-602 (2008)

297. J.H. Lee, I.H. Son, Y.T. Im, S.H. Chon, J.K. Park, Design guideline of multi-pass equal channel angular extrusion for uniform strain distribution, *Journal of Materials Processing Technology*, **191**(1-3), 39-43 (2007)

298. F. Zaïri, B. Aour, J.M. Gloaguen, M. Naït-Abdelaziz, J.M. Lefebvre, Numerical modelling of elastic-viscoplastic equal channel angular extrusion process of a polymer, *Computational Materials Science*, **38**(1), 202-216 (2006)

299. Y.X. Li, T.T. Zhou, Y.G. Zhang, C.Q. Chen, The shear strain measurement and finite element modeling during equal channel angular pressing of aluminum, *Materials Science Forum*, 2002, p 441-446

300. M.A. Agwa, M.N. Ali, A.E. Al-Shorbagy, Optimum processing parameters for equal channel angular pressing, *Mechanics of Materials*, **100**, 1-11 (2016)

301. R. Nemati-Chari, K. Dehghani, A. Kami, D. Banabic, Application of response surface methodology for study of effective strain in equal channel angular pressing of AA6061 alloy, *Proceedings of the Romanian Academy Series A - Mathematics Physics Technical Sciences Information Science*, **16**(2), 184-192 (2015)

302. S.C. Baik, R.J. Hellmig, Y. Estrin, H.S. Kim, Modeling of deformation behavior of copper under equal channel angular pressing, *Zeitschrift fuer Metallkunde/Materials Research and Advanced Techniques*, **94**(6), 754-760 (2003)

303. I.J. Beyerlein, R.A. Lebensohn, C.N. Tomé, Modeling texture and microstructural evolution in the equal channel angular extrusion process, *Materials Science and Engineering A*, **345**(1-2), 122-138 (2003)

304. N.A. Enikeev, H.S. Kim, I.V. Alexandrov, Kinetic dislocation model of microstructure evolution during severe plastic deformation, *Materials Science and Engineering A*, **460-461**, 619-623 (2007)

305. Y. Estrin, Modeling of Severe Plastic Deformation: Evolution of Microstructure, Texture, and Strength, *Integral Materials Modeling: Towards Physics-Based Through-Process Models*, 2007, p 275-284 Journal?

306. Y. Estrin, H.S. Kim, Modelling microstructure evolution toward ultrafine crystallinity produced by severe plastic deformation, *Journal of Materials Science*, **42**(5), 1512-1516 (2007)

307. Y. Estrin, H.S. Kim, Modelling microstructure evolution towards ultrafine crystallinity produced by severe plastic deformation, *Journal of Materials Science*, **42**(21), 9092-9096 (2007)

308. J.M. García-Infanta, S. Swaminathan, F. Carreño, O.A. Ruano, T.R. McNelley, Grain shape and microstructural evolution during equal channel angular pressing, *Scripta Materialia*, **58**(1), 17-20 (2008)

309. D. Goran, J.J. Fundenberger, E. Bouzy, W. Skrotzki, S. Suwas, T. Grosdidier, L.S. Toth, Local texture and microstructure in cube-oriented nickel single crystal deformed by equal channel angular extrusion, *Philosophical Magazine*, **91**(2), 291-309 (2011)

310. H. Hallberg, M. Wallin, M. Ristinmaa, Modeling of continuous dynamic recrystallization in commercial-purity aluminum, *Materials Science and Engineering A*, **527**(4-5), 1126-1134 (2010)

311. S. Li, A.A. Gazder, I.J. Beyerlein, C.H.J. Davies, E.V. Pereloma, Microstructure and texture evolution during equal channel angular extrusion of interstitial-free steel: Effects of die angle and processing route, *Acta Materialia*, **55**(3), 1017-1032 (2007)

312. F. Liu, H. Yuan, J. Yin, J.T. Wang, Influence of stacking fault energy and temperature on microstructures and mechanical properties of fcc pure metals processed by equal-channel angular pressing, *Materials Science and Engineering A*, (2015)

313. H. Petryk, S. Stupkiewicz, A quantitative model of grain refinement and strain hardening during severe plastic deformation, *Materials Science and Engineering A*, **444**(1-2), 214-219 (2007)

314. J.W. Signorelli, P.A. Turner, V. Sordi, M. Ferrante, E.A. Vieira, R.E. Bolmaro, Computational modeling of texture and microstructure evolution in Al alloys deformed by ECAE, *Scripta Materialia*, **55**(12), 1099-1102 (2006)

315. L.S. Tóth, Modelling of strain hardening and microstructural evolution in equal channel angular extrusion, *Computational Materials Science*, **32**(3-4), 568-576 (2005)

316. L.S. Toth, C.F. Gu, Modeling of disorientation axis distribution in severely deformed copper, *Scripta Materialia*, **69**(2), 183-186 (2013)

317. J.C. Werenskiold, H.J. Roven, Microstructure and texture evolution during ECAP of an AlMgSi alloy: Observations, mechanisms and modeling, *Materials Science and Engineering A*, **410-411**, 174-177 (2005)

318. V.S. Zhernakov, I.N. Budilov, G.I. Raab, I.V. Alexandrov, R.Z. Valiev, A numerical modelling and investigations of flow stress and grain refinement during equal-channel angular pressing, *Scripta Materialia*, **44**(8-9), 1765-1769 (2001)

319. S.R. Agnew, P. Mehrotra, T.M. Lillo, G.M. Stoica, P.K. Liaw, Texture evolution of five wrought magnesium alloys during route a equal channel angular extrusion: Experiments and simulations, *Acta Materialia*, **53**(11), 3135-3146 (2005)

320. I.V. Alexandrov, M.V. Zhilina, A.V. Scherbakov, A.I. Korshunov, P.N. Nizovtsev, A.A. Smolyakov, V.P. Solovyev, I.J. Beyerlein, Texture formation during severe plastic deformation, *Materials Science Forum*, **495-497**, 785-790 (2005)

321. R. Arruffat-Massion, L.S. Tóth, J.P. Mathieu, Modeling of deformation and texture development of copper in a 120° ECAE die, *Scripta Materialia*, **54**(9), 1667-1672 (2006)

322. S.J. Kim, M.H. Seo, S.C. Baik, Y. Estrin, H.S. Kim, Finite element analysis of equal channel angular pressing based on a dislocation density and cell size evolution model, *Journal of Metastable and Nanocrystalline Materials*, **15-16**, 231-234 (2003)

323. B. Beausir, S. Suwas, L.S. Tóth, K.W. Neale, J.J. Fundenberger, Analysis of texture evolution in magnesium during equal channel angular extrusion, *Acta Materialia*, **56**(2), 200-214 (2008)

324. I.J. Beyerlein, C.N. Tomé, Modeling transients in the mechanical response of copper due to strain path changes, *International Journal of Plasticity*, **23**(4), 640-664 (2007)

325. I.J. Beyerlein, L.S. Tóth, C.N. Tomé, S. Suwas, Role of twinning on texture evolution of silver during equal channel angular extrusion, *Philosophical Magazine*, **87**(6), 885-906 (2007)

326. J.A. del Valle, O.A. Ruano, Separate contributions of texture and grain size on the creep mechanisms in a fine-grained magnesium alloy, *Acta Materialia*, **55**(2), 455-466 (2007)

327. G.Y. Deng, C. Lu, L.H. Su, X.H. Liu, A.K. Tieu, Modeling texture evolution during ECAP of copper single crystal by crystal plasticity FEM, *Materials Science and Engineering A*, **534**, 68-74 (2012)

328. Y. Estrin, R.J. Hellwig, S.C. Baik, H.S. Kim, H.G. Brokmeier, A. Zi, Microstructure and texture development in copper and aluminum under ecap: New experimental results and modeling, *Ultrafine Grained Materials III*, 2004, pp 247-253

329. A. Gholinia, P. Bate, P.B. Prangnell, Modelling texture development during equal channel angular extrusion of aluminium, *Acta Materialia*, **50**(8), 2121-2136 (2002)

330. S. Li, I.J. Beyerlein, D.J. Alexander, S.C. Vogel, Texture evolution during multi-pass equal channel angular extrusion of copper: Neutron diffraction characterization and polycrystal modeling, *Acta Materialia*, **53**(7), 2111-2125 (2005)

331. S. Li, I.J. Beyerlein, C.T. Necker, On the development of microstructure and texture heterogeneity in ECAE via route C, *Acta Materialia*, **54**(5), 1397-1408 (2006)

332. L.S. Tóth, R.A. Massion, L. Germain, S.C. Baik, S. Suwas, Analysis of texture evolution in equal channel angular extrusion of copper using a new flow field, *Acta Materialia*, **52**(7), 1885-1898 (2004)

333. G.G. Yapici, I. Karaman, Z.P. Luo, Mechanical twinning and texture evolution in severely deformed Ti-6Al-4V at high temperatures, *Acta Materialia*, **54**(14), 3755-3771 (2006)

334. D.J. Alexander, I.J. Beyerlein, Mechanical properties of high-purity copper processed by equal channel angular extrusion, *Ultrafine Grained Materials III*, 2004, pp 517-522

335. B. Aour, F. Zaïri, R. Boulahia, M. Nait-Abdelaziz, J.M. Gloaguen, J.M. Lefebvre, Experimental and numerical study of ECAE deformation of polyolefins, *Computational Materials Science*, **45**(3), 646-652 (2009)

336. R.N. Chari, A. Kami, B.M. Dariani, Modeling and optimization of equivalent plastic strain in equal-channel angular rolling using response surface methodology, *Proceedings of the Institution of Mechanical Engineers, Part B: Journal of Engineering Manufacture*, **229**(11), 1963-1975 (2015)

337. H.S. Kim, M.H. Seo, S.I. Hong, H.R. Lee, B.S. Chun, K.H. Lee, Modelling of equal channel angular pressing for ultrafine-grained metals, *Materials Science Forum*, **386-388**, 421-426 (2002)

338. S. Poortmans, L. Duchêne, A.M. Habraken, B. Verlinden, Modelling compression tests on aluminium produced by equal channel angular extrusion, *Acta Materialia*, **57**(6), 1821-1830 (2009)

339. H.J. Sue, H. Dilan, C.K.Y. Li, Simple shear plastic deformation behavior of polycarbonate plate due to the equal channel angular extrusion process. I: Finite element methods modeling, *Polymer Engineering and Science*, **39**(12), 2505-2515 (1999)

340. L. Trebacz, H. Paul, L. Madej, M. Pietrzyk, Numerical analysis of the microstructure and mechanical properties evolution during equal channel angular pressing, *Materials Science Forum*, 2010, p 1940-1945

341. H. Mughrabi, H.W. Höppel, Cyclic deformation and fatigue properties of very fine-grained metals and alloys, *International Journal of Fatigue*, **32**(9), 1413-1427 (2010)

342. A.P. Zhilyaev, A.A. Gimazov, T.G. Langdon, Recent developments in modelling of microhardness saturation during SPD processing of metals and alloys, *Journal of Materials Science*, **48**(13), 4461-4466 (2013)

343. Y. Estrin, A. Vinogradov, Fatigue behaviour of light alloys with ultrafine grain structure produced by severe plastic deformation: An overview, *International Journal of Fatigue*, **32**(6), 898-907 (2010)

344. A.R. Eivani, A.K. Taheri, Effective strain based on shear and principal strains in equal channel angular extrusion with outer curved corner, *Computational Materials Science*, **41**(3), 409-419 (2008)

345. R.E. Goforth, K.T. Hartwig, L.R. Cornwell, Severe plastic deformation of materials by equal-channel angular extrusion (ECAE), *Investigations and Applications of Severe Plastic Deformation*, 3-12 (2000)

346. B. Avitzur, W. Pachla, UPPER BOUND APPROACH TO PLANE STRAIN PROBLEMS USING LINEAR AND ROTATIONAL VELOCITY FIELDS - PART I AND 2: BASIC CONCEPTS AND APPLICATIONS, *Journal of engineering for industry*, **108**(4), 295-316 (1986)

347. B. Avitzur, W. Pachla, The Upper Bound Approach to Plane Strain Problems Using Linear and Rotational Velocity Fields - Part II: Application, *J. Eng. Ind.*, **108**, 307-316 (1986)

348. A.R. Eivani, S. Ahmadi, E. Emadoddin, S. Valipour, A.K. Taheri, The effect of deformations passes on the extrusion pressure in axi-symmetric equal channel angular extrusion, *Computational Materials Science*, **44**(4), 1116-1125 (2009)

349. M. Reihanian, R. Ebrahimi, M.M. Moshksar, Upper-bound analysis of equal channel angular extrusion using linear and rotational velocity fields, *Materials & Design*, **30**(1), 28-34 (2009)

350. E. Hosseini, M. Kazeminezhad, The effect of ECAP die shape on nano-structure of materials, *Computational Materials Science*, **44**(3), 962-967 (2009)

351. A. Hasani, L.S. Toth, Deformation Field Analysis in Equal Channel Angular Extrusion of Metals Using Asymmetric Flow Function, *Advanced Engineering Materials*, **17**(12), 1760-1772 (2015)

352. Y. Estrin, L.S. Tóth, A. Molinari, Y. Bréchet, A dislocation-based model for all hardening stages in large strain deformation, *Acta Materialia*, **46**(15), 5509-5522 (1998)

353. E. Hosseini, M. Kazeminezhad, ETMB model investigation of flow softening during severe plastic deformation, *Computational Materials Science*, **46**(4), 902-905 (2009)

354. F. Djavanroodi, M. Ebrahimi, Effect of die parameters and material properties in ECAP with parallel channels, *Materials Science and Engineering a-Structural Materials Properties Microstructure and Processing*, **527**(29-30), 7593-7599 (2010)

355. F. Djavanroodi, M. Ebrahimi, Effect of die channel angle, friction and back pressure in the equal channel angular pressing using 3D finite element simulation, *Materials Science and Engineering a-Structural Materials Properties Microstructure and Processing*, **527**(4-5), 1230-1235 (2010)

356. B. Talebanpour, N. Pardis, M. Hariri, M.M. Moshksar, Utilization of channel angular deformation as an alternative for direct extrusion, *Materials Science and Engineering a-Structural Materials Properties Microstructure and Processing*, **527**(10-11), 2492-2497 (2010)

357. A.L. Gurson, Continuum Theory of Ductile Rupture by Void Nucleation and Growth: Part I—Yield Criteria and Flow Rules for Porous Ductile Media, *Journal of Engineering Materials and Technology*, **99**(1), 2-15 (1977)

358. R.D. Haghghi, A.J. Jahromi, B.E. Jahromi, Simulation of Aluminum Powder in Tube Compaction Using Equal Channel Angular Extrusion, *Journal of Materials Engineering and Performance*, **21**(2), 143-152 (2012)

359. M. Ebrahimi, B. Rajabifar, F. Djavanroodi, New approaches to optimize strain behavior of Al6082 during equal channel angular pressing, *Journal of Strain Analysis for Engineering Design*, **48**(6), 395-404 (2013)

360. F. Ahmadi, M. Farzin, Finite element analysis of ultrasonic-assisted equal channel angular pressing, *Proceedings of the Institution of Mechanical Engineers Part C-Journal of Mechanical Engineering Science*, **228**(11), 1859-1868 (2014)

361. F. Ahmadi, M. Farzin, Investigation of a new route for equal channel angular pressing process using three-dimensional finite element method, *Proceedings of the Institution of Mechanical Engineers Part B-Journal of Engineering Manufacture*, **228**(7), 765-774 (2014)

362. M. Ebrahimi, S. Attarilar, C. Gode, F. Djavanroodi, Damage prediction of 7025 aluminum alloy during equal-channel angular pressing, *International Journal of Minerals Metallurgy and Materials*, **21**(10), 990-998 (2014)

363. R.N. Chari, A. Kami, B.M. Dariani, Modeling and optimization of equivalent plastic strain in equal-channel angular rolling using response surface methodology, *Proceedings of the Institution of Mechanical Engineers Part B-Journal of Engineering Manufacture*, **229**(11), 1963-1975 (2015)

364. A. Vinogradov, Mechanical Properties of Ultrafine-Grained Metals: New Challenges and Perspectives, *Advanced Engineering Materials*, **17**(12), 1710-1722 (2015)

365. R. Lapovok, The positive role of back-pressure in equal channel angular extrusion, *Materials Science Forum*, 2006 37-44

366. C. Xu, M. Furukawa, Z. Horita, T.G. Langdon, The evolution of homogeneity and grain refinement during equal-channel angular pressing: A model for grain refinement in ECAP, *Materials Science and Engineering a-Structural Materials Properties Microstructure and Processing*, **398**(1-2), 66-76 (2005)

367. C. Pearson, The viscous properties of extruded eutectic alloys of lead-tin and bismuth-tin, *J. Inst. Metals*, **54**(1), 111-124 (1934)

368. T.G. Langdon, Seventy-five years of superplasticity: Historic developments and new opportunities, *Journal of Materials Science*, **44**(22), 5998-6010 (2009)

369. A.H. Chokshi, A.K. Mukherjee, T.G. Langdon, Superplasticity in advanced materials, *Materials Science and Engineering: R: Reports*, **10**(6), 237-274 (1993)

370. T.G. Langdon, The mechanical properties of superplastic materials, *Metallurgical Transactions A*, **13**(5), 689-701 (1982)

371. M. Kawasaki, T.G. Langdon, Review: achieving superplastic properties in ultrafine-grained materials at high temperatures, *Journal of Materials Science*, **51**(1), 19-32 (2016)

372. M. Ashby, Indentation creep, *Materials Science and Technology*, **8**(7), 594-601 (1992)

373. R. Mahmudi, R. Alizadeh, S. Azhari, Strain rate sensitivity of equal-channel angularly pressed Sn–5Sb alloy determined by shear punch test, *Materials Letters*, **97**, 44-46 (2013)

374. R. Alizadeh, R. Mahmudi, A.H.W. Ngan, Y. Huang, T.G. Langdon, Superplasticity of a nano-grained Mg–Gd–Y–Zr alloy processed by high-pressure torsion, *Materials Science and Engineering: A*, **651**, 786-794 (2016)

375. H. Miyamoto, Corrosion of Ultrafine Grained Materials by Severe Plastic Deformation, an Overview, *Materials Transactions*, **57**(5), 559-572 (2016)

376. C. Pan, L. Liu, Y. Li, B. Zhang, F. Wang, The Electrochemical Corrosion Behavior of Nanocrystalline 304 Stainless Steel Prepared by Magnetron Sputtering, *Journal of The Electrochemical Society*, **159**(11), C453-C460 (2012)

377. C. Blawert, D. Manova, M. Störmer, J.W. Gerlach, W. Dietzel, S. Mändl, Correlation between texture and corrosion properties of magnesium coatings produced by PVD, *Surface and Coatings Technology*, **202**(11), 2236-2240 (2008)

378. E. Mostaed, M. Hashempour, A. Fabrizi, D. Dellasega, M. Bestetti, F. Bonollo, M. Vedani, Microstructure, texture evolution, mechanical properties and corrosion behavior of ECAP processed ZK60 magnesium alloy for biodegradable applications, *Journal of the Mechanical Behavior of Biomedical Materials*, **37**, 307-322 (2014)

379. G.-L. Song, Z. Xu, Crystal orientation and electrochemical corrosion of polycrystalline Mg, *Corrosion Science*, **63**, 100-112 (2012)

380. R. Xin, B. Li, L. Li, Q. Liu, Influence of texture on corrosion rate of AZ31 Mg alloy in 3.5 wt.% NaCl, *Materials & Design*, **32**(8–9), 4548-4552 (2011)

381. H. Garbacz, M. Pisarek, K.J. Kurzydłowski, Corrosion resistance of nanostructured titanium, *Biomolecular Engineering*, **24**(5), 559-563 (2007)

## Table captions

**Table 1.** Summary of the used materials, process parameters and the goal of the ECAP process in the Iranian published works

**Table 2.** Summary of the methods, their novelty and the aim of the simulations and models proposed by Iranian researchers.

## Figure captions

**Fig. 1.** Schematic illustration of microstructural evolution of the as-cast, deformed and reheated semi-solid structure formation of ECAPed specimens: (a) as-cast, (b) 4 passes of ECAP, (c) 5 min reheated, (d) 10 min reheated and (e) 20 min reheated [13].

**Fig. 2.** Schematic illustration of particle consolidation in conventional sintering (left column) and SPD consolidation (right column) [136].

**Fig. 3.** Specimen configurations to prevent surface cracking before and after ECAP of CIP Al 2024 alloy powder: (a) the cross-section of the CIP specimen with a 2024 Al cap, (b) the CIP specimen before pressing, and (c) the consolidated alloy after a single pass of ECAP at 300°C [138].

**Fig. 4.** Schematic view of the combined methods based on ECAP to consolidate powders: (a) ECAP-FE [123]; (b) T-ECAP [184]; (c) FE-ECAP [9].

**Fig. 5.** Effective strain variation across the width of the cross-section from top to bottom in various deformation processes, ECAP-FE, FE-ECAP, FE and ECAP [187].

**Fig. 6.** Fraction of publications that are focused on the modeling and simulation with respect to the total number of publication on ECAP as well as the contribution of various methods in the modeling and simulation

**Fig. 7.** TEM image of the microstructure in the central and periphery part of the pure aluminum sample after ECAP through one pass at room temperature [366].

**Fig. 8.** (a) EBSD orientation color maps and (b) the corresponding boundary maps taken from the center and periphery of transverse direction (TD) section of pure Al subjected to eight passes of ECAP, (c) mean boundary spacing and (d) fraction of high angle grain boundaries and the mean misorientation angle through the TD section of the same sample (all images extracted from [11]).

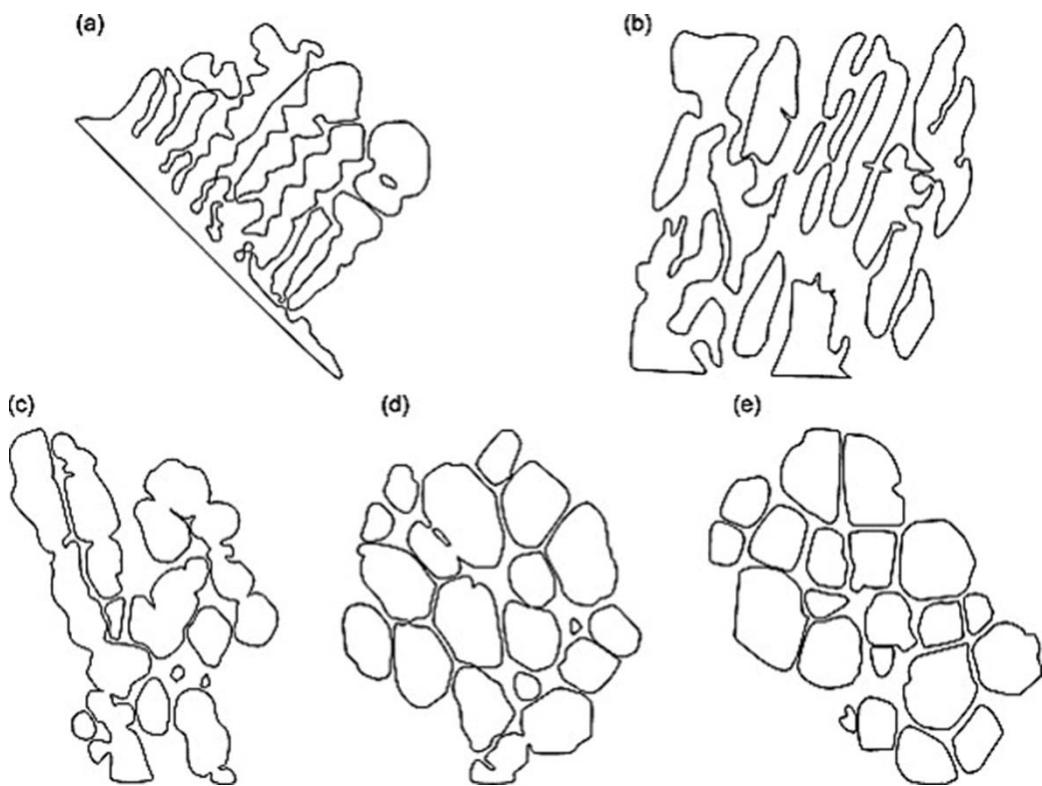


Fig. 1. Schematic illustration of microstructural evolution of the as-cast, deformed and reheated semi-solid structure formation of ECAPed specimens: (a) as-cast, (b) 4 passes of ECAP, (c) 5 min reheated, (d) 10 min reheated and (e) 20 min reheated [13].

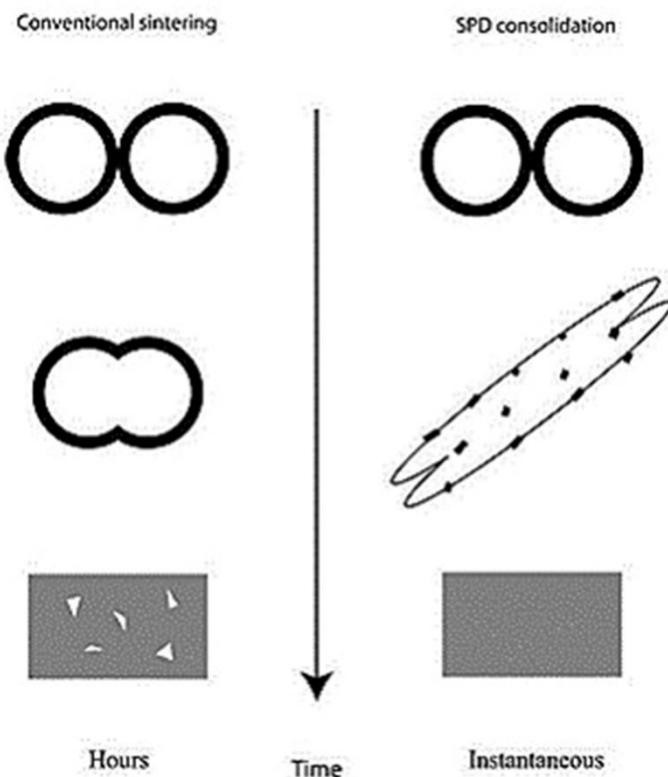


Fig. 2. Schematic illustration of particle consolidation in conventional sintering (left column) and SPD consolidation (right column) [136].

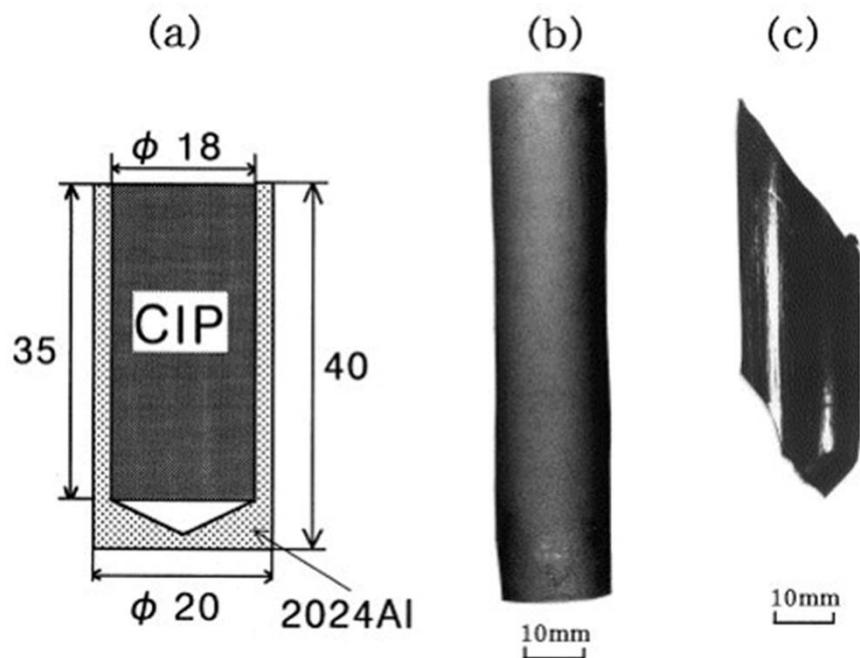


Fig. 3. Specimen configurations to prevent surface cracking before and after ECAP of CIP Al 2024 alloy powder: (a) the cross-section of the CIP specimen with a 2024 Al cap, (b) the CIP specimen before pressing, and (c) the consolidated alloy after a single pass of ECAP at 300°C [138].

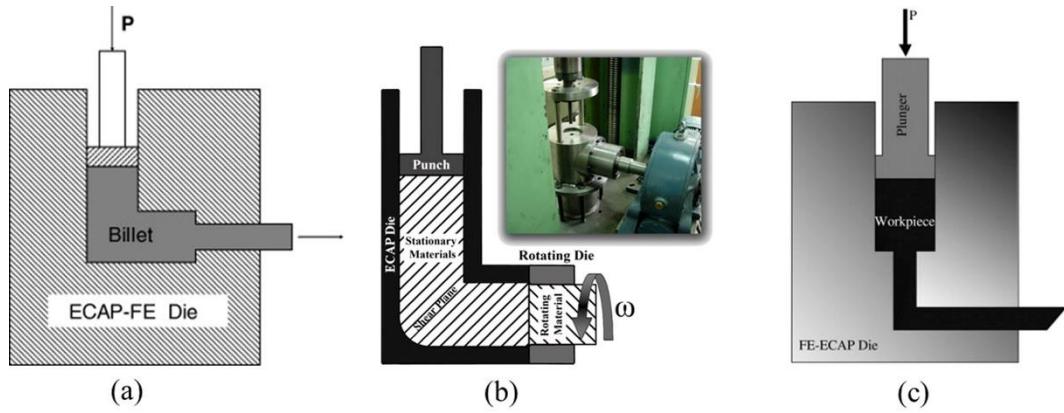


Fig. 4. Schematic view of the combined methods based on ECAP to consolidate powders: (a) ECAP-FE [123]; (b) T-ECAP [184]; (c) FE-ECAP [9].

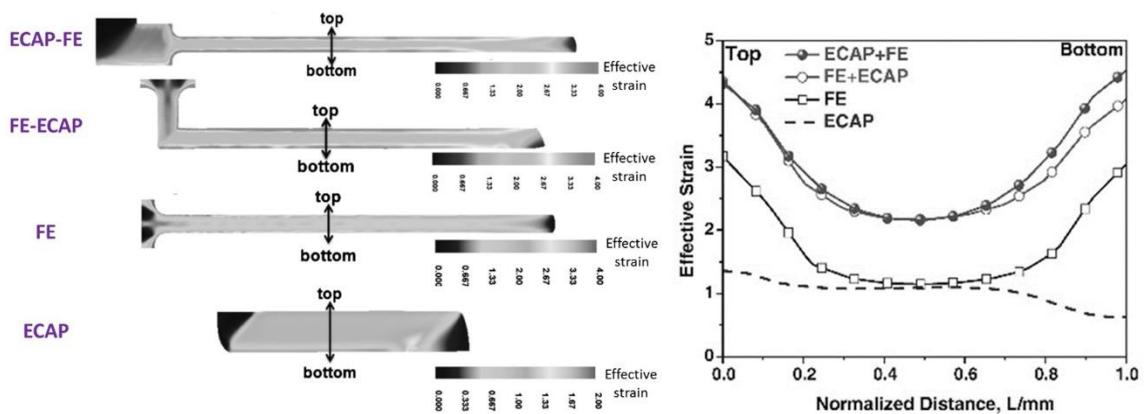


Fig. 5. Effective strain variation across the width of the cross-section from top to bottom in various deformation processes, ECAP-FE, FE-ECAP, FE and ECAP [187].

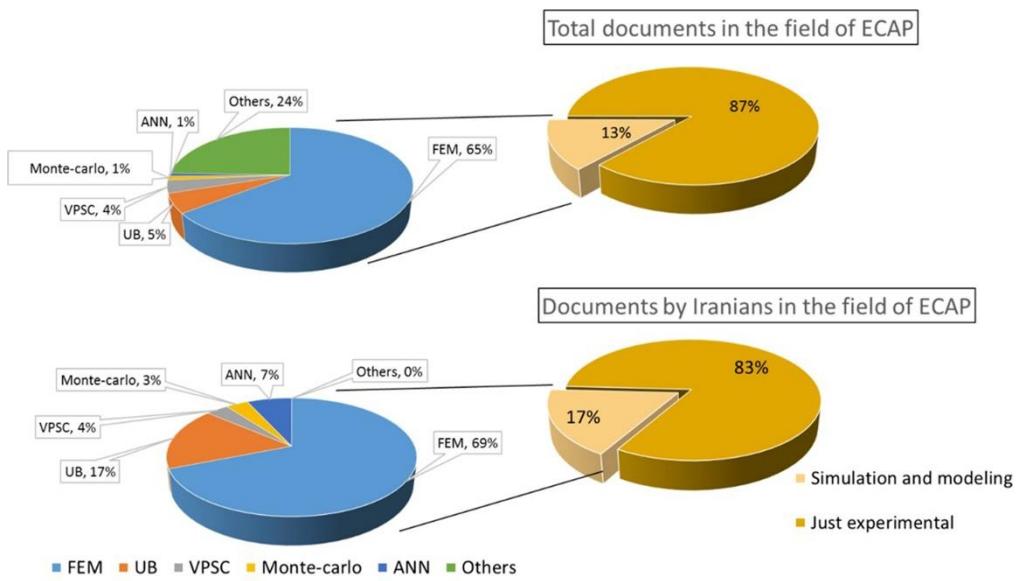


Fig. 6. Fraction of publications that are focused on the modeling and simulation with respect to the total number of publication on ECAP as well as the contribution of various methods in the modeling and simulation

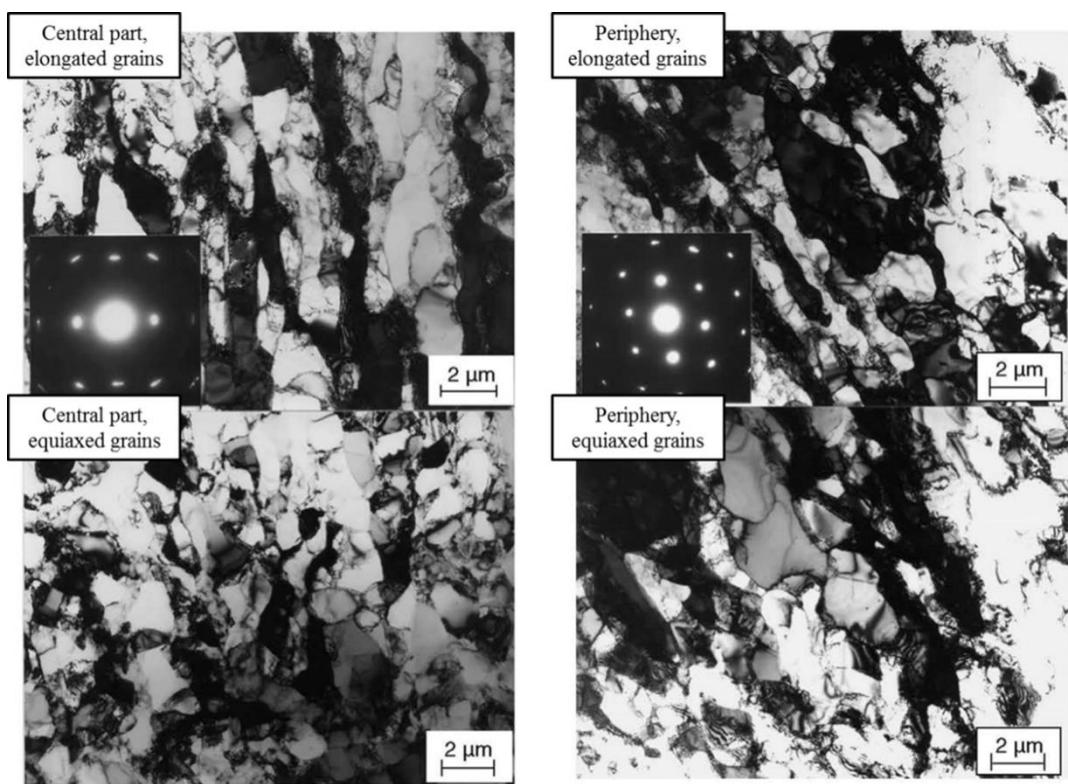


Fig. 7. TEM image of the microstructure in the central and periphery part of the pure aluminum sample after ECAP through one pass at room temperature [366].

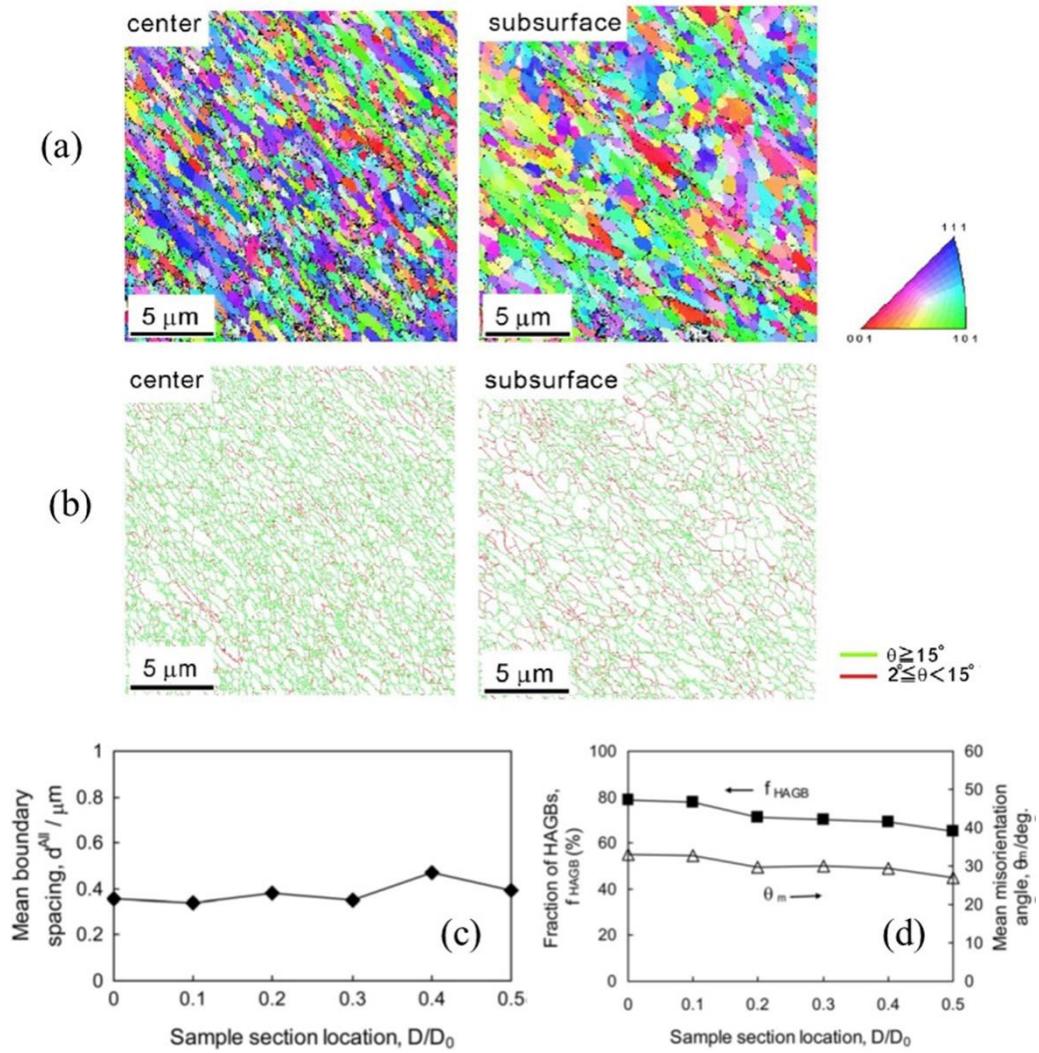


Fig. 8. (a) EBSD orientation color maps and (b) the corresponding boundary maps taken from the center and periphery of transverse direction (TD) section of pure Al subjected to eight passes of ECAP, (c) mean boundary spacing and (d) fraction of high angle grain boundaries and the mean misorientation angle through the TD section of the same sample (all images extracted from [11]).

**Table. 1.** Summary of the used materials, process parameters and the goal of the ECAP process in the Iranian published works

Material	Aim	Die parameters	No. of passes	Route	Temp.	Ref.
<b>Aluminum and its alloys</b>						
Commercial purity aluminum	Grain refinement	$\Phi = 90^\circ$ $\Psi = 0^\circ$	8	B <sub>C</sub>	RT	[11,12]
Commercial purity aluminum	Grain refinement	$\Phi = 90^\circ$ $\Psi = 20^\circ$	8	B <sub>C</sub>	RT	[35]
Commercial purity aluminum	Grain refinement	$\Phi = 90^\circ$ $\Psi = 20^\circ$	8	B <sub>C</sub>	RT	[36]
Commercial purity aluminum	Texture investigation	$\Phi = 90^\circ$ $\Psi = 20^\circ$	2	A, B <sub>A</sub> , B <sub>C</sub> , C	RT	[22,23,37]
Commercial purity aluminum	Fatigue design	$\Phi = 90^\circ$ $\Psi = 15^\circ$	8	B <sub>C</sub>	RT	[38]
Commercial purity aluminum	Enhancement of strain distribution uniformity	$\Phi = 90^\circ$ $\Psi = 15^\circ$	8	A	RT	[39]
Commercial purity aluminum	effect of ultrasonic vibration during ECAP	$\Phi = 90^\circ$ $\Psi = 15^\circ$	1	-	RT	[40]
Al (A356)	Post semi-solid processing	$\Phi = 90^\circ$ $\Psi = 20^\circ$	4-1	B <sub>C</sub>	NR-RT	[13,16,18,19] -[41]
Al (A356)	Effect of heat-treatments	$\Phi = 90^\circ$ $\Psi = 20^\circ$	1	-	RT, HT	[42]
Al (A356)	Effect of reheating and Partial Re-melting	$\Phi = 90^\circ$ $\Psi = 20^\circ$	8	A	RT	[43]
2014 Al alloy	Predicting the critical pre-aging time	$\Phi = 90^\circ$ $\Psi = 20^\circ$	4	B <sub>C</sub>	RT	[44]
2024 Al alloy	Effect of post aging	$\Phi = 90^\circ$ $\Psi = 22.5^\circ$	2	B <sub>C</sub>	RT	[45]
6061 Al alloy	Fatigue design	$\Phi = 90^\circ$ , $\Psi = 15^\circ$	4	B <sub>C</sub>	RT	[38]
6061 Al alloy	Grain refinement-Effect of dynamic ageing on the mechanical properties	$\Phi = 90^\circ$ $\Psi = 10^\circ$	4	B <sub>C</sub>	100°C, 50°C, 200°C	-[47][46]
6061 Al alloy	Influence of Friction	$\Phi = 90^\circ$	1	-	RT	[48]

							$\Psi = 20^\circ$
6061 Al alloy	Enhancement of corrosion resistance-Tensile properties and impact toughness- Improving homogeneity	$\Phi = 90^\circ$ $\Psi = 20^\circ$	4-4-2	C	RT	-[50]-[51][49]	
6061 Al alloy	Effect of post cold rolling on hot deformation-Modeling the Hot Ductility	$\Phi = 100^\circ$	2	C <sub>x</sub>	RT	-[53][52]	
6061 Al alloy	Effect of aging (processing Temp.) on homogeneity	$\Phi = 90^\circ$ $\Psi = 10^\circ$	4	B <sub>C</sub>	100°C, 50°C, 200°C	[54]	
6061 Al alloy	Effect of post bake hardening	$\Phi = 90^\circ$ $\Psi = 0^\circ$	8	NR	NR	[55]	
6061 Al alloy	Investigation of machinability	$\Phi = 120^\circ$ $\Psi = 0^\circ$	10	A,B <sub>C</sub>	RT	[56]	
6063 Al alloy	Effect of precipitation hardening	$\Phi = 90^\circ$ $\Psi = 20^\circ$	4	B <sub>C</sub>	RT	[57]	
6063 Al alloy	Fatigue behavior	$\Phi = 90^\circ$	6	A	200°C	[58]	
6082 Al alloy	Strengthening study and aging treatment	$\Phi = 120^\circ$ $\Psi = 0^\circ$	1	-	RT	[59]	
6082 Al alloy	Effect of pre, during and post aging	$\Phi = 90^\circ$ $\Psi = 0^\circ$	1	-	RT,HT	[60]	
6082 Al alloy	Effects of ECAP+ Shot Peening process (SP) on the fatigue properties	$\Phi = 90^\circ$ $\Psi = 20^\circ$	4	B <sub>C</sub>	NR	[61]	
7075 Al alloy	Predicting the critical pre-aging time- Texture investigation	$\Phi = 90^\circ$ $\Psi = 20^\circ$	4	B <sub>C</sub> - A,B <sub>C</sub>	RT	- [62][44]	
7075 Al alloy	Effect of pre, during and post aging	$\Phi = 90^\circ$ $\Psi = 20^\circ$	4	B <sub>C</sub>	Different Temperat ures	[63]	
7075 Al alloy	Effect of ECAP on aging- texture evolution	$\Phi = 90^\circ$ $\Psi = 20^\circ$	3-4	B <sub>C</sub>	RT, 120°C- RT	-[65][64]	
8006 Al Alloy	Effect of semisolid post heat treatment	$\Phi = 90^\circ$	1	-	NR	[66]	
Al-1.4Si-0.9Cu-0.9Mg-	Effect of dynamic strain aging	$\Phi = 90^\circ$	1	-	RT,	[67]	

0.6Fe-0.1Mn	on hardness and electrical resistivity	$\Psi = 20^\circ$		50°C, 100°C, 150°C, 200°C		
Al-1.8Fe-0.95Si	Post semisolid processing	$\Phi = 90^\circ$ $\Psi = 20^\circ$	1	-	RT	[68]
Al-6Mg	Grain refinement	$\Phi = 120^\circ$	4	A, B <sub>A</sub> , B <sub>C</sub> , C	RT	[69]
Al-1Mg	Tailoring grain size and work hardening	-	7	B <sub>C</sub>	-	[70]

### Copper and its alloys

commercially pure copper	Fatigue design	$\Phi = 90^\circ$ $\Psi = 15^\circ$	4	B <sub>C</sub>	RT	[38]
commercially pure copper	Effect of post-rolling-A comparison with TE	$\Phi = 110^\circ$ $\Psi = 20^\circ$	4	B <sub>C</sub>	RT	-[74][71-73]
commercially pure copper	Effect of various strain rates- Fatigue behavior	$\Phi = 90^\circ$	8	A	NR	-[76][75]
OFHC copper	Texture investigation	$\Phi = 120^\circ$ $\Psi = 20^\circ$	10	A, B <sub>30</sub> - B <sub>60</sub> , B <sub>C</sub>	RT	-[78][77]
OFHC copper	Grain refinement	$\Phi = 120^\circ$	20	A,B <sub>30</sub> ,B <sub>45</sub> ,B <sub>60</sub> ,B <sub>C</sub>	RT	[79]
Various brass and bronze alloys	Investigation of shear localization and segmentation	$\Phi = 90^\circ$ $\Psi = 20^\circ$	1	-	RT, 350°C	[80]

### Steels

18Ni maraging steel	Grain refinement	$\Phi = 90^\circ$ $\Psi = 0^\circ$	4	B <sub>C</sub>	RT	[14,15,17,81]
Fe-0.22C-2.0Si-3.0Mn	Martensitic transformation	$\Phi = 90^\circ$ $\Psi = 0^\circ$	2	B <sub>C</sub>	RT	[82,83]
Fe-17.6Ni-8.3Co-4.5Mo-0.7 Ti	Grain refinement	$\Phi = 90^\circ$ $\Psi = 0^\circ$	4	B <sub>C</sub>	RT	[84]
Fe-10Ni-7Mn	Cold roll Vs. ECAP	$\Phi = 90^\circ$ $\Psi = 0^\circ$	4	B <sub>C</sub>	RT	[85]
Fe-22Mn-3Si-Al	Feasibility of RT ECAP	$\Phi = 120^\circ$	1	-	RT	[86]
austenitic TWIP steel	processing of TWIP steel	$\Psi = 45^\circ$				

commercially pure Fe	Compare ECAP with cold rolling and drawing by AFM	NR	4	A	RT	[87]
	investigations					
Commercial 304 SS	Grain refinement	$\Phi = 90^\circ$ $\Psi = 20^\circ$	3	B <sub>C</sub>	RT	[88]

AISI 316L austenitic stainless steel	Corrosion and biological behavior	$\Phi = 105^\circ$ $\Psi = 20^\circ$	8	B <sub>C</sub>	350°C	[89,90]
--------------------------------------	-----------------------------------	---	---	----------------	-------	---------

### Titanium and its alloys

commercially pure titanium	Corrosion behavior	$\Phi = 90^\circ$ $\Psi = 20^\circ$	8	B <sub>C</sub>	450°C	[91]
Commercial purity titanium	Grain refinement- Recrystallization kinetics- Effect of post rolling on grain refinement- Electrochemical and cellular behavior	$\Phi = 105^\circ$ $\Psi = 20^\circ$	10	B <sub>C</sub>	250°C	-[93]-[92] [94]-[95,96]
Ti-6Al-4 V	Effect of ultrasonic vibrations on the ECAP process	$\Phi = 120^\circ$ $\Psi = 20^\circ$	4	B <sub>C</sub>	RT	[97]

### Magnesium and its alloys

AZ31 Mg alloy	Effects of rare earth elements and Ca additions	$\Phi = 90^\circ$ $\Psi = 20^\circ$	4	B <sub>C</sub>	200°C	[98,99]
AZ31 Mg alloy	Grain refinement	$\Phi = 90^\circ$ $\Psi = 20^\circ$	4	B <sub>C</sub>	200°C	[100]
AZ31 Mg alloy	Grain refinement	$\Phi = 90^\circ$ $\Psi = 20^\circ$	4	B <sub>C</sub>	230°C	[101]
AZ31 Mg alloy	Correlation between shear punch and tensile measurements	$\Phi = 90^\circ$ $\Psi = 20^\circ$	4	B <sub>C</sub>	230°C	[102]
AZ31 Mg alloy+Al-3Ti-0.15C master alloy as grain refiner	The grain refinement efficiency of Al-3Ti-0.15C master alloy	$\Phi = 90^\circ$ $\Psi = 20^\circ$	4	B <sub>C</sub>	230°C	[103]
AZ80 Mg alloy	Grain refinement	$\Phi = 90^\circ$ $\Psi = 20^\circ$	6	B <sub>C</sub>	220°C	[104]
AM60 Mg alloy	Fatigue behavior-Grain refinement	$\Phi = 90^\circ$ $\Psi = 20^\circ$	6	B <sub>C</sub>	220°C	-[106][105]
AM30 Mg alloy	Grain refinement	$\Phi = 90^\circ$ $\Psi = 20^\circ$	4	B <sub>C</sub>	275°C	[107]
Mg-12Li-1Zn alloy	Superplasticity	$\Phi = 90^\circ$	2	B <sub>C</sub>	200°C	[108]

GZ31 magnesium alloy	Superplasticity	$\Psi = 20^\circ$					
		$\Phi = 90^\circ$	2	$B_C$	280°C	[109]	
		$\Psi = 20^\circ$					
<b>Metal Matrix Composites</b>							
AZ31 magnesium alloy+ Al2O3 nano-particles	Grain refinement	$\Phi = 90^\circ$ $\Psi = 20^\circ$	4	$B_C$	230°C	[101]	
Cu-1.1 wt-%Al2O3 +Al2O3 particles	Softening behavior-Effect of strain path	$\Phi = 120^\circ$ $\Psi = 60^\circ$	1-2	-A,B,C	RT	-[111][110]	
Al+ $\alpha$ -Al2O3 nanoparticles	Fabrication (consolidation)	$\Phi = 90^\circ$ $\Psi = 20^\circ$	4	$B_C$	200°C	[112-114]	
Al-4.5%Mg +10Vol%SiC <sub>p</sub>	High strain rate superplasticity	$\Phi = 90^\circ$ $\Psi = 20^\circ$	8	$B_C$	RT	[115]	
AA6061- 5% SiC <sub>p</sub>	Effect of Aging	$\Phi = 120^\circ$ $\Psi = 60^\circ$	2	A	RT	[116]	
PureAl+ nickel based(90%Ni- 10%Cr)wires	Flow behavior	$\Phi = 90^\circ$ $\Psi = 20^\circ$	2	A	RT	[117]	
<b>Bimetals</b>							
Al-Cu bimetal	Fabrication	$\Phi = 90^\circ$ $\Psi = 45^\circ$	2	A, C	350°C	[3]	
AA1100- commercially pure copper bimetal	Diffusion bonding (fabrication)	$\Phi = 120^\circ$ $\Psi = 0^\circ$	1	-	RT+HT	[118]	
Al-Cu bimetal	Fabrication	Various $\Phi$ s and $\Psi$ s	1	-	RT+HT	[119]	
Al-Cu bimetal	Cold-Welding and Diffusion-Bonding	$\Phi = 120^\circ$ $\Psi = 0^\circ$	1	-	RT+HT	[120]	
<b>Others</b>							
Sn-lwt.% Bi alloy	Creep and superplasticity	$\Phi = 90^\circ$ $\Psi = 20^\circ$	4	$B_C$	RT	[21]	
Sn- 5 wt.% Sb	Superplasticity	$\Phi = 90^\circ$ $\Psi = 20^\circ$	4	$B_C$	RT and HT	[121,122]	
Commercially pure aluminum powder	Fabrication (consolidation)	$\Phi = 90^\circ$	1	-	200°C	[9,123]	
NiTi shape memory alloys	Feasibility of RT ECAP processing of NiTi shape	$\Phi = 90^\circ$ $\Psi = 20^\circ$	2-1-1	C	RT	- [124-127] [128]-[129]	

---

memory alloys-study  
martensitic stabilization and  
recrystallization kinetics-Effect  
of post-deformation annealing

---

RT: room temperature, HT: high temperature, NR: not reported

**Table 2.**Summary of the methods, their novelty and the aim of the simulations and models proposed by Iranian researchers.

Method	Novelty		Aim	Confirmation	Ref.
multi-stage ECAE dies	Simplification		Strain estimation	Previous models	[4,344]
Continuum mechanics	Introduce a new equation base on the logarithmic strain	Effect of die geometry on strain homogeneity and mean effective strain		Previous models	[20]
Upper bound analysis	Consideration of all the process parameters simultaneously	Effects of die geometry and friction coefficient on the total strain and extrusion pressure	Experiments and a previous model		[238]
Upper bound analysis	Consideration the effect of dead metal zone formation	Effect of dead metal zone formation on strain and extrusion force	Experiments and a previous model		[6]
Upper bound analysis	Using rotational and linear velocity fields by the approach of Avitzur and Pachla [346,347]	Effect of constant friction factor and inner corner radius on the development and shape of PDZ was investigated.	Experimental results		[349]
Upper bound analysis	Analyze the circular cross-sections	Prediction of the size of the plastic deformation zone and the relative extrusion pressure	Experimental results		[10]
Upper bound analysis	A solution for circular cross-sections (axi-symmetric channels)	Effect of deformations passes on the extrusion pressure	Experimental results		[348]
Upper bound analysis	Using a Bezier-shaped curve to define a general streamline	To introduce a more general and much improved formulation with respect to previous work	Previous experiments and models		[245,295]
Upper bound analysis	Theoretically consider the effects of temperature and strain rate on plastic flow behavior	Investigation of the plastic deformation and dynamic strain ageing behavior of Al-6082 alloy during the ECAP	Experimental results		[250]

A flow line model	consider the outer curve of ECAP die wall	Predict the dislocation structure evolution and nano-structure	Previous experimental results	[350]
A flow line model	Propose a new flow line function	Determine the velocity field, the strain rate field, and, in general, the shape of the plastic deformation zone and also to simulate textures	Experimental results	[351]
A kinetic dislocation model + Monte Carlo algorithm	Combination of a flow filed model, kinetic dislocation model, and Monte Carlo algorithm	Prediction of the recrystallized microstructure	Experimental results	[8]
A Monte Carlo model	Modification by using Turnbull–Fisher nucleation rate	To predict the microstructure evolution during annealing	Previous experiments	[7]
ETMB model [352]	Introduce more solidarity in the model	Investigation of flow softening of FCC materials during SPD	-	[353]
Simulations by VPSC model	-	Multi pass simulation of texture	Experimental results	[22]
FEM simulation	-	Influences of die parameters (and material properties on deformation by equal channel angular pressing with parallel channels (ECAP-PC)	Experimental results	[354]
FEM simulation	-	Investigation of deformation behavior of pure Al	Experimental results	[355]
FEM simulation	Propose channel angular deformation (CAD) as a substitute for the traditional direct extrusion	Test different CAD profiles to find the especial geometries of CAD which could be used as an alternative for direct extrusion effectively	-	[356]
FEM simulation	Design ECAP die based on the optimum strain behavior	Selection of ECAP parameters based on strain distribution uniformity	Experimental results	[39]

FEM simulation	using Gurson model [357]	Modeling of densification of aluminum powder in tube through multipass ECAP at room temperature	Experimental results	[358]
FEM simulation	A new specimen and punch modification has been proposed to reduce the head and tail zone effects	Fabricate materials with least wastage, higher ES magnitude and better strain dispersal homogeneity	Experimental results	[359]
	of ECAPed billet			
FEM simulation	superimposing ultrasonic vibration during ECAP	Propose a more realistic approach to simulate ultrasonic-assisted metal forming to investigate the effect of ultrasonic vibrations on the forming conditions in ECAP p	Experimental results	[360,361]
FEM simulation		- Damage prediction of AA7025 alloy during ECAP	Experimental results	[362]
FEM simulation + RSM + ANOVA	The first study on optimization of ECA rolling parameters	Obtain the optimum values of the ECA rolling parameters	Experimental results	[363]
FEM simulation and ANN Modeling		- Study the deformation behavior of AA2024 alloy	Experimental results	[285,286]

---

VPSC: Visco plastic self-consistent; ETMB: (Estrin–Tóth–Molinary–Bréchet); FEM: finite element method; ANN: artificial neural network; RSM: response surface methodology; ANOVA: analysis of variance;