

Residual Capacity of Corroded Reinforced Concrete Bridge Components:

A State-of-the-Art Review

Mohammad M Kashani¹, Jake Maddocks², Ebrahim Afsar Dizaj³

Abstract

The current paper provides a comprehensive review of experimental studies on corrosion damaged reinforced concrete (RC) components, and the ability of current state-of-the-art numerical models to predict the residual capacity of these corroded RC components. The experimental studies on corroded RC components are classified into five different categories including: (i) beams in flexure, (ii) beams in shear, (iii) columns under pure axial compression, (iv) circular columns in flexure, and (v) rectangular columns in flexure. For each group, a summary of all the previous research are provided. Through the regression analyses, the experimental results of each abovementioned groups are used to examine the adverse effect of corrosion on ductility and, flexural, shear, and axial capacity loss of the corroded RC components. Finally, the observed results of the previous experimental studies are compared with the predicted values using the state-of-the-art numerical models currently available in the literature. The summarised experimental results show that corrosion has much more adverse impact on ductility of the RC columns than strength. However, the effect of corrosion on ductility and strength reduction of RC beams is the same. Moreover, results of cross-sectional moment-curvature analyses using the state-of-the-art corrosion damage models show a good correlation between the predicted residual flexural capacity and observed experimental results. Finally, the existing shortcomings in the literature and open issues to be addressed in the future research are discussed, and some recommendations are provided.

Keywords: Corrosion; residual capacity; ductility loss; RC component; numerical modelling

¹ Associate Professor, Faculty of Engineering and Physical Sciences, University of Southampton, Southampton, SO17 1BJ, United Kingdom (corresponding author), Email: mehdi.kashani@soton.ac.uk

² MEng Student, Faculty of Engineering and the Environment, University of Southampton

³ PhD in Structural Engineering, University of Guilan, Email: ebrahim_afsar@live.com

22 **Introduction**

23 Bridges are recognised as the most important elements of any transport infrastructure network, which result in a
24 severe corruption in functionality of the entire network if they are disabled. There is an enormous amount of
25 ageing major bridges that are in service in earthquake prone regions (ASCE, 2013; Ghosh and Padgett, 2010).
26 To advance a reliable solution, the safety, functionality and the service life of bridges must be estimated using a
27 systematic mathematical approach.

28 Ageing reinforced concrete (RC) bridges are susceptible to various environmental stressors including chloride-
29 induced corrosion and carbonation. Chloride-induced corrosion of reinforcing steel is a major environmental
30 stressor affecting the performance of ageing RC bridges and structures in the UK, USA and other developed
31 countries (Rao et al., 2016a; Chiu et al., 2015). Severe corrosion can result in catastrophic failure (Broomfield,
32 2007). In the UK, corrosion damage to highway bridges is estimated to cost about £1 billion/year in England and
33 Wales alone (Wallbank, 1989) (this is approximately 10% of the total bridges in the UK). In the US, the estimated
34 cost to repair or replace corroded RC bridges is about \$150 billion (Transportation Research Board, 1991).

35 Over the past few decades several researchers have put a significant effort in studying the impact of corrosion on
36 the nonlinear behaviour of corroded structural components (beams, slabs and columns) using accelerated
37 corrosion procedure in the laboratory (Cairns and Zhao 1993; Rodriguez et al. 1996; Rodriguez et al. 1997; Razak
38 and Choi 2001; Cairns et al. 2005; Rodriguez et al. 2005; Du et al 2007; Azad et al. 2007). The principal effects
39 of corrosion on structural elements are: (i) loss of reinforcement cross section, (ii) changing the mechanical
40 properties and ductility of reinforcement, (iii) reduced compressive strength of the cracked cover concrete, and
41 (iv) reduction of bond strength at the reinforcement and concrete interface (Vu et al., 2016). The progressive
42 expansion of rust at the reinforcement and concrete interface induces splitting stresses in concrete and eventually
43 leads to cover cracking and spalling (Vidal et al., 2004). This will weaken the bond strength between steel and
44 concrete, which will influence the bending stiffness and the shear capacity of the structural element (Rodriguez
45 et al. 1996; Chung et al. 2008a; Yoon et al. 2000; Malumbela et al. 2009). Moreover, pitting corrosion causes
46 localised cross section loss, which results in degradation of ductility and strength of the corroded reinforcing
47 bars. Therefore, corrosion induced mechanical damage at material level (concrete, steel and bond strength) will
48 lead to diminished structural performance of RC elements and will subsequently affect the global response of the
49 structural system.

50 In recent years researchers have conducted several experimental studies exploring the impact of pitting corrosion
51 on residual capacity, ductility loss, inelastic buckling, and low-cycle fatigue behaviour of corroded reinforcing
52 bars (Palsson and Mirza 2002; Cairns et al. 2005; Almusallam 2001; Du et al. 2005a, b; Apostolopoulos et al.
53 2006; Alexopoulos et al. 2007; Apostolopoulos and Michalopoulos 2007; Papadopoulos et al. 2007;
54 Apostolopoulos and Papadopoulos 2007; Apostolopoulos and Pasialis 2008; Apostolopoulos and Koutsoukos
55 2008; Apostolopoulos and Papadakis 2008; Apostolopoulos 2009; Lee and Cho 2009; Kashani et al., 2013a,
56 2013b, 2015a, Fernandez et al., 2015).

57 A significant number of studies have been dedicated to investigating the nonlinear behaviour of corrosion
58 damaged RC beams and slabs under vertical loading (Rodriguez et al. 1997; Cairns and Zhao 1993; Rodriguez
59 et al. 1996; Razak and Choi 2001; Cairns et al. 2005; Rodriguez et al. 2005; Du et al. 2007; Azad et al. 2007). In
60 recent years, several researchers have also employed nonlinear finite element analysis to study the adverse
61 influence of corrosion on the structural response of RC beams (Coronelli and Gambarova 2004; El Maaddawy et
62 al. 2005a; Kallias 2011). Most of the early numerical and experimental studies have been focused on the structural
63 response of RC beams and slabs under monotonic loading. However, there is a large number of RC bridges and
64 structures that are located in environmentally aggressive and high seismicity regions. Therefore, recently,
65 researchers have started to investigate the influence of corrosion on the nonlinear behaviour of RC beams,
66 columns, and frames under cyclic loading (Pantazopoulou et al. 2001; Aquino 2002; Tastani et al. 2004; Bousias
67 et al. 2004; Belarbi and Bae 2007; Ou et al., 2011; Meda et al., 2014; Li et al., 2015; Liu et al., 2017).

68 More recently, several researchers have studied the influence of corrosion on seismic performance, fragility and
69 the life-cycle cost analysis of deteriorating structures and bridges (Stewart , 2004; Choe et al. 2008; Berto et al.
70 2009; Ghosh and Padgett 2010; Choe et al. 2009; Akiyama et al. 2011; Simon et al. 2010; Akiyama and Frangopol
71 2013; Alipour et al. 2011; Biondini et al. 2014 ,Ou et al. 2013, Guo et al., 2015a; Ni Choine et al., 2016; Rao et
72 al., 2016b; Ghosh et al., 2016; Cui et al., 2018). The results of these studies showed that corrosion significantly
73 affects the seismic vulnerability of RC structures and bridges. In these studies, fibre-based nonlinear finite
74 element programmes (e.g. OpenSees (McKenna, 2011)), have been used for the analysis.

75 According to the aforementioned studies, it is evident that a significant effort has been put to investigate and
76 quantify the impact of material deterioration on structural and seismic performance of corroded RC components
77 and bridges. Despite all these previous studies in investigating the impact of corrosion of reinforcement on

78 structural performance of RC structures and bridges, it is still an open issue, and requires a significant research
79 in the future. This is due to the complexity in quantification of corrosion of reinforcing bars inside concrete, and
80 random nature of corrosion, which result in significant uncertainties in numerical models and performance
81 prediction.

82 Currently, there is no concise paper available in the literature to review the state-of-the-art research and highlights
83 the needs for future research. Accordingly, the aim of this paper is to provide a critical review of the previous
84 experimental testing and the available state-of-the-art numerical models for structural performance evaluation of
85 corroded RC components. To this end, the results of the previous experimental studies are used to investigate the
86 effects of corrosion on strength and ductility loss, and failure mechanisms of corroded RC components.
87 Furthermore, an exemplary comparison has been made between the observed experimental results and the current
88 state-of-the-art numerical models for predicting the residual flexural strength of corroded RC components.
89 Finally, the current shortcomings in the literature are identified, and some recommendations to address the open
90 issues in future research are provided. It should be noted that the details of all the experimental data and computed
91 values are provided in two downloadable Excel files (Comp Vs Exp. xlsx and Exp data.xlsx) as the online
92 supplementary.

93 **Experimental Investigation of Structural Performance of Corroded RC Beams**

94 *Adverse effect of corrosion on structural performance of RC beams in flexure*

95 A summary of all the experimental studies on corroded Rectangular RC Beams in Flexure (RRBF) and their
96 outcomes is provided in Table 1. In this table, ψ_l is the average percentage of mass loss of longitudinal
97 reinforcements. Several researchers (Tables 1) conducted experimental testing to study the effect of corrosion on
98 nonlinear flexural behaviour of RC beams. All these studies agree that corrosion of longitudinal reinforcements
99 has a significant influence on the failure mode of RC beams. In this section, the key common findings of these
100 experimental studies are provided.

101 Using an accelerated corrosion procedure, Mangat and Elgarf (1999) carried out a set of experimental testing on
102 corrosion damaged RC beams subjected to pure flexural loading. They investigated the influence of corrosion
103 rate on the strength and ductility of the tested specimens, and found that 10% of mass loss of longitudinal
104 reinforcement with corrosion rate of 2 mA/cm² results in about 60% reduction in flexural capacity and 77%
105 reduction in ductility. However, another corroded beam with 10% of mass loss of longitudinal reinforcement

106 with rate of 4 mA/cm² resulted in about 70% reduction in flexural capacity and 77% reduction in ductility. This
107 is because higher corrosion rate has more significant impact on degradation of concrete, and subsequently results
108 in a more reduction in strength.

109 Castel et al. (2000) conducted experimental testing on uncorroded and 14 years old corroded RC beams under
110 flexural loading. They found that about 20% corrosion results in about 35% reduction in flexural stiffness and
111 about 70% reduction in ductility of corroded RC beams. They found that the residual flexural strength of corroded
112 RC beams is primarily a function of mass loss of tensile reinforcement, and is not significantly affected by loss
113 of bond strength.

114 El Maaddawy et al. (2005b) conducted a set of experimental testing on pristine and corroded RC beams. The
115 tested specimens were corroded using accelerated corrosion procedure and a sustained load to represent the
116 service load on the structure. The sustained load on the beam resulted in flexural cracks, which subsequently
117 resulted in accelerating the corrosion-induced material degradation. They reported that the rate of corrosion-
118 induced concrete cover cracking increased by about 22% in the loaded beam in comparison to unloaded beam.
119 They found that there is a linear relationship between cross sectional area loss of tensile reinforcement and
120 residual flexural strength of corroded RC beams. However, corrosion had a more significant influence on ductility
121 of corrosion damaged RC beams with mass loss ratios greater than 15%, where severe pitting in corroded
122 reinforcement were formed.

123 Torres-Acosta et al. (2006) identified that maximum pitting depth has the greatest impact on the load capacity,
124 rather than the average corrosion penetration in relation to the reinforcement radius. They also reported that
125 corrosion-induced concrete cracking is larger in dry environments, despite a wet setting accelerating pit creation
126 on the reinforcement exterior. The experimental results showed that about 10% reduction in the average corrosion
127 penetration over initial longitudinal reinforcement radius resulted in 60% reduction of the flexural strength of RC
128 beam.

129 Du et al. (2007) conducted experimental testing on corroded and uncorroded RC beams with various
130 reinforcement details under pure flexural loading. They used accelerated corrosion procedure to corrode the
131 specimens. The experimental testing included over-reinforced, balanced-reinforced, under-reinforced, and very
132 under-reinforced RC beams. They reported that corrosion changes the failure mode of over-reinforced beams
133 from brittle failure to a less brittle and even ductile failure mode, but reduces the ductility of under-reinforced

134 beams to fail in a less ductile or even a very brittle manner. They also found that corrosion mass loss more than
135 10% results in premature fracture of tensile reinforcement in very under-reinforced beams, which results in severe
136 reduction of ductility in these beams.

137 Cairns et al. (2008) conducted a set of experimental testing on RC beams with high-ductility plain round bars,
138 with about 4%-10% cross-sectional area loss of reinforcement (lightly corroded). They observed that corrosion
139 changes the failure mechanism of RC beams from flexure to flexure followed by local bond-slip failure of
140 reinforcement. They found that the flexural strength of corroded beams is higher than uncorroded specimens.
141 This is primarily due to an increase in the anchorage strength, to be associated primarily with increased radial
142 stresses on the reinforcement–concrete interface near the end supports.

143 Azad et al. (2007) and (2010), conducted experimental testing on corroded and uncorroded RC beams under pure
144 flexural loading with different cross-sectional sizes and bar diameters. They found that in lightly corroded RC
145 beams (less than 10% of mass loss), the reduction of bar diameter is the most important factor affecting the
146 residual flexural strength of corroded RC beams. However, as corrosion increases, the pitting corrosion effects,
147 loss of bond strength and damage in concrete have significant contribution in residual flexural strength of
148 corroded RC beams. Their research output showed that corrosion damaged beams experiences higher deflection
149 in comparison to uncorroded beams, which is due to loss of flexural stiffness. They also reported that the
150 percentage of mass loss of steel is smaller for larger diameter bars compared with that of smaller bar diameters.

151 Ou et al. (2012) conducted a number of cyclic tests on large scale cantilever beams. One of the specimens was
152 used as an uncorroded control specimen and other four specimens were corroded with varied percentage of mass
153 losses including 1.7%, 3.08%, 4.08% and 8.03%. The uncorroded beams and the beams with different corrosion
154 durations including 12.5, 25, and 50 days (specimens with 1.7%, 3.08% and 4.08% mass loss respectively) were
155 failed in the flexure. The flexural cracks initiated on the top and bottom faces of the beams, and as the drift
156 increased, cracks propagated through the thickness of the section. The cover concrete spalled off at about 3%
157 drift. The main reinforcement (longitudinal) started to show a significant inelastic buckling at 5% drift and
158 subsequently resulted in crushing of core concrete which eventually led to beam failure. For the specimens with
159 low level corrosion from 0% to 4.08% of mass loss, the maximum applied force reached at about 4% drift. The
160 combined influence of core concrete crushing and buckling of longitudinal reinforcement resulted in a significant
161 reduction in load capacity beyond the 4% drift. The fracture of reinforcement was not observed in the

162 experiments. However, as the level of corrosion increased to 8.03%, the mode of failure changed from flexural
163 failure to flexural-shear failure. The envelope response of this specimen shows that the maximum strength was
164 reached at 0.8% drift. Significant softening type behaviour observed once the third hoop fractured at about 2.5%
165 drift.

166 The results of various experiments performed by Zhu and François (2014, 2015) and Zhu et al. (2013) showed
167 that about 1% loss in cross-sectional area of longitudinal reinforcement leads to about 1% decrease in relative
168 yield strength and 0.85% reduction in ultimate capacity. However, this was found to be the result of the concrete
169 crushing. The five beams for the experiments were cast in 1984; three of which were kept in a chloride
170 environment, one in a chloride environment under applied loading and another one experienced corrosion
171 simulation via notches.

172 Yu et al. (2015) conducted a similar experiment to Zhu and François (2014, 2015), with the same dimensions,
173 loading conditions and cover thickness as the 1984 samples. The control beam failed by compressive concrete
174 crushing accompanied with the fracture of both rebar near the middle of the beam. This was after the formation
175 of four cracks beginning at the tensile zone and extending to the compressive zone. On the other hand, the
176 corroded RC beam also formed cracks from the tensile to compressive zone which rapidly increased in width
177 until the beam failed via fracture of a single tensile bar, 75 mm away from the centre, which confirms corrosion
178 does alter the failure mode. Yu et al. (2015) concluded that corrosion longitudinal reinforcement in RC beams
179 has a significant impact on the ductile failure mode, but does not have a great impact on yield and ultimate
180 strength of RC beams.

181 Al-Saidy et al. (2016) conducted a set of experimental testing on corroded RC beams in flexure with and without
182 any shear reinforcement (stirrups). They reported that corroded beams without shear reinforcement fail in a very
183 brittle manner, with about 60% reduction in the maximum deflection. This was due to premature bond failure of
184 the longitudinal reinforcement. The corroded beams with shear reinforcement had some reduction in flexural
185 strength but failed in a more ductile manner. They reported that corroded beams with 5% and 7.5% of mass have
186 about 1% and 25% reduction in the maximum deflections respectively.

187 In order to draw a conclusion on the abovementioned experimental results, the ratio of residual ultimate bending
188 moment strength and the ratio of residual ultimate deformation of each beam specimen is plotted against the
189 corresponding percentage of mass loss, ψ_l (Fig. 1). The residual ultimate bending moment ratio is defined herein

as the ratio of bending moment strength of each tested corroded beam ($M_{u,corr}$) to its corresponding uncorroded beam ($M_{u,0}$). Similarly, the residual maximum deformation ratio is defined as the ratio of maximum deflection of each corroded beam to its corresponding uncorroded beam.

Fig. 1 shows that both the residual ultimate moment ratio and residual maximum deformation ratio follow a linear trend, considering all the experimental results. However, the results are highly scattered due to considering various experiments with different scenarios. It worth noting that, the number of data points in Fig. 1(b) is less than that of Fig. 1(a) as in some studies the maximum deflections of the tested specimens have not reported.

Adverse effect of corrosion on structural performance of RC beams in shear

Table 2 summarises all the previous experimental studies on structural response of corroded Rectangular RC Beams in Shear (RRBS). In this table, ψ_t is the average percentage of mass loss of shear reinforcement (stirrups). Higgins and Farrow III (2006) conducted experimental testing on corroded RC beams with three types of cross-sectional geometry, such as rectangular, Inverted-T, and T sections. They only corroded the shear reinforcement (stirrups) using accelerated corrosion technique. The longitudinal reinforcement was epoxy coated, and hence, remained uncorroded. For each group, a control specimen and three corrosion levels (corrosion at shear reinforcement only) including, light damage with about 12% of mass loss, moderate damage with about 20% of mass loss, and severe with about 40% of mass loss were considered. They reported that diagonal shear cracking of concrete normally arisen in beams at low amplitude loading. However, corroded stirrups could not sustain and constrain shear cracks. Therefore, RC beams with severe corrosion of shear reinforcement corrosion (often highly localised pitting corrosion) will fail in a very brittle manner following the initiation of diagonal shear cracks in concrete.

Suffern et al. (2010) conducted experimental testing to investigate the nonlinear behaviour of disturbed regions with corroded stirrups in RC deep beams. They reported that corrosion rates up to about 20% results in approximately 53% reduction in shear strength of corroded deep beams. They also reported that increasing the shear span-to-depth ratio of beams results in further reduction in shear strength of corroded beams

Xia et al. (2011) carried out experimental testing on uncorroded and corroded RC beams to investigate the shear behaviour of RC beams with corrosion damaged shear reinforcement. They found that corrosion changes the shear failure mechanism of corroded beams. The shear failure of uncorroded beams was initiated by concrete crushing in compression. However, shear failure of corroded beams initiated by fracture of shear reinforcement

(stirrups). Corrosion of shear reinforcement greater than 10% resulted in a significant reduction on in shear capacity of corroded RC beams.

Alaskar (2013) tested seventeen RC beams considering different shear reinforcement types, corrosion mass loss ratios, and repair availability. The longitudinal reinforcement was epoxy coated to be prevented from corrosion, and only transverse reinforcement were corroded using accelerated corrosion technique. They reported that low level of corrosion (up to 8% of mass loss) results in an increase in shear capacity of corroded beams in comparison to uncorroded specimens. However, for mass loss ratios beyond 8% almost a linear reduction in shear strength of corroded beams observed (15.6% of mass loss resulted in 14.4% shear strength reduction).

Khan et al. (2014) conducted experimental testing on two extremely corrosion damaged shear-critical deep beams. The beams were taken out from a twenty-six years old corroded beam subjected to long-term chloride environment by cutting into two short-span beams. Corroding the stirrups did not change the failure modes of corroded deep beams. However, it resulted in a reduction in both shear strength and ductility of the corroded deep beams.

Wang et al. (2015) conducted an experimental investigation to investigate the influence of stirrup and inclined bar corrosion on the shear strength of corroded RC beams. They found that corrosion mass loss less than 10% in inclined bars and stirrups does not have a significant impact on the shear strength. However, higher corrosion rate results in damage in inclined bars and corroded stirrups, as well as degradation surrounding concrete section, which ultimately results in a significant reduction in the shear strength significantly, and changes the failure mode to a more brittle failure.

El-Sayed et al. (2016) conducted experimental testing on slender RC beams (flexural beams) with and without corroded shear reinforcement to investigate the shear behaviour of these corroded beams. They reported that about 7% mass loss in shear reinforcement results in about 10% reduction in shear strength of corroded RC beams. They also found that corrosion changes the shear failure mechanism of RC beams, which is in good agreement with the outcomes of the research carried out by Xia et al. (2011).

El-Sayed (2017) presented procedures for assessment of the shear capacity of RC beams with corroded shear reinforcement. They incorporated their procedure into the current shear design and assessment methods of RC beams, which can be used in the assessment of corroded beams. Their methodology has been validated against experimental results reported by Suffern et al. (2010), El-Sayed et al. (2016), and Khan et al. (2016).

Fig. 2 shows the influence of corrosion on shear strength and ductility of the experimentally tested RC beams. In this figure, $V_{u,corr}$ is the shear strength capacity of the corroded RC beams and $V_{u,0}$ denotes the corresponding value of uncorroded RC beams. Fig. 2 shows that the trend of residual shear strength and ductility of RC beams with increasing level of stirrups corrosion, is different with those of Fig 1. . Moreover, comparison of Fig. 2 and Fig. 1 shows that corrosion has a more significant adverse influence on flexural behaviour of corroded beams than shear (both strength and ductility).

Experimental Investigation of Structural Performance of Corroded RC Columns

The most common collapse mechanism of RC bridge piers, which is observed in the past earthquakes (e.g. Kobe 1998 and Chile 2010), is buckling of the vertical reinforcement together with crushing of core confined concrete and/or fracture of vertical bars. This is due to the lack of confining reinforcement in older RC columns. This problem is more critical in corrosion damaged bridge piers, where corrosion has a significant adverse influence on the stress-strain behaviour of reinforcing bars. Therefore, in this section a critical review of the experimental studies on nonlinear behaviour of corroded RC columns subject to pure axial, and combined axial and lateral loading is provided. It should be noted that despite the numerous experimental studies of corroded beams, there is very little experimental studies conducted on investigation of the effects of corrosion on nonlinear behaviour of RC columns.

Adverse effect of corrosion on Axial Force capacity of RC Columns (AFRCC)

Lee et al. (2000), and Bae et al (2005) conducted experimental studies on short columns to investigate the effectiveness of strengthening using CFRP sheets. They reported that corrosion has a significant impact on the axial load-displacement behaviour of RC columns in compression. The test results show that the corrosion significantly reduces the ductility and crushing strain of concrete in compression and to a lesser extent reduces the compressive strength. Lee et al. (2000) reported that the ductility ratio of the uncorroded specimen was 9.9 whereas the ductility of corroded column was 2.7. They also took physical cross sections through the thickness of the unrepaired corroded column to explore the internal damage due to corrosion. The cross-section cuts showed that corrosion resulted in radial cracks in the cover concrete aligned with the vertical reinforcement. Moreover, they observed that a single crack had formed a continuous ring around the spiral reinforcement which resulted in complete delamination of the cover concrete. This is a very important observation that explains the significant influence of corrosion on the crushing strain of RC columns.

274 It is recognised that the compressive behaviour of confined concrete depends on mechanical properties of
275 transverse reinforcement including yield strength and fracture strain and volumetric ratio of tie reinforcement
276 (Park et al. 1982; Mander et al. 1988a,b; Penelis and Kappos 1997). Since tie reinforcement is the outmost
277 reinforcement to be exposed to chloride attack its corrosion starts prior to the corrosion initiation of the vertical
278 reinforcing bars. Therefore, the volumetric ratio of confinement reinforcement, fracture strain and yield strength
279 are reduced. Therefore, the tie reinforcement fractures much earlier than the uncorroded columns under
280 compression.

281 Vu et al (2017) conducted a set of experimental testing to investigate the nonlinear behaviour of confined concrete
282 with corroded transverse reinforcement (confinement reinforcement). They considered various corrosion-induced
283 mass loss ratios of transverse reinforcement, arrangement and configuration of confinement reinforcement and
284 cross-sectional shape of confined concrete. The experimental results showed that as mass loss ratio of confining
285 reinforcement increases both capacity and ductility of the corrosion damaged confined concrete significantly
286 decreases, and the post-peak softening branch of the stress-strain curve becomes much steeper. In other words,
287 corrosion changes the failure mode of confined concrete from ductile to brittle. The experimental results also
288 show that the effect of corrosion is less significant for mass loss ratios less than 10%. Finally, they developed an
289 empirical uniaxial constitutive model for corrosion damaged confined concrete using the experimental data. Their
290 proposed model incorporates the effect of corrosion into the model for uncorroded confined concrete developed
291 by Mander et al. (1988b). Their model is in good agreement with the experimental results for both square and
292 circular specimens with various mass loss ratios and confinement reinforcement subject to compression axial
293 loading.

294 To date, Vu et al (2017) study is the only experimental testing on corroded confined concrete and their constitutive
295 model is the only available model for the corroded confined concrete. However, there is no experimental data
296 available on the nonlinear behaviour of corroded confined concrete under cyclic loading.

297 Table 3 summarises the experimental studies carried out on corroded RC columns subjected to pure axial
298 compression loading.

299 ***Adverse effect of corrosion on nonlinear Flexural behaviour of Circular RC Columns (FCRCC)***

300 In highway bridges, piers are normally located in central reserve, thus the piers end regions can experience higher
301 rates of corrosion due to the splashing of de-icing salt from the adjacent road/or downfall of water carrying

chloride ions from above (due to failure of expansion joints on the deck). This is very critical for bridges in seismic zones, where the lower region of bridge piers (or both ends in integral bridge piers) is exactly where plastic hinge is formed during earthquake excitation. Therefore, in all of the experimental testing of corroded bridge piers, researchers tested cantilever columns, and corrode either the entire column or only the lower region. Aquino and Hawkins (2007) conducted a set of experimental tests on six RC columns. One column was used as the control uncorroded specimen, one column was used as a control corroded specimen without strengthening and the other four columns were strengthened using CPRP sheets. The columns were corroded using an accelerated corrosion procedure. In this experiment, only 1200mm immediately above the base was corroded. In these columns a heavy accumulation of rust product on the surface of the concrete and a uniform staining of the corrosion along the length of longitudinal reinforcement is observed. Of these three columns (1, 3 and 5), Column 1 presented the most severe cracking and rust accumulation on the surface of concrete (Aquino and Hawkins, 2007). The observed damage in the uncorroded specimen was mainly due to the opening of a large crack at the connection between the column and the base due to slippage of the bars in the base. A few small flexural horizontal cracks were observed in the column along with major cracks running parallel to the longitudinal reinforcement, which appeared close to the maximum load and opened significantly when this load was attained. This is the typical failure mode of columns with insufficient lap splice lengths which does not allow the full strength and straining capacity of the reinforcing steel to be developed. However, the only corroded column without any strengthening tested in this study showed a different failure mode. Failure during the cyclic loading was due to buckling of the vertical reinforcement in compression. It was observed that most of the tie reinforcement (hoops) had fractured due to pitting corrosion and they had experienced a significant loss of cross-sectional area during the corrosion process. The fracture of the tie reinforcement resulted in a significant loss of confinement and subsequently premature buckling of the corroded vertical reinforcement in compression (Aquino and Hawkins, 2007).

Ma et al. (2012) carried out a series of experimental testing on thirteen columns with varied corrosion levels and axial force ratios. They also used an accelerated corrosion procedure to corrode the test specimens. Each specimen consisted of a 260mm diameter and 1000 mm long column cast into a 1300 mm×360 mm×400 mm base. The effective length of the columns was and the span to depth ratio were 820 mm and 3.15, respectively. The clear cover to the spirals was 30 mm. Six 16mm diameter reinforcing bars were used as vertical reinforcement and

8mm diameter reinforcing bars at 100mm spacing were used as the tie reinforcement (Ma et al. 2012). Eight out of thirteen columns had axial force ratios ($P/A_g f_c$, where P is the axial force, A_g is the gross cross-sectional area of the columns, and f_c is the compressive strength of concrete) between 0.15 and 0.4 and five of them had axial force ratios between 0.60 and 0.90 which are rather high compared to normal bridge columns. Therefore, only the results of eight columns with axial force ratios below 0.5 are discussed in this section. In the three control specimens (with different axial force ratios), the first flexural crack formed perpendicular to the column axis in the bottom of column where the plastic hinge region occurred. These cracks propagated and with the increasing lateral load diagonal cracks appeared. In the last cycle, the core concrete crushed indicating the failure of these specimens (Ma et al. 2012). The five corroded columns C9-15, C4-25, C9-25, C9-40 and C14-32, showed a flexural failure mechanism similar to the uncorroded specimens. However, the failure of these corroded specimens was very brittle. The crack spacing of corroded specimens at failure was greater than for the corresponding control specimens. As the displacement demand increased, cover concrete was spalled at the bottom of the column (plastic hinge region) which was then followed by severe buckling of the longitudinal bars and crushing of the core concrete. As expected the energy dissipation capacity and ductility of specimens decreased with increasing reinforcement corrosion and axial load ratio. Columns C0-25, C4-25 and C9-25 had the same axial load ratio, however a smaller hysteretic area was observed in severely corroded specimen C9-25. Specimen C9-15, C9-25 and C9-40 had almost the same corrosion level, but severe degradation in the hysteretic responses was observed with increasing the axial force ratio. Comparing the axial force and corrosion level, it was found that the corrosion level is the governing factor that affects the hysteretic behaviour. For example, specimen C14-32 which was subjected to slightly lower axial load than specimen C4-25, but which had more severe corrosion damage, showed very poor energy dissipation capacity and failed in a brittle manner. This was mainly due to the inelastic buckling of main bars (vertical reinforcement), which caused spalling concrete cover and crushing of core concrete.

Yuan et al. (2017) conducted experimental tests on eight circular RC columns with varied corrosion rates under combined repeated axial loading and cyclic lateral loading. In their experimental program column C0 was uncorroded, the three columns C5-L0, C5-L40 and C5-L60 were with target corrosion rate of 5%, and four others, C10-L0, C10-L40, C10-L60 and CG10 were with target corrosion rate of 10%. Using an electrochemical system, they implemented accelerated corrosion procedure to accelerate the corrosion rate of embedded reinforcing bars. Results showed that corrosion has a significant adverse impact on capacity of the columns. Moreover, they found

that vertical axial loading has no significant impact on yield strength and ultimate capacity of the tested specimens. Based on their finite element analysis, the yield strength and ultimate displacement of corrosion damaged columns were declined by 35% and 34%, respectively. A summary of the abovementioned experiments is presented in Table 4.

Fig. 3 shows the impact of corrosion on nonlinear flexural behaviour of all the experimentally tested circular RC columns in the literature. As it is shown in Fig. 3(a), there is no correlation the corrosion and residual ductility and strength of corroded beams using the available data ($R^2=-0.42$). This is because there are only 11 data points for flexural capacity of corroded circular RC columns varied in corrosion and axial force in the literature, and hence, data points are highly scattered. Therefore, more experimental research is required on circular columns to draw a solid conclusion. However, based on the available data and fitted curve, the flexural capacity of corroded circular columns shows a slight reduction in comparison with that of uncorroded column. This is because the tested specimens are not corroded enough and their average percentage of mass loss is up to 16%.

Fig. 3(b) shows the influence of corrosion on residual displacement capacity of circular RC columns which is defined here as the ratio between maximum tip displacement of each corroded specimen ($\Delta_{u,corr}$) to its corresponding uncorroded specimen ($\Delta_{u,0}$). Similar to Fig. 3(a), the fitted line in Fig. 3(b) does not show any correlation between corrosion and residual displacement of corroded circular columns ($R^2=-0.33$).

Adverse effect of corrosion on nonlinear Flexural behaviour of Rectangular RC Columns (FRRCC)

Lee et al. (2003) conducted experimental testing on six rectangular RC columns with 300mm \times 300mm in cross section and 1100 mm in height. They also used accelerated corrosion procedure to produce various corrosion levels. The columns tested under simultaneous axial and lateral cyclic loading. They found that corrosion results in a severe decrease in mechanical properties of reinforcing bars and spalling of concrete cover, which caused a significant reduction in confinement of core concrete. In their experiment, the failure of uncorroded specimen initiated by bond failure and slippage of vertical bars. However, corrosion changed this failure mode to buckling of vertical reinforcement and fracture of hoops (confinement reinforcement).

Meda et al. (2014) conducted experimental testing on corroded and uncorroded rectangular columns under cyclic loading. They used accelerated corrosion procedure to corrode the columns. The columns were tested under axial (400 kN) and lateral cyclic loading with about 20% corrosion mass loss of vertical reinforcements. It should be noted that Meda et al. (2014), just corroded the vertical reinforcing bars, and the transverse reinforcements were

protected from corrosion. They reported that corrosion has a significant impact on the nonlinear response of rectangular RC columns subjected to cyclic loading. They observed corrosion results in about 30% reduction in the ultimate strength and about 50% reduction in the ductility, as well as significant cyclic degradation (loss of stiffness) in the last cycles.

Guo et al. (2015b) conducted a set of experimental testing on corroded and uncorroded cantilever rectangular RC bridge piers. The test specimens were corroded using accelerated corrosion procedure, and tested under combined axial and lateral cyclic loading. They found that corrosion mass loss greater than 10% results in severe degradation in nonlinear cyclic behaviour of RC bridge piers. They reported that heavily corroded column with average mass loss of 15.24% shows the smallest hysteretic responses, greatest cyclic degradation of stiffness and strength, and subsequently a significant reduction in ductility and energy dissipation capacity.

All the previous experimental studies on flexural behaviour of corroded rectangular RC columns are summarised in Table 5. Fig. 4 summarises the influence of corrosion on flexural behaviour of rectangular RC columns. Comparing Fig. 4(a) with Fig. 4(b), ductility reduction of corroded rectangular columns is slightly more than their flexural capacity loss. The other interesting finding is that the fitted line equation for flexural strength loss of rectangular RC columns (Fig. 4(a)) is same to that of rectangular RC beams (Fig. 1(a)).

Numerical Modelling of Corroded RC Components

Modelling nonlinear flexural behaviour

In the recent few years, a significant number of researchers have employed analytical and nonlinear finite element analysis approaches (Coronelli and Gambarova 2004, El Maaddawy et al. 2005b, Kallias 2011, for structural performance evaluation of corroded RC components. Azam (2010) and Alaskar (2013) have used modified compression field theory (MCFT) to estimate the shear strength of uncorroded and corroded RC beams. More recently, Di Carlo et al. (2017a,b) have employed 3D continuum finite element modelling approaches for nonlinear structural and seismic performance assessment of corroded RC bridge piers subject to cyclic loading. Considering its capability in nonlinear bond-slip modelling, the 3D finite element modelling approach is widely used in the literature to develop the bond strength deterioration models (Lundgren et al. (2012), Kallias A.M and Rafiq M.I 2013).

All of these numerical models have been validated against some benchmark experimental test data.

Although all the aforementioned numerical models can simulate the nonlinear behaviour of RC components with relatively good accuracy, they are computationally very expensive. Therefore, it is not possible to easily implement these models in nonlinear dynamic analyses and seismic fragility assessment of bridge systems. Accordingly, researchers in earthquake engineering community have employed force-based fibre beam-column element (Spacone et al. 1996a and 1996b, Taucer et al. 1991) for seismic fragility assessment of corroded RC bridges. A force-based fibre beam-column element is a line element in which the moment-curvature response at integration points is determined from the assigned fibre sections for each integration point. Currently, force-based fibre elements are the most advanced 1D models available in the literature for nonlinear analysis of RC components. In the force-based elements, moment is considered to be distributed along the entire length of the column. The curvatures at each section (integration point) are accordingly estimated for the given moment at that section. Weighting the integration of the sections' response, finally, the column response is obtained. (Taucer et al. 1991). Using a fibre section technique, the cross section of the member is discretised into several concrete and steel fibres. The material nonlinearity is considered through uniaxial constitutive material models for reinforcing steel and concrete (confined and unconfined concrete cover), and hence, the accuracy of the model is highly dependent on the accuracy of the material models. Therefore, several researchers have put significant effort to implement corrosion damaged material models in nonlinear fibre beam-column elements. Kashani et al. (2015b) proposed a phenomenological hysteretic material model for uncorroded and corroded reinforcing bars. This model simulates the influence of corrosion on low-cycle fatigue and inelastic buckling behaviour of reinforcing steel bars. Rao et al. (2016a) proposed a simplified nonlinear analytical model to simulate corrosion-induced degradation of RC bridge pier. The main focus of this models is on average cross-sectional area reduction of reinforcing bars due to corrosion and other deteriorating mechanisms are disregarded.

Dizaj et al. (2018a) developed a modelling technique using force-based fibre beam-column element for nonlinear seismic performance evaluation of corroded RC bridge piers, which is currently the most advanced model available in the literature. This model is validated against a benchmark experimental testing conducted by Meda et al. (2014), then implemented in vulnerability assessment of corrosion damaged RC frames (Dizaj et al., 2018b).

Although fibre beam-column element models are very efficient in simulation nonlinear flexural response of RC components, they do not account for nonlinear shear deformation and axial-shear-flexure interaction. Therefore, in shear critical RC components, fibre beam-column elements are not very accurate. Some researchers have used

uncoupled nonlinear shear springs to account for shear deformation in uncorroded RC components, but these springs do not account for axial-shear-flexure interaction (Jeon et al., 2015). However, there has not been any significant research conducted on modelling axial-shear-flexure interaction in corroded RC components. This is an important area for future studies (further discussion is available in section 5 of this paper).

Comparison of the state-of-the-art numerical models with available experimental data

As discussed in previous section, the nonlinear moment-curvature response of RC sections (accounting for axial-flexure interaction) is extremely important for structural assessment of corroded RC bridge piers and beams. Furthermore, moment-curvature response of cross section is the basis of nonlinear fibre beam-column element model implementation for seismic performance assessment of uncorroded and corroded RC bridges. In this section, a comparison has been made between the predicted residual bending moment capacity of corroded beams and columns using the state-of-the-art models in the literature and the available experimental results.

The detailed derivation of theoretical axial force-moment-curvature relationship of corroded RC sections is discussed in Kashani et al. (2017). The main assumptions in this method are: (i) plane sections remain plane and (ii) shear stress/deformation in the beam is small, and hence, there is no shear-flexure (Euler-Bernoulli beam theory). This technique accounts for inelastic buckling of the compression reinforcing bars (Kashani, 2014). The slenderness ratio, L_{eff}/D , used in the buckling model was taken as the ratio of effective buckling length (L_{eff}) to diameter of vertical reinforcement (D). In this study, the L_{eff} is taken from the experimental results. In the absence of experimental data, the procedure developed by Dhakal and Maekawa (2002) can be used to calculate the L_{eff} . The constitutive material models that are used here are the ones that originally developed by Kashani (2014), and later validated by Dizaj et al. (2018a). These models account for the adverse impact of corrosion on nonlinear stress-strain behaviour of reinforcing bars (strength and ductility), inelastic buckling of longitudinal reinforcement in compression (vertical bars in columns), cracked concrete cover, and core confined concrete (due to corrosion of confinement reinforcement). The detailed discussion of the material models is available in (Kashani et al., 2016).

Using the numerical modelling technique developed by Kashani et al. (2017), the bending moment capacity of all the corroded and uncorroded rectangular columns (with various axial force) and flexural beams are computed and plotted against their corresponding experimental values (reported in Tables 1 and 5) in Fig. 5. In this figure, $M_{u,comp}$ is the computational ultimate moment of the tested specimens and $M_{u,exp}$ is that of their corresponding

experimental values. As it is shown in Fig. 5, there is a good correlation between the predicted and experimental values of bending moment capacity. This confirms that the developed numerical model is able to precisely predict the residual capacity of corroded RC components. A quantitative comparison between the computed values and experimental data have been prepared in a set of tables and attached as downloadable supplementary material (Comp Vs Exp.xlsx).

Outstanding Issues and Needs for Future Research

There is a large amount of experimental data available in the literature on large-scale testing of corroded RC beams in flexure and/or shear under monotonic and cyclic static loading. In comparison to corroded RC beams, there is very little experimental data available in the literature on large-scale testing of corroded RC columns (rectangular and circular) under axial and static lateral loading (monotonic and cyclic). All the previous experimental testing of corroded RC columns has been conducted on flexural govern columns, and there has been no experimental testing on shear critical columns. In general, there is a need for further experimental testing on RC columns with different geometry, reinforcing details, axial force ratios, and shear span to depth ratio. In terms of modelling, there is a large number of numerical models in the literature using 2D and 3D continuum finite element and nonlinear fibre element technique using beam-column models. The existing models can predict the residual capacity and simulate the nonlinear behaviour of RC elements under flexural loading very well (including modelling axial-flexure interaction). However, modelling axial-shear-flexure interaction is a major challenge in fibre element technique, as the nonlinear beam-columns elements employ Euler-Bernoulli beam theory and do not account for axial-shear-flexure interaction. This is in addition to the significant paucity in the literature on the impact of corrosion on shear critical columns. Moreover, there is only one experimental testing available in the literature on corroded RC columns under dynamic earthquake loading (Yuan et al., 2018). There is a need for some benchmark shaking table experimental tests on corroded RC columns with different reinforcement details and ground motion types. Furthermore, recent advances in X-Ray Computing Tomography (CT) scanning facilities, allow researchers to scan corroded RC elements using X-Ray CT scanner prior to structural testing (Lim et al., 2017). The advancement in CT scan technology and computing power allows more sophisticated 3D multi-scale multi-physics nonlinear finite element modelling of corroded RC elements (Michel et al., 2015). The advantage of multi-scale multi-physics is that researchers can model the whole process of corrosion induced progressive damage in structural integrity as well as residual capacity of corroded RC elements.

Another advantage of multi-scale modelling is that multiple failure modes can be automatically captured (e.g. axial-shear-flexure). However, there is a need for significant experimental and computational research to validate and calibrate the new multi-scale multi-physics models. However, these models are computationally very expensive, and therefore, the major challenge in future will be implementing these models in the analysis of whole bridge structures under various loading scenarios (traffic, trains, earthquakes etc.).

Conclusions

An extensive review of all the experimental research on corroded RC components including (i) beams in flexure, (ii) beams in shear, (iii) columns under pure axial compressive loading, (iv) circular columns in flexure, and (v) rectangular columns in flexure is conducted. Furthermore, a crucial review of the current state-of-the-art numerical models in the literature is conducted, and an exemplary comparison has been made between these models and experimental testing of corroded RC beams in flexure. The main findings of this state-of-the-art review paper can be summarised as follows:

- (1) Regression analyses of all the experimental studies on corroded RC beams show that both the flexural strength and ductility loss follow a similar linear trend, with ductility loss being more critical than strength loss.
- (2) Corrosion has less adverse impact on residual shear strength of corroded RC beams in comparison with residual flexural strength. Moreover, the trend of shear strength loss of corrosion damaged RC beams with increasing level of corrosion is different with that of flexural behaviour.
- (3) As corrosion level increases, the ductility and compressive strength of confined concrete decreases. This results in a significant reduction in axial compressive capacity of RC columns in seismic regions.
- (4) Experimental results show that flexural strength reduction of corroded rectangular RC columns is generally more than corroded circular RC columns. However, the number of available experimental tests in the literature is not sufficient to draw a solid conclusion, and therefore, there is need for further research in the future.
- (5) While the flexural behaviour of rectangular corroded RC columns follows a linear trend, there is not any solid evidence to show this trend for circular columns. This confirms that there is a need for further experimental researches on corrosion damaged circular columns.

(6) Exemplary comparisons between the computational residual capacity of corroded RC beams and columns with their corresponding experimental values, confirms that the currently available models in the literature can accurately anticipate the residual capacity of corrosion damaged RC beams and columns in flexure.

References

- Alaskar, A. (2013). "Shear Behaviour of Slender RC Beams with Corroded Web Reinforcement". Master thesis, University of Waterloo, Ontario, Canada.
- Afsar Dizaj, E., Madandoust, R., Kashani, M. M. (2018a). "Exploring the impact of chloride-induced corrosion on seismic damage limit states and residual capacity of reinforced concrete structures"., *Struct Infrastruct Eng.*, 14(6):714-29.
- Afsar Dizaj, E., Madandoust, R., Kashani, M. M. (2018b). "Probabilistic seismic vulnerability analysis of corroded reinforced concrete frames including spatial variability of pitting corrosion"., *Soil Dynamics and Earthquake Engineering.*, 114: 97–112.
- Akiyama, M., Frangopol, D. M. (2013). "Long-term seismic performance of RC structures in an aggressive environment: emphasis on bridge piers." *Struct Infrastruct E.*, 10 (7): 865-879.
- Akiyama, M., Frangopol, D. M., Matsuzaki, H. (2011). "Life-cycle reliability of RC bridge piers under seismic and airborne chloride hazards." *Earthquake Eng and Struct Dyn.*, 40: 1671–1687.
- Alexopoulos, N. D., Apostolopoulos, C. A., Papadopoulos, M. P., Pantelakis, S.G. (2007). "Mechanical Performance of BStIV Grade Steel Bars with Regard to the Long-term Material Degradation Due to Corrosion Damage." *Constr Build Mater.*, 21(6): 1362-1369.
- Alipour, A., Shafei, B. and Shinozuka, M. (2011). "Performance evaluation of deteriorating highway bridges located in high seismic areas." *J Bridge Eng.*, 6 (5): 597-611.
- Almusallam, A.A. (2001). "Effect of degree of corrosion on the properties of reinforcing steel bars." *Const and Build Mat.*, 15(8): 361-368.
- Al-Saidy A. H., Saadatmanesh, H., El-Gamal, S., Al-Jabri K. S., Waris, B. M. (2016). "Structural behavior of corroded RC beams with/without stirrups repaired with CFRP sheets." *Materials and Structures* 49 (9): 3733-3747.
- American Society of Civil Engineers. (2013). Report Card for America's Infrastructure. Retrieved from <https://www.infrastructurereportcard.org/a/#p/bridges>

553 Apostolopoulos, C. A. (2009). "The influence of corrosion and cross-section diameter on the mechanical
554 properties of B500c steel." *J Mater Eng Perfor.*, 18 (2): 190-195.

555 Apostolopoulos, C. A., Koutsoukos, P. G. (2008). "Study of the corrosion of reinforcement in concrete elements
556 used for the repair of monuments." *Constr Build Mater.*, 22 (7): 1583–1593.

557 Apostolopoulos, C. A., Michalopoulos, D. (2007). "Corrosion of reinforcing steel and low cycle fatigue
558 behaviour." *Mater Corr.*, 58 (6): 438–446.

559 Apostolopoulos, C. A., Papadakis, V. G. (2008). "Consequences of steel corrosion on the ductility properties of
560 reinforcement bar." *Constr Build Mater.*, 22(12): 2316-2324.

561 Apostolopoulos, C. A., Papadopoulos, M. P. (2007). "Tensile and low cycle fatigue behavior of corroded
562 reinforcing steel bars S400." *Constr Build Mater.*, 21(4): 855-864.

563 Apostolopoulos, C. A., Papadopoulos, M. P., Pantelakis, S. G. (2006). "Tensile behavior of corroded reinforcing
564 steel bars BSt 500s." *Construct and Build Mater.*, 20(9): 782–789.

565 Apostolopoulos, C. A., Pasialis, V. P. (2008). "Use of quality indices in comparison of corroded technical steel
566 bars B500c and S500s on their mechanical performance basis." *Constr Build Mater.*, 22 (12): 2325-2334.

567 Aquino, W. (2002). "Long-term performance of seismically rehabilitated corrosion-damaged columns." PhD
568 Thesis, University of Illinois at Urbana Champaign.

569 Aquino, W., Hawkins, N. M. (2007). "Seismic Retrofitting of Corroded Reinforced Concrete
570 Columns Using Carbon Composites." *ACI Structural Journal.*, 104(3): 348-356.

571 Azad, A. K., Ahmad, S., Azher, S. (2007). "Residual strength of corrosion-damage reinforced concrete beams." *ACI Struct J.*, 104 (1): 40-47.

572
573 Azad, A. K., Ahmad, S., Al-gohi, B. H. A. (2010). "Flexural strength of corroded reinforced
574 concrete beams." *Magazine of Concrete Research.*, 62 (6): 405-414.

575 Azam, R. (2010). "Behaviour of shear critical RC beams with corroded longitudinal steel reinforcement," MASc
576 Thesis, University of Waterloo, Waterloo, Ontario, Canada.

577 Bae, S.W., Belarbi, A., and Myers, J.J. (2005). "Performance of Corrosion-Damaged RC Columns Repaired by
578 CFRP Sheets." *ACI, Special Publication*; 230: 1447-1464.

579 Belarbi, A. I., Sang-Wook, B. (2007). "An experimental study on the effect of environmental exposures and
580 corrosion on RC columns with FRP composite jackets." *Compos Part B: Eng.*, 38 (5): 674-684.

581 Berto, L., Vitaliani, R., Saetta, A., Simioni, P. (2009). "Seismic assessment of existing RC structures affected by
 582 degradation phenomena." *Struct Saf.*, 31(4): 284–297.

583 Biondini, F., Camnasio, E., Palermo, A. (2014). "Lifetime seismic performance of concrete bridges exposed to
 584 corrosion." *Struct Infrastruct E.*, 10(7): 880-900.

585 Bousias, S. N., Triantafyllou, T. C., Fardis, M. N., Spathis, L. (2004). "Fiber-reinforced polymer retrofitting of
 586 rectangular reinforced concrete columns with or without corrosion." *ACI Struct J.*, 101 (4).

587 Broomfield, J. P. (2007). *Corrosion of steel in concrete: understanding, investigation and repair*. 2. Taylor and
 588 Francis.

589 Cairns, J., Du, Y., Law, D. (2008). "Structural performance of corrosion-damaged concrete beams." *Mag*
 590 *Concrete Res.*, 60 (5): 359-370.

591 Cairns, J., Plizzari, G. A., Du, Y. G., Law, D. W., Chiara, F. (2005). "Mechanical properties of corrosion-
 592 damaged reinforcement." *ACI Mat J.*, 102 (4): 256–264.

593 Castel, A., Francois, R., Arliguie, G. (2000). "Mechanical behaviour of corroded reinforced concrete beams-Part
 594 1: experimental study of corroded beams." *Materials and Structures.*, 33(9):539-544.

595 Chiu, C. K., Tu, F. J., and Hsiao, F. P. (2015). "Lifetime seismic performance assessment for chloride-corroded
 596 reinforced concrete buildings." *Structure and Infrastructure Engineering.*, 11(3): 345–362.

597 Choe, D., Gardoni, P., Rosowsky, D., and Haukaas, T. (2008). "Probabilistic capacity models and seismic
 598 fragility estimates for RC columns subject to corrosion." *Reliab Eng Syst Safe.*, 93(3): 383–393.

599 Choe, D., Gardoni, P., Rosowsky, D., Haukaas, T. (2009). "Seismic fragility estimates for reinforced concrete
 600 bridges subject to corrosion." *Struct Saf.*, 31(4): 275-283.

601 Chung, L., Husam, N., Perumalsamy, B. (2008). "Flexural behavior of concrete slabs with corroded bars.
 602 *Cement & Concrete Composites*" *Cement Concrete Composites.*, (30): 184-193.

603 Coronelli, D., Gambarova, P. (2004). "Structural assessment of corroded reinforced concrete beams: modelling
 604 guidelines." *J Struct Eng.*, 130 (8): 1214-1224.

605 Cui, F., Zhang, H., Ghosn, M., & Xu, Y. (2018). "Seismic fragility analysis of deteriorating RC bridge
 606 substructures subject to marine chloride-induced corrosion." *Engineering Structures*, 155, 61-72.

607 Dhakal, R. P., Maekawa, K. (2002). "Reinforcement stability and fracture of cover concrete in RC members." *J*
 608 *of Struct Eng.*, 128 (10): 1253–1262.

609 Di Carlo, F., Meda, A., & Rinaldi, Z. (2017a). "Numerical evaluation of the corrosion influence on the cyclic
610 behaviour of RC columns.", *Engineering Structures.*, 153, 264-278.

611 Di Carlo, F., Meda, A., & Rinaldi, Z. (2017b). "Numerical cyclic behaviour of un-corroded and corroded RC
612 columns reinforced with HPFRC jacket.", *Composite Structures.*, 163, 432-443.

613 Du, Y., Clark, L. A., Chan, A. H. C. (2007). "Impact of reinforcement corrosion on ductile behaviour of
614 reinforced concrete beams." *ACI Struct J.*, 104 (3): 285-293.

615 Du, Y. G., Clark, L. A., Chan, A. H. C. (2005a). "Effect of corrosion on ductility of reinforcing bars." *Magazine
616 of Conc Res.*, 57 (7): 407-419.

617 Du, Y. G., Clark, L. A., Chan, A. H. C. (2005b). "Residual capacity of corroded reinforcing bars." *Magazine of
618 Conc Res.*, 57 (3): 135-147.

619 El Maaddawy, T., Soudki, K., Topper, T. (2005a). "Analytical model to predict nonlinear flexural behaviour of
620 corroded reinforced concrete beams." *ACI Struct J.*, 102 (4): 550-559.

621 El Maaddawy, T., Soudki, K., Topper, T. (2005b). "Long-Term Performance of Corrosion-Damaged
622 Reinforced Concrete Beams." *ACI Struct J.*, 102 (5): 649-656.

623 El-Sayed, A. K. (2017). "Shear capacity assessment of reinforced concrete beams with corroded
624 stirrups." *Construction and Building Material.*, 134: 176-184.

625 El-Sayed, A. K., Hussain, R. R., Shuraim, A. (2016). "Influence of Stirrup Corrosion on Shear Strength of
626 Reinforced Concrete Slender Beams." *ACI Structural Journal.*, 113(6): 1223-1232.

627 Fernandez, I., Bairan, J. M., & Mari, A. R. (2015). Corrosion effects on the mechanical properties of reinforcing
628 steel bars. Fatigue and σ - ϵ behavior, *Construction and Building Materials.*, 101, 772-783.

629 Ghosh, J., Padgett, J. (2010). "Aging considerations in the development of time-dependent seismic fragility
630 curves." *J Struct Eng.*, 136 (12): 1497-1511.

631 Ghosh, J., Sood, P. (2016). "Consideration of Time-Evolving Capacity Distributions and Improved Degradation
632 Models for Seismic Fragility Assessment of Aging Highway Bridges." *Reliability Engineering & System Safet.*,
633 154 :197-218.

634 Guo, A., Yuan, W., Lan, Ch, Guan, X., Li, H. (2015a). "Time-dependent seismic demand and fragility of
635 deteriorating bridges for their residual service life." *Bulletin of Earthquake Engineering.*, 13(8): 2389-2409

636 Guo, A., Li, H., Ba, X., Guan, X., Li, H. (2015b). "Experimental investigation on the cyclic performance of
637 reinforced concrete piers with chloride-induced corrosion in marine environment." *Engineering Structures.*, 105:
638 1-11.

639 Higgins, Ch., Farrow, W. (2006). "Tests of Reinforced Concrete Beams with Corrosion Damaged Stirrups."
640 *ACI Structural Journal.*, 103(1): 133-141.

641 Jeon, J. S., DesRoches, R., Lowes, L. N., Brilakis, I. (2015). "Framework of aftershock fragility assessment—case
642 studies: older California reinforced concrete building frames." *Earthquake Engineering and Structural
643 Dynamics.*, 44(15):2617–2636.

644 Kallias, A. N. (2011). "Advanced probabilistic resistance assessment of corroding RC beams." PhD Thesis,
645 University of Surrey.

646 Kashani, M. M. (2014). "Seismic Performance of Corroded RC Bridge Piers: Development of a Multi-
647 Mechanical Nonlinear Fibre Beam-Column Model." PhD Thesis, Bristol: University of Bristol.

648 Kashani, M. M., Alagheband, P., Khan, R., & Davis, S. (2015a). Impact of corrosion on low-cycle fatigue
649 degradation of reinforcing bars with the effect of inelastic buckling. *International Journal of Fatigue*, 77, 174–
650 185.

651 Kashani, M. M., Lowes, L. N., Crewe, A. J., Alexander, N. A. (2015b). "Phenomenological hysteretic model for
652 corroded reinforcing bars including inelastic buckling and low-cycle fatigue degradation." *Comput Struct.*, 156:
653 58-71.

654 Kashani, M. M., Lowes, L. N., Crewe, A. J., & Alexander, N. A. (2016). "Nonlinear fibre element modelling of
655 RC bridge piers considering inelastic buckling of reinforcement." *Engineering Structures.*, 116, 163–177.

656 Kashani, M. M., Crewe, A. J., & Alexander, N. A. (2013a). "Nonlinear cyclic response of corrosion-damaged
657 reinforcing bars with the effect of buckling." *Construction and Building Materials.*, 41, 388–400.

658 Kashani, M. M., Crewe, A. J., & Alexander, N. A. (2013b). "Nonlinear stress– strain behaviour of corrosion-
659 damaged reinforcing bars including inelastic buckling." *Engineering Structures.*, 48, 417–429.

660 Kashani, M. M., Crewe A. J., Alexander, N. A. (2017). "Structural capacity assessment of corroded RC bridge
661 piers." *Proceedings of the Institution of Civil Engineers-Bridge Engineering.*, 170(1): 28-41.

662 Kallias, A.N., Rafiq, M.I. (2013). "Performance assessment of corroding RC beams using response surface
663 methodology", *Engineering Structures.*, 49: 671–685.

664 Khan, I., Francois, R., Catel, A. (2014). "Experimental and analytical study of corroded shear-critical
665 reinforced concrete beams." *Materials and Structures*, 47:1467–1481.

666 Lee, C., Bonacci, J. F., Thomas, M. D., Maalej, M., Khajepour, S., Hearn, N., Sheikh, S. (2000). "Accelerated
667 corrosion and repair of reinforced concrete columns using carbon fibre reinforced polymer sheets." *Can J Civil*
668 *Eng.*, 27 (5): 941-948.

669 Lee, H., Kage, T., Noguchi, T., Tomosawa, F. (2003). "An experimental study on the retrofitting effects of
670 reinforced concrete columns damaged by rebar corrosion strengthened with carbon fibre sheets." *Cement*
671 *Concrete Res.*, 33: 536-570.

672 Lee, H. S., Cho, Y. S. (2009). "Evaluation of the mechanical properties of steel reinforcement embedded in
673 concrete specimen as a function of the degree of reinforcement corrosion." *Int J Fracture.*, 157 (1-2): 81-88.

674 Li, X., Liang, Y.-S., Zhao, Z.-H., & Lv, H.-L. (2015). Low-cycle fatigue behavior of corroded and CFRP-
675 wrapped reinforced concrete columns. *Construction and Building Materials*, 101, 902–917.

676 Liu, X., Jiang, H., He, L. (2017). "Experimental investigation on seismic performance of corroded reinforced
677 concrete moment-resisting frames." *Engineering Structures.*, 153: 639-652.

678 Li, D., Wei, R., Xing, F., Sui, L., Zhou, Y., Wang, W. (2018). "Influence of Non-uniform corrosion of steel
679 bars on the seismic behaviour of reinforced concrete columns". *Construction and Building Materials.*, 167: 20-
680 32.

681 Li, J., Gong, J., Wang, L. (2009). "Seismic behavior of corrosion-damaged reinforced concrete columns
682 strengthened using combined carbon fiber-reinforced polymer and steel jacket". *Construction and Building*
683 *Materials.*, 23: 2653-2663.

684 Lim, S., Akiyama, M., Frangopol, D. M., & Jiang, H. (2017). "Experimental investigation of the spatial variability
685 of the steel weight loss and corrosion cracking of reinforced concrete members: novel X-ray and digital image
686 processing techniques.", *Structure and Infrastructure Engineering.*, 13(1), 118-134.

687 Lundgren, K., Kettil, P., Hanjari, K., Schlune, H., Roman, A. (2012). "Analytical model for the bond-slip
688 behaviour of corroded ribbed reinforcement", *Structure and Infra Structure Engineering.*, 8(2): 157-169.

689 Ma, Y., Che, Y., Gong, J. (2012). "Behavior of corrosion damaged circular reinforced concrete columns." *Construction and Building Materials.*, 29: 548-556.

690 Malumbela, G., Moyo, P., Alexander, M. G. (2009). "Behaviour of RC beams corroded under sustained service
691 loads.", *Construction & Building Materials.*, 23: 3346–3351.

693 Mander, J. B., Priestley, M. J. N., Park, R.. (1988a). "Observed stress-strain behavior of confined concrete." J
694 Struct Eng., 114 (8): 1827-1849.

695 Mander, J. B., Priestley, M. J. N., Park, R. (1988b). "Theoretical stress-strain model for confined concrete." J
696 Struct Eng., 114 (8): 1804-1825.

697 Mangat, P. S., and Elgarf, M. S. (1999). "Flexural Strength of Concrete Beams with Corroding
698 Reinforcement." ACI Structural Journal., 96(1): 149-159.

699 McKenna, F. (2011). "OpenSees: a framework for earthquake engineering simulation." Computing in Science &
700 Engineering., 13(4): 58-66.

701 Meda, A., Mostosi, S., Rinaldi, Z., & Riva, P. (2014). Experimental evaluation of the corrosion influence on the
702 cyclic behaviour of RC columns. Engineering Structures., 76: 112–123.

703 Michel, A., Geiker, M. R., Stang, H., & Lepech, M. (2015). "Multi-Physics and Multi-Scale Deterioration
704 Modelling of Reinforced Concrete Part I: Coupling Transport and Corrosion At the Material Scale." In 2015
705 Symposium of the Federation Internationale du Beton (fib). Copenhagen, Denmark: fib.

706 Ni Choine, M., Kashani, M. M., Lowes, L. N., O'Connor, A., Crewe, A. J., Alexander, N. A., Padgett, J. E.
707 (2016). "Nonlinear dynamic analysis and seismic fragility assessment of a corrosion damaged integral bridge."
708 International Journal of Structural Integrity., 7 (2): 227-239.

709 Ou, Y., Chen, H. (2014). "Cyclic Behavior of Reinforced Concrete Beams with Corroded Transverse Steel
710 Reinforcement." Journal of Structural Engineering., 140(9): 04014050.

711 Ou, Y. C., Fan, H. D., Nguyen, N. D. (2013). "Long-term seismic performance of reinforced concrete bridges
712 under steel reinforcement corrosion due to chloride attack." Earthq Eng Struct D., 42 (14): 2113–2127.

713 Ou, Y., Tsai, L., Chen, H. (2011). "Cyclic performance of large-scale corroded reinforced concrete beams."
714 Earthquake Eng and Struct Dyn., 41(4): 592-603.

715 Palsson, R., Mirza, M. S. (2002). "Mechanical response of corroded steel reinforcement of abandoned concrete
716 bridge." ACI Struct J., 99 (2): 157–162.

717 Pantazopoulou, S. J., Bonacci, J. F., Sheikh, S. T., Thomas, M. D. A., Hearn, N. A. (2001). "Repair of corrosion-
718 damaged columns with FRP wraps." J compos constr., 5 (1): 3-11.

719 Papadopoulos, M. P., Apostolopoulos, C. A., Alexopoulos, N. D., Pantelakis, S. G. (2007). "Effect of salt spray
720 corrosion exposure on the mechanical performance of different technical class reinforcing steel bars." Mater Des.,
721 28 (8): 2318-2328.

722 Park, R., Priestley, N., Gill, W. (1982). "Ductility of square-confined concrete columns." J Struct Div., 108 (4):
 723 929-950.

724 Penelis, G., Kappos, A. (1997). "Earthquake resistance concrete structures." London: E & FN Spon.

725 Rao, A. S., Lepech, M. D., Kiremidjian, A. S., & Sun, X.-Y. (2016a). "Simplified structural deterioration model
 726 for reinforced concrete bridge piers under cyclic loading." Structure and Infrastructure Engineering., 13(1): 55–
 727 66.

728 Rao, A. S., Lepech, M. D., Kiremidjian, A. (2016b). "Development of time-dependent fragility functions for
 729 deteriorating reinforced concrete bridge piers." Structure and Infrastructure Engineering, 13(1): 67-83.

730 Razak, H. A., Choi, F. C. (2001). "The effect of corrosion on the natural frequency and modal damping of
 731 reinforced concrete beams." Eng Struct 23 (9): 1126-1133.

732 Rodriguez, J., Ortega, L. M., Casal, J., Diez, J. (1996). "Corrosion of reinforcement and service life of concrete
 733 structures." Sweden: Seventh International Conference on Durability of Building Materials and Components,
 734 E&FN Spon Publisher.

735 Rodriguez, J., Ortega, L. M., Aragoncillo, J., Izquierdo, D., Andrade, C. (2005). "Methodology for the structural
 736 assessment of concrete affected by reinforcement corrosion." ACI Struct J SP., 229: 305-318.

737 Rodriguez, J., Ortega, L. M., Casal, J. (1997). "Load carrying capacity of concrete structures with corroded
 738 reinforcement." Constr Build Mater., 11 (4): 239-248.f

739 Simon, J., Brac, J. M., Gardoni, P. (2010). "Seismic Response and Fragility of Deteriorated Reinforced Concrete
 740 Bridges." *Journal of Structural Engineering.*, 136(10): 1273–1281.

741 Spacone, E., Filippou, F. C., Taucer, F. F. (1996a). "Fibre beam-column model for non-linear analysis of R/C
 742 frames: part I: formulation." Earthq Eng Struct D., 25: 711-725.

743 Spacone, E., Filippou, F. C., Taucer, F. F. (1996b). "Fibre beam-column model for non-linear analysis of R/C
 744 frames: part II: applications." Earthq Eng Struct D., 25: 727-742.

745 Stewart M.G. (2004). "Spatial variability of pitting corrosion and its influence on structural fragility and
 746 reliability of RC beams in flexure." Structural Safety., 2004; 26(4): 453-470.

747 Suffern, Ch., El-Sayed, A., Soudki, Kh. (2010). "Shear strength of disturbed regions with corroded
 748 stirrups in reinforced concrete beams." Can. J. Civ. Eng. 37: 1045–1056.

749 Tastani, S. P., Pantazopoulou, S. J. (2004). "Experimental evaluation of FRP jackets in upgrading RC corroded
 750 columns with substandard detailing." Eng Struct., 26 (6): 817-829.

751 Taucer, F., Spacone, E., Filippou, F. C. (1991) . “A fiber beam-column element for seismic response analysis of
752 reinforced concrete structures.” Berkeley: EERC College of Engineering, University of California.

753 Torres-Acosta, A. A., Navarro-Gutierrez, S., Teran-Guill'en, J. (2006). “Residual flexure capacity of corrode
754 reinforced concrete beams.” *Engineering Structures.*, (29): 1145-1152.

755 Transportation Research Board. (1991). “Highway deicing: Comparing salt and calcium magnesium acetate,
756 special report 235.” Washington, DC: National Research Council.

757 Vidal, T., Castel, A., Francois, R. (2004). “Analysing crack width to predict corrosion in reinforced concrete.”
758 *Cement Concrete Res.*, 34(1): 165-174.

759 Vu, N. S., Yu, B., & Li, B. (2016). “Prediction of strength and drift capacity of corroded reinforced concrete
760 columns.” *Construction and Building Materials.*, 115, 304–318.

761 Vu, N. S., Yu, B., & Li, B. (2017). “Stress-strain model for confined concrete with corroded transverse
762 reinforcement.” *Engineering Structures* 151: 472–487.

763 Wallbank., E. J. (1989). “The performance of concrete in bridges: A survey of 200 highway bridges.” London:
764 H.M.S.O.

765 Wang, L., Zhang, X., Ma, Y., Liu, Y. (2015). “Effects of stirrup and inclined bar corrosion on shear behaviour
766 of RC beams.” *Construction and Building Materials.*, 98: 537–546.

767 Xia, J., Jin, W., Li, L. (2011). “Shear performance of reinforced concrete beams with corroded stirrups in
768 chloride environment.” *Corrosion Science.*, 53: 1794–1805.


769 Yang, Sh., Song, X., Jia, H., Chen, X., Liu, X. (2016). “Experimental research on hysteretic behaviors of
770 corroded reinforced concrete columns with different maximum amounts of corrosion of
771 rebar”. *Construction and Building Materials.*, 121: 319-327.

772 Ye, Z., Zhang, W., Gu, X. (2018). “Deterioration of shear behavior of corroded reinforced concrete beams”,
773 *Engineering Structures.*, 168: 708–720.


774 Yuan, Z., Fang, C., Parsaeimaram, M., Yang, S. (2017). “Cyclic Behavior of Corroded Reinforced Concrete
775 Bridge Piers”. *Journal of Bridge Engineering.*, 22(7):1-21.

776 Yu, L., Francois, R., Dang, V. H., L'Hostis, V., Gangne, R. (2015). “Structural performance of RC beams
777 damaged by natural corrosion under sustained loading in a chlorine environment.” *Engineering Structures.*, 96:
778 30-40.

- 779 Yoon, D. J., Weiss, W. and Shah, S. P. (2000). "Assessing Damage in Corroded Reinforced Concrete using
780 Acoustic Emission," J. Engineering Mechanics, ASCE, 126(3), 189-194.
- 781 Yuan, W., Guo, A., Yuan, W., Li, H. (2018). "Shaking table tests of coastal bridge piers with different levels of
782 corrosion damage caused by chloride penetration.", Construction and Building Material., 173: 160-171.
- 783 Zhang, R., Castel, A., Francois, R. (2009). "Serviceability Limit State criteria based on steel–concrete bond loss
784 for corroded reinforced concrete in chloride environment." Materials and Structures., 42: 1407-1421.
- 785 Zhu, W., and François, R., Coronelli, D., Cleland, D. (2013). "Effect of corrosion of reinforcement on the
786 mechanical behaviour of highly corroded RC beams." Engineering Structures., 56: 544–554.
- 787 Zhu, W., and François, R. (2015). "Structural performance of RC beams in relation with the corroded period in
788 chloride environment." Mater Struct., 47:1-13.
- 789 Zhu, W., and François, R. (2014). "Corrosion of the reinforcement and its influence on the residual
790 structural performance of a 26-year-old corroded RC beam." Construction and Building Materials., 51: 461–472.

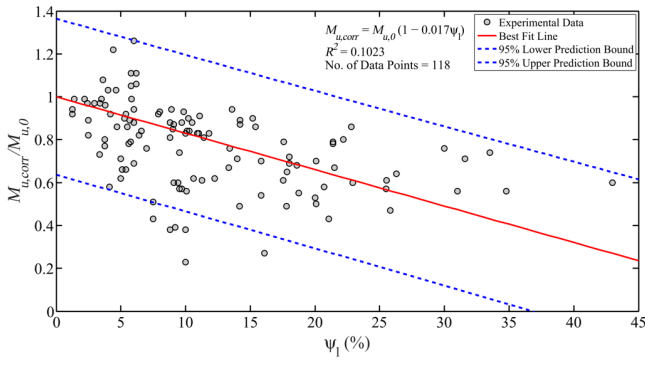


(a)

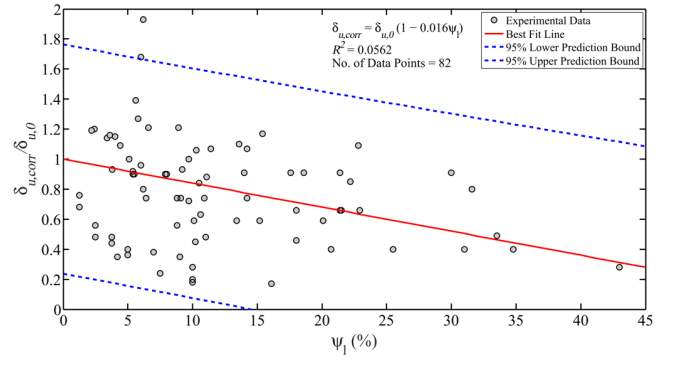


(b)

Fig. 1 Impact of corrosion on residual capacity of RC beams in flexure: (a) bending moment capacity, and (b) maximum deflection capacity

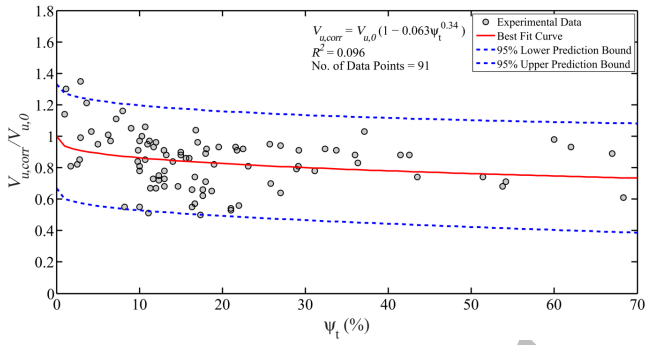


(a)

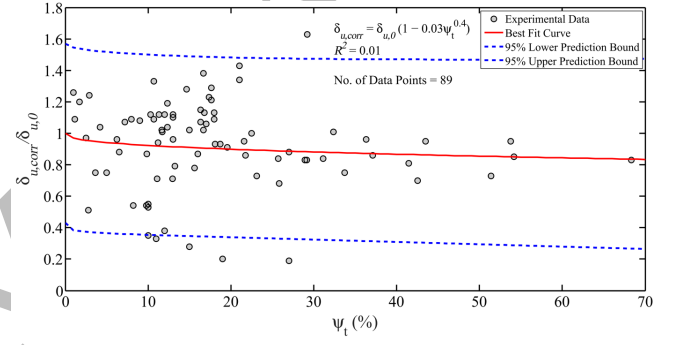


(b)

Fig. 2 Impact of corrosion on residual capacity of RC beams in shear: (a) shear capacity, and (b) maximum deflection capacity

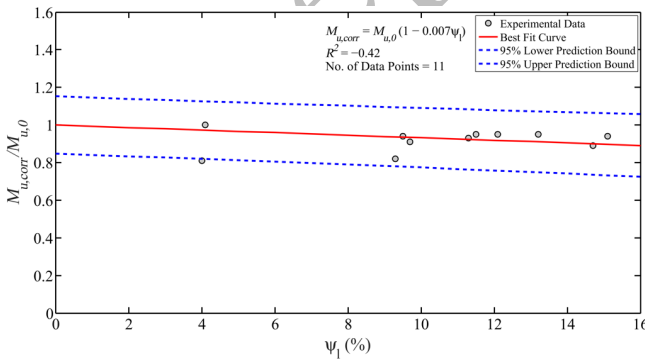


(a)

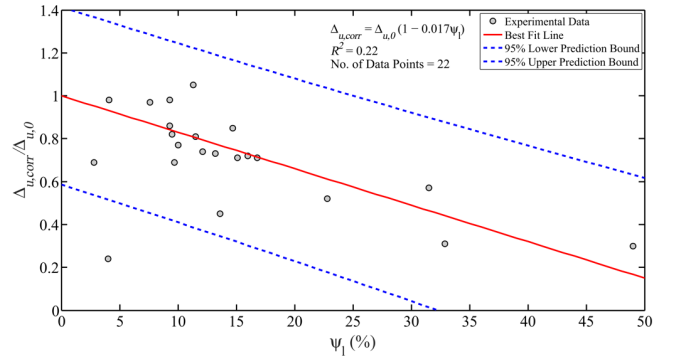


(b)

Fig. 3 Impact of corrosion on residual flexural capacity of circular RC columns: (a) ultimate bending moment capacity, and (b) maximum tip displacement capacity

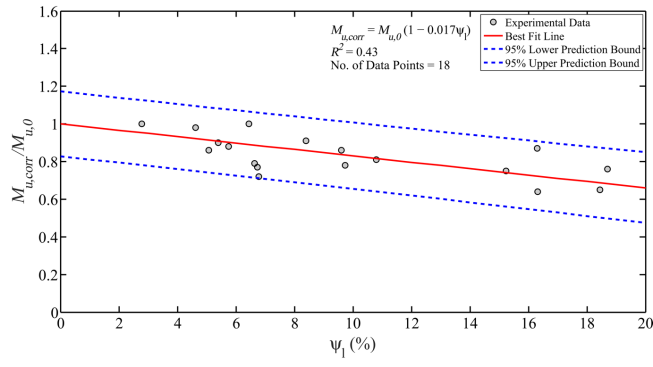


(a)

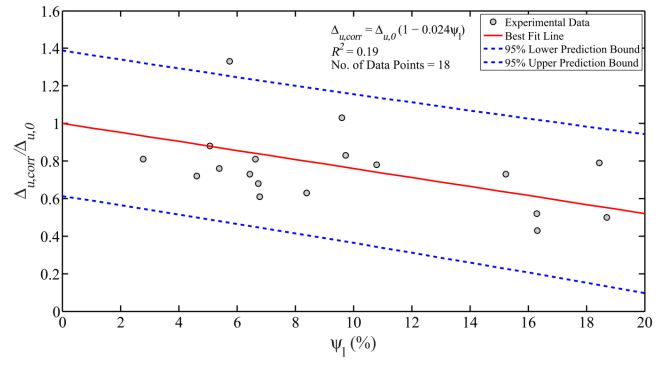


(b)

Fig. 4 Impact of corrosion on residual flexural capacity of rectangular RC columns: (a) ultimate bending moment capacity, and (b) maximum tip displacement capacity

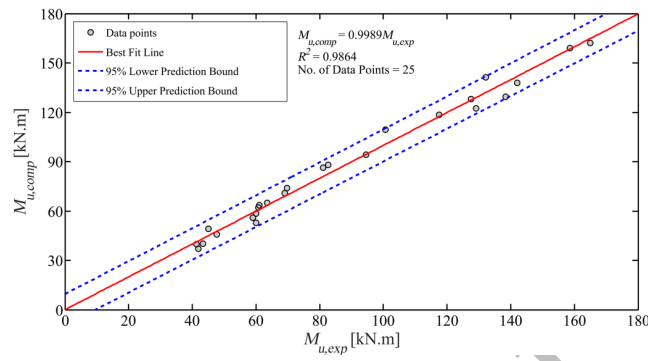

(a)

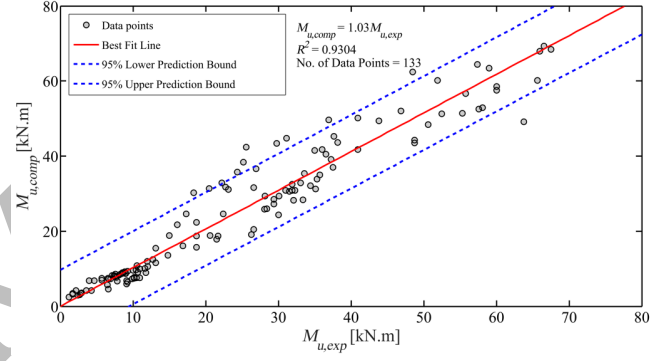

(b)

Fig. 5 Computational bending moment capacity of RC specimens versus corresponding experimental values: (a) rectangular columns and (b) flexural beams

Table 1. Summary of previous experimental studies on flexural behaviour of corrosion damaged RC beams

Reference	No. of Specimens	ψ_l (%)	Summary
Mangat & Elgarf (1999)	13	Up to 10%	The flexural strength of beams reduced with increasing levels of corrosion, primarily due to the breakdown of bond at the steel/concrete interface. Flexural strength reduced more for beams corroded by the higher rate of 4 mA.cm ⁻² than the beams corroded at 2mA.cm ⁻² . Deflection was not significantly affected by corrosion rate.
El Maaddawy et al. (2005b)	9	Up to 32%	The reduction of load-carrying capacity was almost proportional to the reduction in the steel cross-sectional area due to corrosion.
Torres-Acosta et al. (2006)	9	Up to 16%	Increased corrosion lead to a decrease in ultimate moment capacity and maximum midspan displacement. Cracks developed more rapidly in dry, rather than humid, environments.
Du et al. (2007)	18	Up to 14%	Corrosion caused over-reinforced beams to fail in a less brittle manner and under-reinforced beams to fail in a less ductile manner.
Azad et al. (2007)	28	Up to 31%	Increasing corrosion activity index, $I_{corr}T$, was the key measure of metal loss and flexural strength loss. Beams with low values of $I_{corr}T$ could still be predicted just by calculating cross-sectional area loss of the tensile reinforcement.
Cairns et al. (2008)	14	Up to 6%	Strength appeared to increase as corrosion increased. This is believed to be due to the increase in anchorage capacity.
Zhang et al. (2009) Castel et al. (2000)	3	Up to 18%	Deflection was found to be more sensitive to pitting attacks rather than the ultimate load due to the influence of the tension steel-concrete bond reduction. Ultimate load capacity decreased with increasing rebar mass loss.
Azad et al. (2010)	42	Up to 26%	For lower values of $I_{corr}T$ (mA.days.cm ⁻²), the residual flexural strength of beams was able to be predicted fairly accurately by considering only the area loss of the tension reinforcement.
Ou & Chen (2014)	7	Up to 35%	Beams were able to maintain a satisfactory ductile flexural behaviour with plastic rotation capacities larger than 3%, up to 6% mass loss.
Zhu & François (2015)	2	Up to 43%	Loss of one percent of the cross-section of the tensile bar corresponded to approximately one percent reduction in the yield capacity of the corroded beams.
Yu et al. (2015)	3	Up to 11%	The control beam failed by crushing of the compressive concrete followed by tensile rebar rupture, whereas corroded beams failed by cover spalling and failure of a tensile bar.
Al-Saidy et al. (2016)	6	Up to 7%	Corroded beams experienced similar moment capacity losses, however, beams without stirrups experienced much larger decreasing in mid-span displacement.

The detailed data is available in the online supplementary table provided with the paper.

Table 2. Summary of previous experimental studies on nonlinear behaviour of corrosion damaged RC beams in shear

Reference	No. of Specimens	ψ_t (%)	Summary
Rodriquez et al. (1997)	30	Up to 22%	Beams with different tensile and compressive reinforcement were tested. Some beams with only bottom reinforcement corrosion were tested. More highly corroded beams failed by shear or loss of bond compared to low corrosion beams which failed via ductile means such as bending.
Higgins & Farrow III (2006)	8	Up to 34%	Maximum shear decreases with increasing stirrup spacing and rebar mass loss, as does maximum displacement. More localised concrete cover damage for wider spaced stirrups.
Suffern et al. (2010)	12	Up to 19%	Shear strength decreased with increasing corrosion. Increased corrosion leads to large crack widths. Shear strength reduced for beams with smaller span-to-depth ratios.
Xia et al. (2011)	18	Up to 54%	Average and maximum crack widths can be used as an indicator of how much corrosion the beams have experienced. The mode of failure changed from concrete crushing to stirrup failure with increasing corrosion.
Alaskar (2013)	12	Up to 16%	Shear strength was shown to decrease with increasing corrosion except for smooth stirrups with corrosion levels below 8%.
Zhu et al. (2013)	4	Up to 67%	Loss of one percent of the cross-section of the tensile bar corresponded to approximately one percent reduction in the yield capacity of the corroded beams.
Khan et al. (2014)	3	Up to 51%	The mechanical behaviour of deep beams was studied. The corrosion was natural. Corrosion was found to have no effect on the failure mechanism of these deep beams.
Wang (2015)	14	Up to 68%	Corrosion of less than 10% was found to do not have a significant effect on the deterioration of shear strength. Corrosion was not found to effect failure mode but did reduce the number of cracks at failure and encourage early stirrup rupture.
El-Sayed et al. (2016)	9	Up to 18%	Three tests with variable stirrup spacing, 100mm, 150mm, and 200mm. Three beams per test were set up with corrosion levels approximately 0%, 10%, and 20%. Shear compression was more common in low corroded specimens whereas stirrup rupture more common in high.
Ye et al. (2018)	13	Up to 27%	Increased corrosion lead to rapid decrease in shear strength and ductility. Failure mode shifted from bending to shear with increasing corrosion.

The detailed data is available in the online downloadable supplementary file (Exp data.xlsx) provided with the paper.

856

Table 3. Summary of experimental researches on corrosion damaged columns under pure compression loading

Reference	No. of Specimens	ψ_t (%)	Summary
Bae et al. (2005)	3	Up to 49%	Circular columns were tested. Axial strain reduced with increasing corrosion. Compression strength wasn't affected until very high corrosion levels occurred.
Vu et al. (2017)	24	Up to 25%	Square columns were tested. As the corrosion level increased, both ductility and strength of the corroded confined concrete severely decrease.
Vu et al. (2017)	12	Up to 33%	Circular columns were tested. Similar volumetric ratios of transverse reinforcement and corrosion levels gave rise to comparable results, regardless of the columns shape.

857 The detailed data is available in the online downloadable supplementary file (Exp data.xlsx) provided with the paper.

858

Table 4. Summary of experimental studies on flexural behaviour of circular corroded RC columns

Reference	No. of Specimens	ψ_t (%)	Summary
Aquino & Hawkins (2007)	2	Up to 4%	A corrosion level of 4% resulted in a 76% reduction in maximum displacement, as well as a 19% reduction in flexural strength. The axial load was zero.
Ma et al. (2011)	13	Up to 15%	Higher axial loads lead to more brittle failures. Larger corrosion levels and axial force resulted in worse seismic behaviour, stiffness, ductility, and energy dissipation.

860 The detailed data is available in the online downloadable supplementary file (Exp data.xlsx) provided with the paper.

861

862

Table 5. Summary of experimental researches on flexural behaviour of corrosion damaged rectangular RC columns

Reference	No. of Specimens	Summary
Lee et al. (2003)	4	Increased corrosion leads to a decline in strength and deformability due to the loss in rebar cross-sectional area, loss of bond between the steel and concrete, and decline in restraining effect due to the spalling of concrete cover.
Li et al. (2009)	4	Corrosion reduced flexural strength, more so for the higher axial loads. Ductility and displacement showed no strong trend for the four specimens.
Meda et al. (2014)	2	Corrosion resulted in a large decrease in ductility and flexural strength, as well as a decrease in M_y/M_u .
Guo et al. (2015b)	4	Higher corrosion levels lead to worse seismic behaviour, poorer strength and stiffness, decreased ductility and displacement, and lower energy dissipation capacity.
Yang et al. (2016)	5	Columns with equal axial force and increasing corrosion were tested. Increased corrosion resulted in decreased flexural strength, deflection, and ductility. Flexural strength was not affected much until the maximum corrosion reached 10%.
Li et al. (2018)	6	Flexural strength, ductility, and maximum displacement decreased with increasing corrosion. Flexural strength and displacement were affected more with a larger axial force, whereas, the opposite occurred for ductility.

865 The detailed data is available in the online downloadable supplementary file (Exp data.xlsx) provided with the paper.