

Design, imaging and performance of 3D printed open-cell architectures for porous electrodes: quantification of surface area and permeability

Nazira Kaishubayeva,¹ Carlos Ponce de León,¹ Frank C Walsh¹ and Luis F Arenas^{2*,+}



Abstract

BACKGROUND: The development of new open-cell porous electrodes for electrochemical flow cells and reactors is demonstrated through the application of 3D printing. The properties of diverse architectures were investigated, including rectangular, circular, hexagonal and triangular cells with linear porosity grades of 10, 20 and 30 pores per inch (ppi). Specimens were digitally designed, then 3D printed in stainless steel via selective laser melting. After being examined using scanning electron microscopy, they were characterized in terms of volumetric surface area and porosity with the aid of X-ray computed tomography. Pressure drop measurements were performed over a range of mean linear velocity and Reynolds number, allowing the estimation of Darcy's friction factor and permeability.

RESULTS: Volumetric surface area estimated from tomography scans was $\leq 36\%$ higher than the nominal values owing to surface roughness and post-processing algorithms. By contrast, volumetric porosity obtained by tomography agreed fully with measured values. Triangular architectures afforded additional surface area both digitally and according to tomography. The largest pressure drop was found in circular materials, the triangular ones showing the lowest. The 20 ppi triangular architecture had a volumetric surface area of $\approx 44.5 \text{ cm}^{-1}$ and a permeability of $2.31 \times 10^{-5} \text{ cm}^2$.

CONCLUSION: Triangular architectures were preferred as a consequence of their favourable combination of high surface area and high permeability with low mass and reduced digital complexity. This provides a strategy to initiate the optimization of 3D printed porous electrodes for electrochemical flow cells and reactors in novel and niche applications.

© 2021 The Authors. *Journal of Chemical Technology and Biotechnology* published by John Wiley & Sons Ltd on behalf of Society of Chemical Industry (SCI).

Supporting information may be found in the online version of this article.

Keywords: additive manufacturing; electrode design; periodic cell; X-ray computed tomography

INTRODUCTION

Interest in innovative 3D printed electrochemical devices continues to grow.^{1,2} One of the most important and promising applications is the development of tailored electrochemical flow reactors with enhanced efficiency for electrochemical processing and energy storage and conversion.^{3,4} 3D printing already offers the possibility of manufacturing fast prototypes⁵ and working models of electrochemical flow reactors⁶ and electrolysers,⁷ enabling their design through a recently proposed cycle of conceptualization, simulation, rapid prototyping and experimental validation.^{8,9} However, it also is important to adequately assess the characteristics of electrodes produced by 3D printing in order to predict their performance realistically and to enable the design of improved electrochemical reactors.

A growing number of 3D printed architectures are based on periodic cellular materials for use as porous electrodes in electrochemical technologies.^{10,11} Such electrodes increase the productivity of electrochemical reactors by providing extended active

* Correspondence to: LF Arenas, Electrochemical Engineering Laboratory, Faculty of Engineering and the Environment, University of Southampton, Southampton, SO17 1BJ, UK. E-mail: lfam1c17@soton.ac.uk

+ Society of Chemical Industry active member.

¹ Current address: Nur-Sultan, Kazakhstan

² Current address: Saltillo, Mexico

Electrochemical Engineering Laboratory, Faculty of Engineering and the Environment, University of Southampton, Southampton, SO17 1BJ, UK

surface area and enhancing mass transfer of reactants compared to planar electrodes.¹² Ideally, porous electrode materials should have good electrical conductivity, high volumetric surface area and high hydraulic permeability,¹³ leading to more efficient, compact reactors. The electrode structure can then be modified using a wide diversity of catalysts and hierarchical structures, adding functionality and selectivity.^{14,15} 3D printing can provide control over pore size and shape, distance between pores, volumetric porosity and surface area of the porous structures within the manufacturing resolution. Such advances could find novel or niche applications for 3D printed electrodes in water treatment,^{16,17} electrosynthesis,^{18,19} environmental remediation^{20,21} and energy storage.^{22,23}

In the case of 3D printed metallic electrodes,¹⁵ the technique chosen in this contribution creates tailored architectures via layer-by-layer deposition of a precursor powder through selective laser melting (SLM).²⁴ Compared to other laser-based techniques, SLM results in better surface morphology, homogeneity and mechanical properties. It permits the production of components not only in ferrous alloys, but also in titanium (Ti), aluminium (Al) and copper (Cu).²⁴ The potential for this concept in electrochemical flow cells has been demonstrated by 3D printed stainless steel electrodes coated with nickel (Ni)³ and molybdenum disulfide (MoS₂),⁷ and by 3D printed titanium electrodes coated with TiO₂²⁵ and platinum (Pt).²⁶ SLM also has been applied to produce helical electrodes,²⁷ moulds for sintered electrodes²⁸ as well as static cells for sensors²⁹ and O₂ evolution.³⁰

The analysis of 3D printed porous electrodes can be carried out by X-ray computed tomography (CT) in order to estimate or validate their volumetric porosity, solid volume, physical surface area and derived parameters.³¹ These characteristics are essential to assess their performance and for the calculation or simulation of their hydrodynamic, ohmic and kinetic behaviour.³² The physical surface area of these materials and its comparison to active electrochemical surface area is particularly important in electrochemical studies.^{33,34} Examples involving conventional porous electrodes by CT include the tortuosity of carbon (C) felt,³⁵ the surface area of reticulated vitreous carbon (RVC)³¹ and the distribution of metal deposits such as Cu and cadmium (Cd)³⁶ or Pt.^{37,38} Related examples of the analysis of inert porous materials by CT include the determination of pore diameter distribution in SiC-Al₂O₃ foams³⁹ and the study of porosity and tortuosity in SiC foams.⁴⁰ Similar structural and parametrical analysis would certainly be of interest in nonelectrochemical 3D printed flow reactors, such as those recently proposed for the enhancement of heterogeneous reactions and separation processes.⁴¹

Following the characterization of the material, the performance of a porous electrode in an electrochemical flow reactor can be quantified by the volumetric mass transfer coefficient, $k_m A_e$, and its relationship to the pressure drop, ΔP , which is caused by frictional losses as the electrolyte flows through the porous structure.^{3,42,43} $k_m A_e$ is strongly related to the limiting current density and the minimization of overpotentials;¹² ΔP depends on the permeability of the material which affects pumping energy demand and energy efficiency.⁴⁴ A low pressure drop also facilitates the assembly and operation of leak-free reactors. Electrodes with high volumetric surface area and high permeability are required for an energy-efficient electrochemical process. A comparative study of porous electrode architectures can be initiated by seeking such characteristics, before progressing to electrochemical aspects.

After introducing 3D printed porous electrodes for electrochemical flow reactors³ and applying CT to the analysis of the surface area of porous electrodes,³¹ we now turn our attention to the development of diverse 3D printed porous architectures for use in electrochemical flow reactors. This approach is an example of a 'virtuous cycle' in which a rational development for porous electrodes, based on the digital design of tailored structures, is followed by their manufacture, subsequent imaging and analysis of their physical properties before their performance is evaluated (see Fig. 1).^{8,9} Previously, attention has been focused on the achievement of smaller pore sizes or on the increase of mass transfer, neglecting the parameters of surface area (which is directly linked to the electrochemical performance) and hydraulic permeability (which is of utmost importance in a practical flow device). The novelty of the present work lies in the methodology for selecting a 3D printed electrode architecture. We have aimed for maximum surface area and high hydrodynamic permeability, an important step towards the development of advanced electrode materials. Work in progress will utilize the results of this study in the assessment of the electrochemical performance and application of the novel 3D printed electrodes under mass transfer-controlled conditions.

THEORETICAL CONSIDERATIONS

Surface area

The volumetric surface area, A_e , is an important property of a porous electrode material and is the ratio of its total surface area, A , to its volume V_R (in a specimen or inside an electrochemical reactor):

$$A_e = \frac{A}{V_R} \quad (1)$$

A_e can then be used to rationalize the performance factor $k_m A_e$ via the estimation of a limiting current, I_L , or mass transfer coefficient, k_m , during electrochemical characterization of the material.^{34,45,46}

The electrode area per unit solid volume, A_{sv} , is related to A_e and the volumetric porosity of the material, ϵ :⁴⁷

$$A_{sv} = \frac{A_e}{(1-\epsilon)} \quad (2)$$

A_{sv} also can be determined using the Ergun equation in the case of materials with relatively small pore sizes,^{39,48} facilitating comparison with other porous electrodes. The value of A_{sv} is particularly useful as an indicator of how well a porous body can maximize its surface area. A similar parameter is the specific surface area, which relates surface area and mass of material.

Pressure drop

Regarding pressure drop through the porous electrodes, a normalization is useful, in terms of the fluid flow regime, to enable comparisons. A simple approach can consider the mean linear velocity of the fluid, v as it passes through the porous material. It is given by the expression⁴⁹:

$$v = \frac{Q}{\epsilon A_x} \quad (3)$$

where Q is volumetric flow rate and A_x is the cross-sectional area of the porous material.

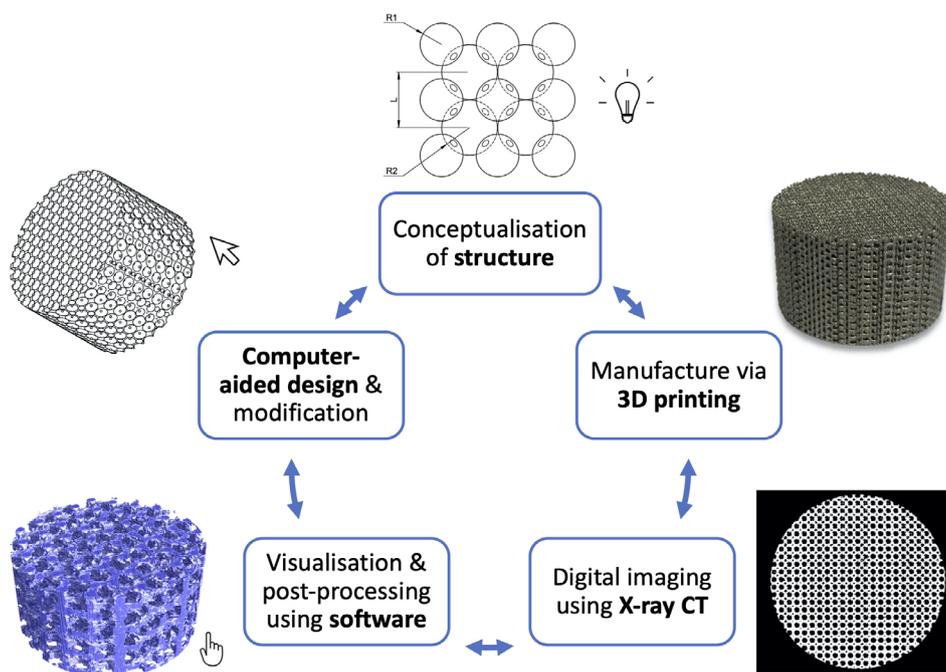


Figure 1. 'Virtuous cycle' for an iterative process involving digital design, manufacture and imaging during the development and production of 3D printed porous electrode architectures for electrochemical flow reactors and other electrochemical devices.^{8,9}

Classically, a dimensionless Reynolds number, Re , considering the hydraulic diameter of the flow channel/tube, d , as characteristic length can be used to define the fluid flow within the porous material in terms of the properties of the fluid:

$$Re = \frac{\rho v d}{\mu} \quad (4)$$

where ρ is density and μ is dynamic viscosity. The experimental value of ΔP can be conveniently fitted to an empirical power law involving Re ⁵⁰:

$$\Delta P = e Re^h \quad (5)$$

where e and h are empirical constants; their values define this relationship, which is specific to each porous material.

ΔP can be used to calculate Darcy's friction factor, f_D , as an indicator of the intensity of frictional losses. This friction factor can be plotted as a function of v or Re allowing a comparison of different porous media:

$$f_D = \frac{2\Delta P d}{L \rho v^2} \quad (6)$$

where L is the length of the porous material experiencing the flow. f_D has been employed previously to characterize rough electrodes,⁵¹ mesh spacers^{52,53} and porous electrodes.^{42,54}

Likewise, Darcy's permeability, K_D can be used to characterize the influence of electrode geometry on the fluid flow.⁵⁵ From Darcy's law, this property defines how fast fluid passes through a volume of porous material per unit of differential pressure and is an indicator of how well the pores are interconnected.⁴⁸ It is calculated from the expression:

$$K_D = \frac{v \mu L}{\Delta P} \quad (7)$$

K_D has been used to describe the suitability of electrode materials in electrochemical reactors,⁵⁶ for instance in redox flow batteries.^{54,57} K_D also is important in the study of hydraulic properties of 3D printed replicas of open cell foams.⁵⁸

EXPERIMENTAL

Design of the porous materials

Nine porous electrode architectures were designed using SOLIDWORKS CAD suite (Dassault Systèmes SA, Vélizy-Villacoublay, France). The open-cells were designed in four geometrical shapes: rectangular, circular, hexagonal and triangular. Drawings for each architecture are found in the Supporting Information; Figs S1–S4. The distances between the two closest edges of neighbouring pores were selected so as to form 10 ppi (linear pores per inch), 20 ppi and 30 ppi structures, whose porosities were limited by computer processing power; the finer the structure, the longer time to manipulate a model. Figure 2 presents CAD examples of each geometrical shape for the 10 ppi porosity grade only, for clarity. Cross-sectional views are found in Fig. S5. All of the architectures were envisaged and printed as cylindrical specimens with diameter 30 mm and height 20 mm. The nine different electrode architectures can be seen in Fig. 3. The arrangement of the pores was such that they formed rectilinear grids in the horizontal direction which were staggered in the vertical direction. The characteristic lengths of the void, interconnected cells ranged from 0.7 mm to 2.6 mm. Table 1 provides a list of their nominal characteristic lengths, linear and volumetric porosities and surface areas according to the CAD program.

3D printing of porous materials

The complex porous geometries, which would have been very problematic to manufacture using traditional machining methods, were printed layer-by-layer using a M2 Cusing (ConceptLaser GmbH, Lichtenfels, Germany) SLM metal printer with maximum resolution 20 μm and power 200 W under a N_2

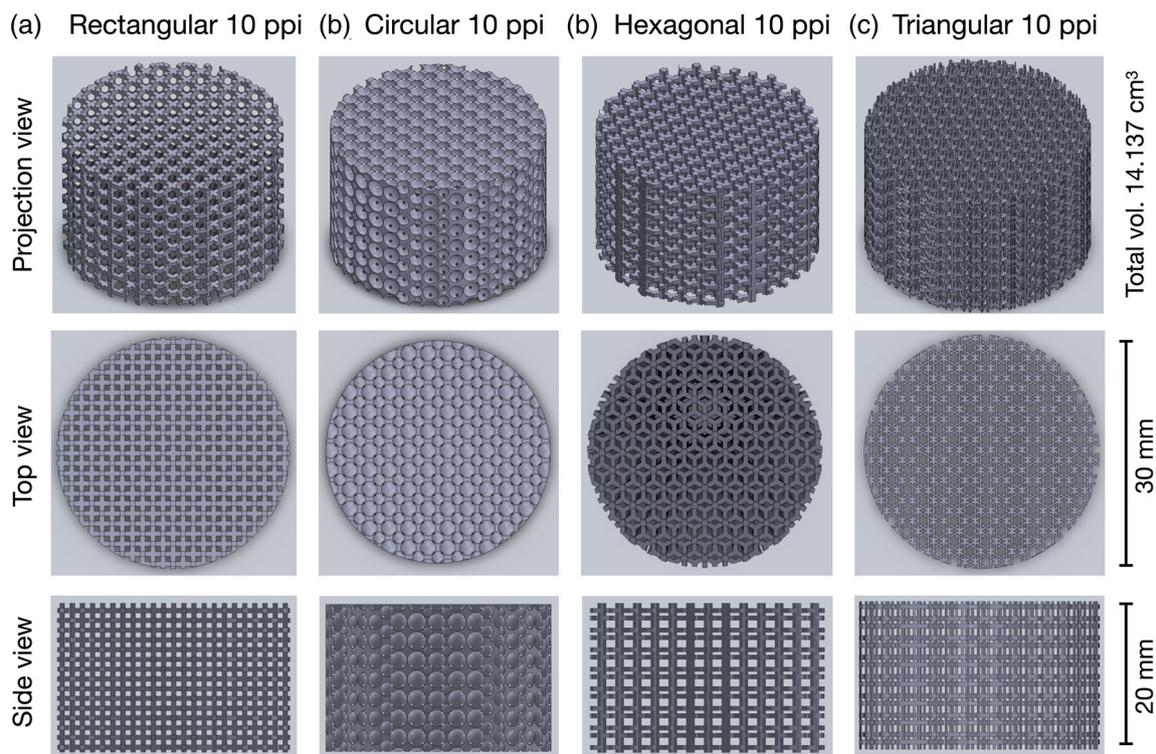


Figure 2. Isometric, top and side views of CAD-designed porous electrode architectures. For clarity, only the 10 ppi porosity grade of each pore shape is shown here.

gas environment. The precursor powder was a 316 L (CL20 ES) austenitic stainless-steel (Fe base containing 17.5% Cr, 11.5% Ni, 2.3% Mo) with particle sizes between 20 and 40 μm in diameter. The 3D printed electrode materials are shown in Fig. S6(a). The mass, diameter and height of the specimens were measured in order to determine their volumetric porosity, ε , and compare it with CAD values. Assuming that the internal microporosity of the material was negligible, ε was calculated from the expression:

$$\varepsilon = \frac{V_{\text{bulk}} - V_{\text{solid}}}{V_{\text{bulk}}} \quad (8)$$

where V_{bulk} is the bulk volume of the specimen and V_{solid} is the volume of the metal. These values were calculated using the following equations:

$$V_{\text{bulk}} = \frac{\pi D^2 H}{4} \quad (9)$$

$$V_{\text{solid}} = \frac{m}{\rho} \quad (10)$$

where D and H are the measured diameter and height of the specimen, respectively, m is the mass of the material and ρ is the density of stainless steel (7.98 g cm^{-3} for austenitic grade 316 L material).⁵⁹ Mass was measured in an analytical balance (Mettler-Toledo Inc., Columbus, OH, USA) to an accuracy of $\pm 1 \text{ mg}$. Dimensions of the 3D printed samples were taken with a digital calliper (Mitutoyo Corp., Kawasaki, Japan).

SEM and CT imaging

Scanning electron microscopy (SEM) images of the 3D printed specimens were obtained at 15 kV using a JSM-6500F field

emission electron microscope (Jeol Inc., Tokyo, USA). X-ray CT scans were performed in a modified Nikon/Xtek HMX equipment (Nikon Corp., Tokyo, Japan) under 195 kV peak voltage and 115 μA current. A CT rendering was constructed from 3401 projections with two frames per projection, each frame taking 708 ms. Shutting was enabled and a filtration of 1 mm Cu was used. The resulting isotropic resolution was 0.0187 mm per voxel. The scan time for each specimen was $\approx 2.5 \text{ h}$. Raw images were processed and analyzed using VG STUDIO MAX v.2.1 (Volume Graphics GmbH, Heidelberg, Germany). Volume and surface area were established using the 'ISO50%' threshold condition.

Pressure drop measurements

Pressure drop measurements were carried out with distilled water in a tubular, circular section flow cell with internal and external diameters of 30 mm and 40 mm, respectively. The clear acrylic polymer flow cell consisted of two threaded tube segments [see Fig. S6(b)]. The entry segment had a length of 30.0 cm, which is ten-fold larger than the internal diameter, to achieve a fully developed flow in the test section.⁶⁰ The outlet segment had a length of 10.0 cm and part of it had a wider internal diameter (3.02 cm) to hold the electrode samples. In order to prevent any bypassing of flow, waterproof adhesive tape was placed between the samples and the tube by compression [see Fig. S6(c)]. Pressure drop was measured with a HT-1890 digital manometer (HTI-Instrument, Guangdong, China) at pressure taps drilled in the flow cell as close to the porous material as the arrangement allowed, using two polypropylene tubes (2 mm internal diameter) sealed with epoxy resin [see Fig. S6(d)]. During the experiments, the flow cell was mounted horizontally, having first removed air bubbles

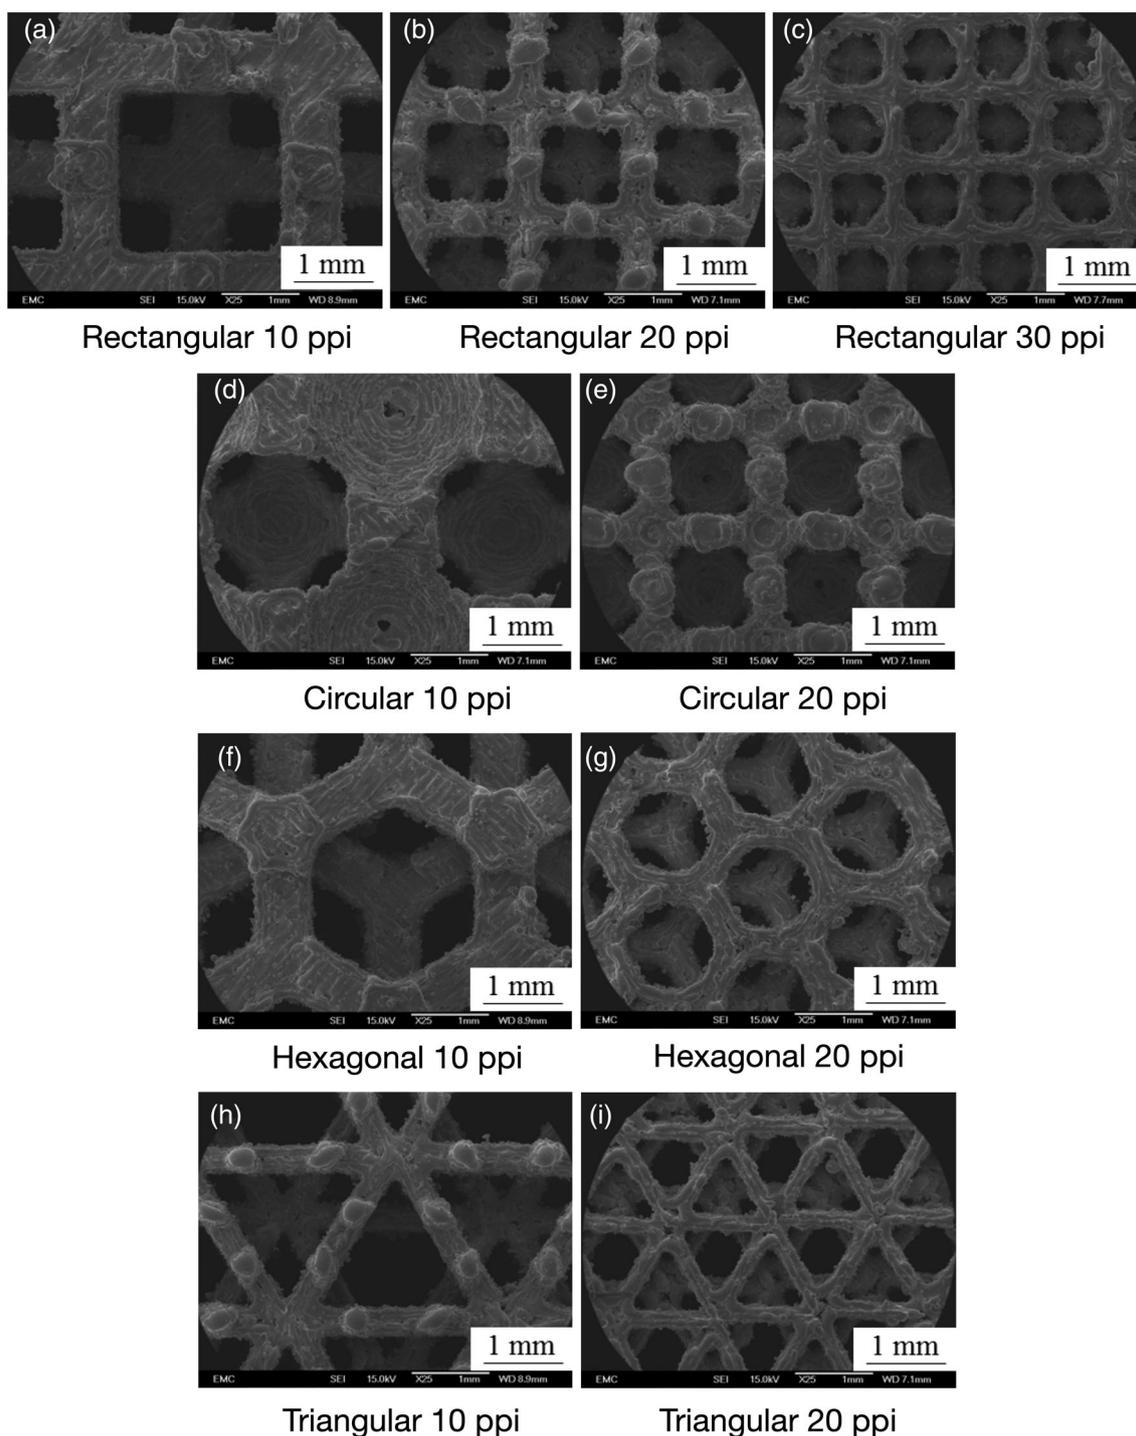


Figure 3. SEM images of 3D printed specimens of the different porous electrode architectures. Magnification $\times 25$.

from it in the vertical position. Three sets of measurements at different volumetric flow rates were taken for each material and an average value was reported. Fluid (water) density 1 g cm^{-3} and dynamic viscosity $8.9 \times 10^{-4} \text{ Pa s}$ at $25 \text{ }^\circ\text{C}$ were used in Reynolds number calculations. The flow cell was connected to a NEMP50/7 magnetically coupled centrifugal pump (Totton Pumps, Flojet, Kendal, UK) through polypropylene tubing, providing volumetric flow rates $\leq 440 \text{ L h}^{-1}$. The temperature was maintained at $25 \pm 1 \text{ }^\circ\text{C}$ using a thermostatic water bath (Grant Instruments Ltd, Royston, UK).

RESULTS AND DISCUSSION

SEM and CT characterization

Figure 3 shows SEM images of the top faces of the 3D printed porous architectures. Layers of stainless steel powder melted by laser and fused during SLM are clearly visible. As expected, some distortion and surface roughness are found in the structure as a consequence of the manufacture method, especially with decreasing pore size. Nodules $< 0.1 \text{ mm}$ in size protrude from the sides and small pores can be observed at the junction of struts. Such deviations result in slightly different volume and

Table 1. Nominal dimensions, volumetric porosity, surface area and linear porosity grade of the porous architectures, according to the CAD suite

Electrode material	Primary pore size (mm)	Secondary pore size (mm)	Distance between pores in 3D (mm)			Solid volume (cm ³)	Void volume (cm ³)	Surface area, A (cm ²)	Volumetric porosity (ϵ)	Porosity grade (ppi)
			x	y	z					
Rectangular 10 ppi	2.00	2.00	0.62	0.62	0.62	3.58	10.56	201.59	0.75	10.00
Rectangular 20 ppi	1.00	1.00	0.31	0.31	0.31	3.58	10.56	403.11	0.75	19.99
Rectangular 30 ppi	0.70	0.70	0.17	0.17	0.17	2.51	11.63	541.98	0.82	30.08
Circular 10 ppi	2.00	2.60	0.62	0.62	0.62	3.62	10.52	261.09	0.74	10.00
Circular 20 ppi	1.00	1.30	0.31	0.31	0.31	3.59	10.55	512.03	0.75	19.99
Hexagonal 10 ppi	2.00	2.00	0.62	0.62	0.62	3.58	10.56	200.53	0.75	10.00
Hexagonal 20 ppi	1.00	1.00	0.31	0.31	0.31	3.61	10.53	403.04	0.74	19.99
Triangular 10 ppi	2.00	2.00	0.62	0.62	0.62	2.92	11.22	313.98	0.79	10.00
Triangular 20 ppi	1.00	1.00	0.31	0.31	0.31	2.97	11.17	628.96	0.79	19.99

Digital objects are cylinders of 30 mm diameter and 20 mm height.

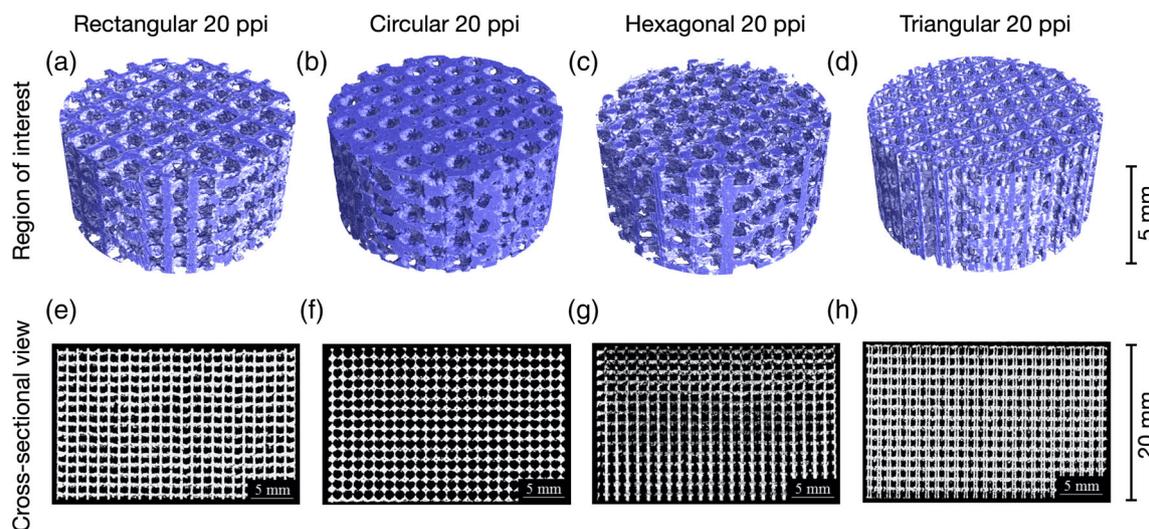


Figure 4. CT images of 3D printed specimens of the porous electrode architectures. For clarity, only the 20 ppi porosity grade of each pore shape is shown here. (a), (c), (e) and (g) 3D regions of interest (ROI) with diameter 10 mm and height 5 mm within the full specimens. (b), (d), (f) and (h) Cross-sectional views of the full specimens (30 mm diameter, 20 mm height).

surface area from the designed geometrical shapes. A larger surface area can be expected to increase the electrochemical performance whereas surface roughness can enhance mixing and mass transfer, albeit by promoting frictional losses in the fluid.

The CT scans obtained for selected porous structures also depict the structure. As an example, Fig. 4(a), (b), (c) and (d) depicts the volume occupied by 3D printed specimens (20 ppi grade) according to the 'ISO50%' thresholding standard within cylindrical regions of interest (ROI) of 10 mm diameter and 5 mm height. Several properties were determined from post-processing these scans, *vide infra*. CT also provided cross-sectional cuts of the

specimens, allowing us to observe the quality of the internal scaffold of the specimens. As shown in Fig. 4(e), (f), (g) and (h), cross-sectional CT images indicate that the manufacture technique can produce distortions in the regularity of the structure. This is attributable to the tolerances in the laser movement relative to the position of the specimen, temperature changes and interruptions during the process. Figure 4(g) also shows in particular that horizontal components of the pores bent downwards as layers of molten metal powder were applied. This effect is less evident in the samples with smaller pore sizes. Because uniform pore distribution was proven to increase efficiency in porous electrodes under

Table 2. Measured dimensions and mass of 3D printed specimens of the porous architectures along a comparison of the calculated and CT-determined porosity and surface area versus nominal CAD values

Electrode material	Mass (g)	Diameter (mm)	Height (mm)	Volumetric porosity (ϵ)					Surface area, A (cm ²)		
				CAD	CT	Mass	CT versus CAD % difference	Mass versus CAD % difference	CAD	CT	CT versus CAD % difference
Rectangular 10 ppi	33.75	29.97	20.00	0.75	—	0.70	—	−6.7	201.59	—	—
Rectangular 20 ppi	37.46	30.24	19.61	0.75	0.64	0.67	−14.7	−10.7	403.11	541.31	+34.3
Rectangular 30 ppi	49.06	30.16	19.95	0.82	0.55	0.57	−32.9	−30.5	541.98	851.87	+57.2
Circular 10 ppi	34.27	30.06	19.62	0.74	—	0.69	—	−6.8	261.09	—	—
Circular 20 ppi	47.80	30.04	19.83	0.75	0.57	0.57	−24.0	−24.0	512.03	566.49	+10.6
Hexagonal 10 ppi	34.15	30.10	20.14	0.75	—	0.70	—	−6.7	200.53	—	—
Hexagonal 20 ppi	39.54	30.41	19.96	0.74	0.65	0.66	−12.2	−10.8	403.04	539.65	+33.9
Triangular 10 ppi	26.82	30.09	19.54	0.79	0.74	0.76	−6.3	−3.8	313.98	366.82	+16.8
Triangular 20 ppi	38.61	30.03	19.69	0.79	0.64	0.65	−19.0	−17.7	628.96	727.92	+15.7

Table 3. Calculated volumetric surface area and surface area per unit solid volume of 3D printed specimens of the porous electrode architectures from CT scans versus nominal CAD values

Electrode material	Volumetric surface area, A_v (cm ^{−1})			Surface area per unit solid volume, A_{sv} (cm ^{−1})		
	CAD	CT	CT versus CAD, % difference	CAD	CT	CT versus CAD, % difference
Rectangular 10 ppi	14.26	—	—	57.04	—	—
Rectangular 20 ppi	28.51	38.43	+34.7	114.06	106.67	−6.5
Rectangular 30 ppi	38.34	59.77	+56.0	212.98	132.89	−37.6
Circular 10 ppi	18.47	—	—	71.03	—	—
Circular 20 ppi	36.22	40.31	+11.3	144.87	93.72	−35.3
Hexagonal 10 ppi	14.18	—	—	56.74	—	—
Hexagonal 20 ppi	28.51	37.22	+30.5	109.65	106.29	−3.1
Triangular 10 ppi	22.21	26.40	+18.9	105.76	101.54	−4.0
Triangular 20 ppi	44.49	52.20	+17.3	211.86	145.00	−31.6

possible mass transfer limitations,⁶¹ further control of the porous structure may be achieved by using a higher resolution, slower speed or more rigid support during printing.

Table 2 shows the measured mass, diameter and height of the 3D printed porous materials. The diameter and height of the specimens deviated by $\leq 2.3\%$ from the designed values. The actual volumetric porosity of the specimens, given reliably by their mass and density, was lower than that of the digital designs. For 10 ppi grade materials, the difference was $\approx 5\%$, whereas for 20 ppi and 30 ppi grade materials it rose to 20% and 30%, respectively. This is the result of the manufacturing tolerances imposed by the SLM technique. However, the porosity values determined from CT scans (see Table 2) are close to the ones calculated from direct mass measurements, with a maximum error of 3%. This implies that CT-determined porosity values are reasonably accurate for

these materials, as opposed to their nominal CAD dimensions. Indeed, in previous work on the study of RVC by CT,^{31,62} it was found that this technique was useful in determining properties derived from a 3D volume (such as porosity), whereas those derived from 2D surfaces required *ad hoc* image post-processing and calibration in order to achieve sufficient accuracy.

The estimation of the surface area of 3D printed porous materials from CT scans was also explored. As seen in Table 2, the CT values are higher than the nominal CAD values owing to the roughness of the manufactured samples. In the case of the rectangular pores, the difference in the surface area increases along linear porosity grade but the opposite is true in the case of the samples with triangular pores. Given the limited number of specimens, a clear trend cannot be established in relation to surface area versus porosity at this point. However, it can be

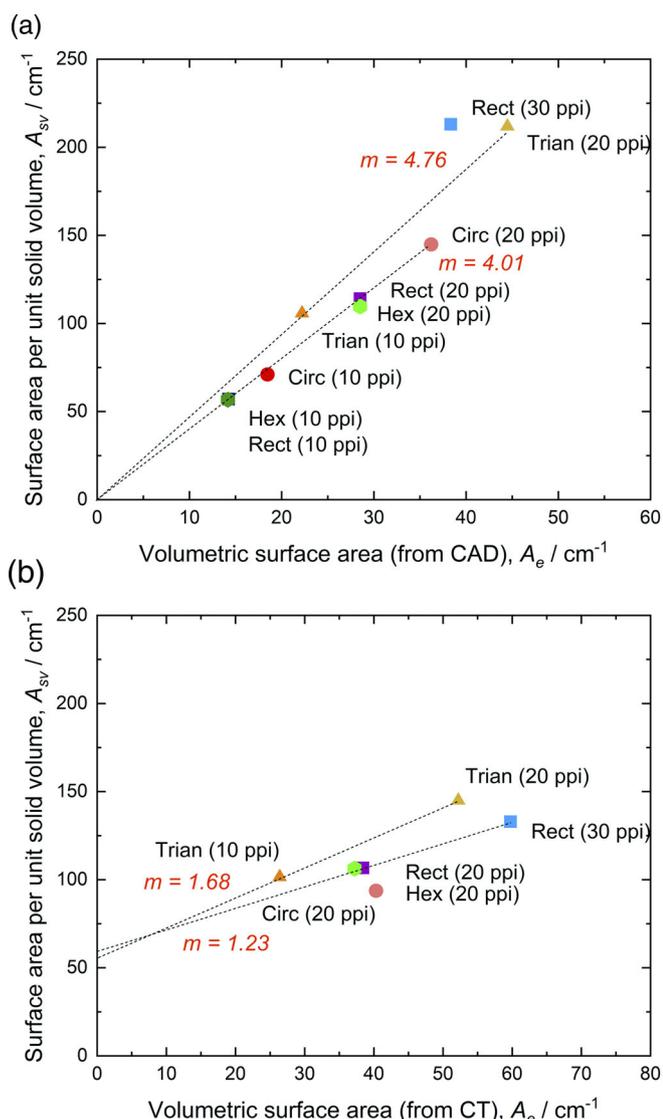


Figure 5. Plot of volumetric surface area versus surface area per unit solid volume for different porous electrode architectures (a) from nominal CAD dimensions and (b) from CT scans with a resolution of 0.0187 mm per voxel and ISO50% thresholding.

safely assumed that the real surface area of these porous geometries is larger than in the CAD drawings. As mentioned above, surface area properties are less accurate than the CT-determined volumetric porosity.³¹ A validation of the surface area of the 3D printed specimens as estimated by CT would require demanding work and careful consideration of the resolution and thresholding algorithms used to process the CT rendering of the specimens,⁶³ as it is known that the ISO50% algorithm is not always accurate.⁶⁴ These tasks are outside the scope of this work but such dependencies have been discussed in the case of RVC.³¹

The values of A_e and A_{sv} can be calculated from the surface area values for the 3D printed electrode architectures using Eqns (1) and (2), respectively. The results are shown in Table 3. As expected, the magnitude of both properties increases with the nominal linear porosity grade. However, when comparing the structures with the same nominal ppi, the triangular pore

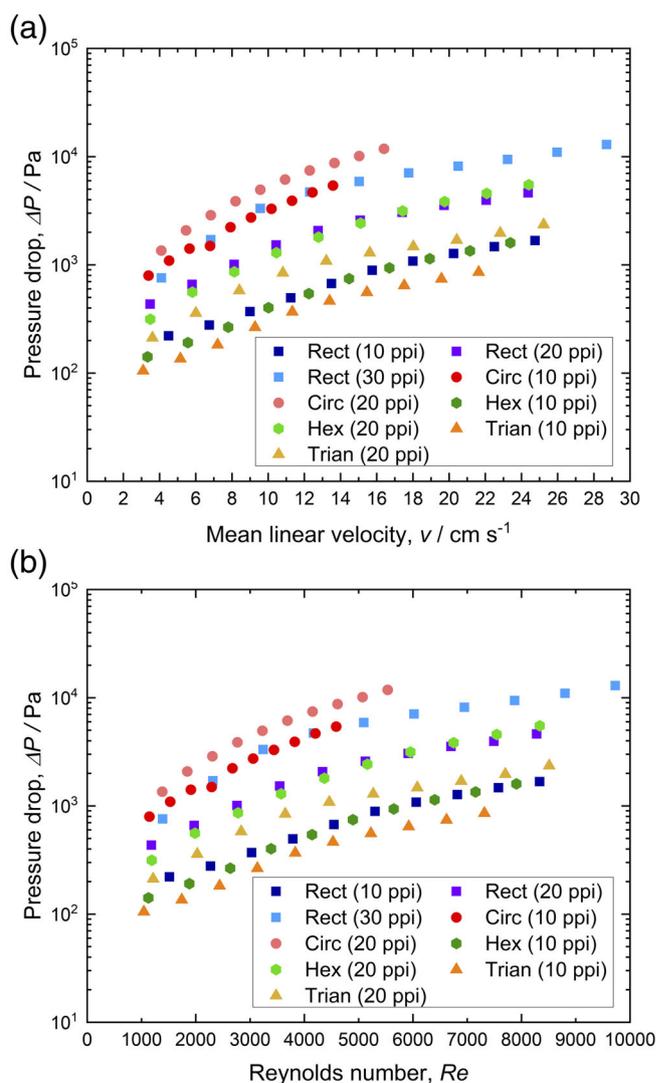


Figure 6. Pressure drop versus mean linear flow velocity and Re measured across different porous electrode architectures. Flow path length 20 mm.

architecture clearly affords the largest values among the geometrical pore shapes studied: at a 20 ppi pore grade, $A_e = 44.49 \text{ cm}^{-1}$ and $A_{sv} = 211.86 \text{ cm}^{-1}$ from CAD values. Such values can be contrasted with those of random, open-cell electrode materials: for Ni foam, A_e ranges between 35.0 and 92.5 cm^{-1} and A_{sv} between 1400 and 3700 cm^{-1} as the porosity grade increases from 45 to 100 ppi;⁴⁷ in the case of RVC, A_e ranges between 13.5 and 67.55 cm^{-1} as the porosity grade increases from 10 to 100 ppi.⁶²

The parameter A_{sv} defines how effective a given structure is to produce a surface out of solid material. An expression of this value as a function of A_e produces a characteristic relationship for a given porous material. An ideal plot of A_{sv} versus A_e from CAD surface area values is found in Fig. 5(a) as a benchmark for all of the architectures. There are apparent linear relationships for all the cases between 10 and 20 ppi, notably passing through the origin, as in the case of RVC between 10 and 100 ppi, which has a dimensionless slope value of ≈ 25.7 , as calculated from the A_e values from Friedrich *et al.*⁶⁵ and the ε values from Arenas *et al.*³¹ (see Fig. S7). However, two slopes are found in the porous electrode architectures: one for the triangular geometry (4.76) and one for the other geometries (4.01). Such a steep slope in

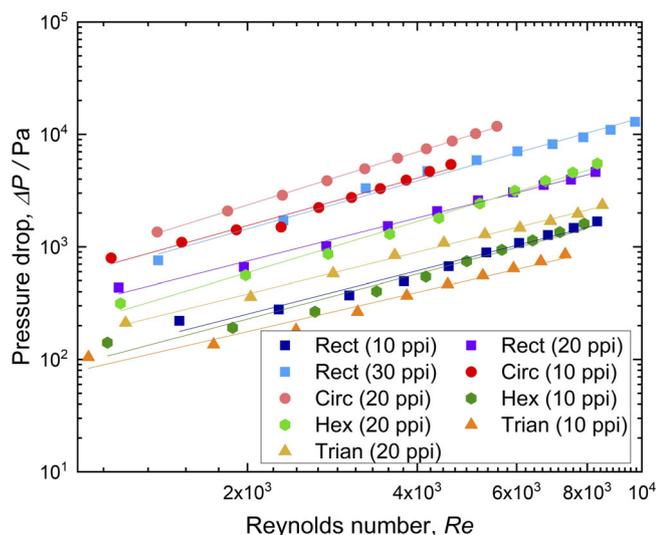


Figure 7. Pressure drop (logarithmic scale) versus Re (logarithmic scale) measured across different porous electrode architectures. Flow path length 20 mm.

the case of RVC reflects its much higher porosity, typically of 0.97. The rectangular pore geometry in a 30 ppi porosity grade material did not lie on the straight line relationship, this being the only sample having that linear porosity grade. Likewise, 100 ppi RVC, the highest porosity grade, appears to deviate from linearity. Further studies could focus on the physical origin of variation the characteristics of 3D printed porous electrodes over a wide range of ppi grades.^{40,66}

A plot of A_{sv} versus A_e constructed from real surface area values established by CT (rather than CAD ideal values) would be useful in practice and would reveal manufacturing tolerances. However, as shown above, the surface area values established by CT are not entirely accurate in this work owing to the further need for validated CT metrology of porous structures. However, a plot of A_{sv} versus A_e can still be presented cautiously for comparison purposes. Indeed, as shown in Table 3, A_e values are $\leq 35\%$ larger, whereas A_s is underestimated with a large dispersion between 3% and 38%. The fact that CT surface area properties are not accurate for the 3D printed specimens in this work is reinforced by the fact that the linear relationship of A_{sv} versus A_e intersects the y-axis at a positive value [see Fig. 5(b)]. Similar behaviour was observed when surface areas were calculated for RVC from CT scans with insufficient resolution in disagreement with direct methods.³¹ Clearly, there are research opportunities in studying the metrology of open-cell 3D printed porous materials and improving software approaches to the computation of surface area-related characteristics.

Pressure drop

The pressure drop taking place across the 20 mm-long 3D printed porous samples is shown in Fig. 6(a) as a function of mean linear velocity and in Fig. 6(b) as a function of the channel Reynolds number (where tube diameter is the characteristic length). Following the typical behaviour, the pressure drop increased along the flow rate for all the specimens, spanning about two orders of magnitude. As expected due to their larger pore sizes, 10 ppi triangular, rectangular and hexagonal structures exhibited a relatively low pressure drop throughout the whole range of flow rate and Reynolds numbers. For the maximum common mean linear

flow velocity of $\approx 14 \text{ cm s}^{-1}$, their values were 463.7, 670.4 and 744.6 Pa, respectively. By contrast, the 10 ppi and 20 ppi circular pore geometry specimens showed the highest values due to their small pores between cells. Their corresponding values near 14 cm s^{-1} were 5.4 and 8.7 kPa, respectively. The 30 ppi rectangular sample, which had the smallest pore size (0.7 mm), displayed a pressure drop of 5.88 kPa at the common linear flow velocity. This behaviour is comparable to the circular 10 ppi structure. The observed trends do not change in any substantial way when the Reynolds number is considered instead. As anticipated, the pressure drop was lowest for those samples having the lowest porosity grade, in accordance with other studies,^{55,67,68} including experiments with 3D printed open-cell metal foams of 3.5, 4.5 and 6 ppi.⁶⁹

Although normalized parameters are studied in the next sections, it is worth contrasting these results to the pressure drop obtained with other porous materials. For instance, the pressure drop of water at a 38-mm-long, uncompressed 10 ppi Al foam was 200 Pa at 10 cm s^{-1} ,⁶⁸ a reasonably lower value in view of its 0.92 volumetric porosity. Carbon felt, a common electrode material,⁷⁰ produced a pressure drop of 60 kPa at 4 cm s^{-1} in a 12-cm-long flow channel with a compression ratio of 80% in $0.5 \text{ mol dm}^{-3} \text{ Na}_2\text{SO}_4$.⁷¹ To put this in perspective, the combined ΔP in the ElectroSynCell® pilot-scale electrochemical reactor with 60 ppi grade Ni foams at an electrolyte (0.5 mol dm^{-3} aqueous NaOH) volumetric flow rate of $132 \text{ cm}^3 \text{ s}^{-1}$ was measured at 14.4 kPa.⁷²

The relationship between pressure drop and Re can be described in a practical manner by a log-log plot, as shown in Fig. 7. Here, the pressure drop over the 3D printed porous materials follows a linear power law [see Eqn (5)]. Thus, a set of two empirical coefficients can characterize their behaviour. These values are given in Table 4, along values found in the literature for Pt/Ti felt ($\epsilon = 0.80$), mesh ($\epsilon = 0.71$), micromesh ($\epsilon = 0.53$) and a polypropylene turbulence promoter (TP) mesh ($\epsilon = 0.78$) in a rectangular flow channel,⁷³ the FM01-LC electrochemical reactor,⁵⁰ and a rectangular channel reactor with a small interelectrode gap.⁷⁴ It can be seen that, for these 3D printed materials, the values for the exponent h , fall between 1.16 and 1.57, the higher

Table 4. Empirical coefficients e and h for the relationship between ΔP and Reynolds number ($\Delta P = e Re^h$) for the 3D printed porous electrode materials along with comparative data for some conventional flow-through electrodes for electrochemical reactors including examples of planar electrodes plus a turbulence promoter (polymer mesh)

Electrode material	e (Pa)	h	Source
Rectangular 10 ppi	1.53×10^{-2}	1.28	This work
Rectangular 20 ppi	4.72×10^{-2}	1.27	This work
Rectangular 30 ppi	3.04×10^{-2}	1.47	This work
Circular 10 ppi	3.52×10^{-2}	1.41	This work
Circular 20 ppi	1.57×10^{-2}	1.57	This work
Hexagonal 10 ppi	0.94×10^{-2}	1.33	This work
Hexagonal 20 ppi	0.61×10^{-2}	1.51	This work
Triangular 10 ppi	2.66×10^{-2}	1.16	This work
Triangular 20 ppi	3.12×10^{-2}	1.24	This work
Ni plate (unrestricted channel)	2.0×10^{-2}	1.29	74
Ni plate (promoter EPM2)	4.1×10^{-2}	1.61	74
Pt/Ti micromesh	114.6	1.07	73
Pt/Ti plate (promoter mesh)	10.1	0.82	73
Pt/Ti mesh	9.2	0.61	73
FM01-LC Cu plate (promoter E)	0.31	1.42	50
FM01-LC Cu plate (promoter F)	0.30	1.33	50

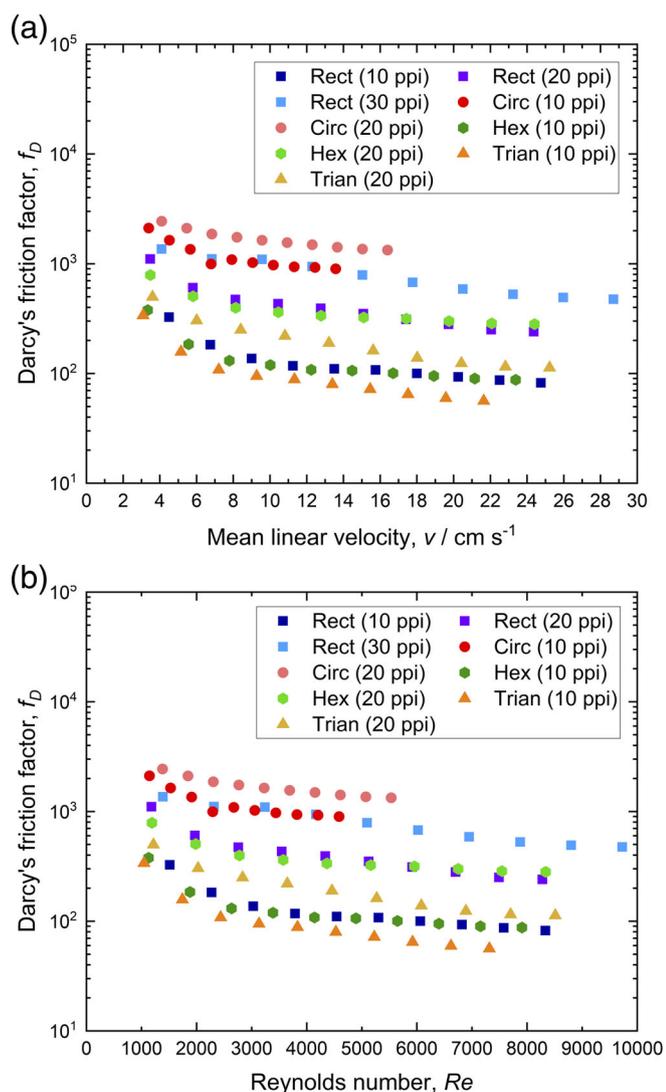


Figure 8. Darcy's friction factor vs. mean linear flow velocity and Reynolds number for different porous electrode architectures.

values corresponding to smaller pores. Consistently, a coarse mesh has a value of only 0.61. As a note, the values for ϵ of the 3D printed porous materials are lower than unity because their ΔP versus Re double logarithmic lines have negative y -values at the intercept.

Although beyond the scope of this work, it is worth mentioning that the hydrodynamic properties of porous electrodes can be implemented in the design of 3D printed structures and integrated with advanced image analysis. Examples of such an approach can be found in the field of modelling pressure drop at porous solids. For instance, periodic open-cell metallic foams were 3D printed using selective electron beam melting in order to estimate their surface area from pressure drop measurements⁶⁹ and the pressure drop at Al_2O_3 foams was modelled from structural parameters determined from magnetic resonance imaging and later determined from pressure drop studies.⁵⁵ More recently, porosity and tortuosity of SiC foams obtained from CT scans were used to predict the pressure drop across these materials.⁴⁰ The application of these strategies to the architectures here presented for electrochemical flow reactors can be expected.

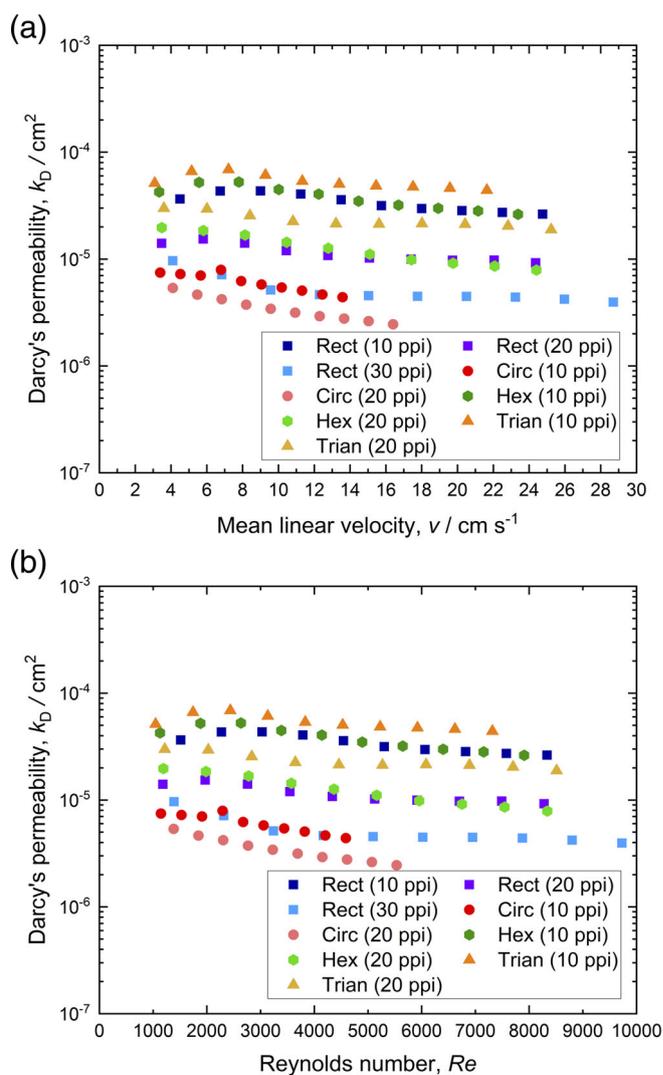


Figure 9. Darcy's permeability versus mean linear flow velocity and Re for different porous electrode architectures.

Table 5. Calculated Darcy's permeability of the evaluated porous electrodes, listed in increasing order

Electrode material	Volumetric porosity (from mass), ϵ	K_D (10^{-5} cm^2)
Circular 20 ppi	0.57	0.35
Rectangular 30 ppi	0.57	0.53
Circular 10 ppi	0.69	0.61
Rectangular 20 ppi	0.67	1.15
Hexagonal 20 ppi	0.66	1.28
Triangular 20 ppi	0.65	2.31
Rectangular 10 ppi	0.70	3.42
Hexagonal 10 ppi	0.70	3.83
Triangular 10 ppi	0.76	5.37

The porosity of 3D printed specimens is based on their mass.

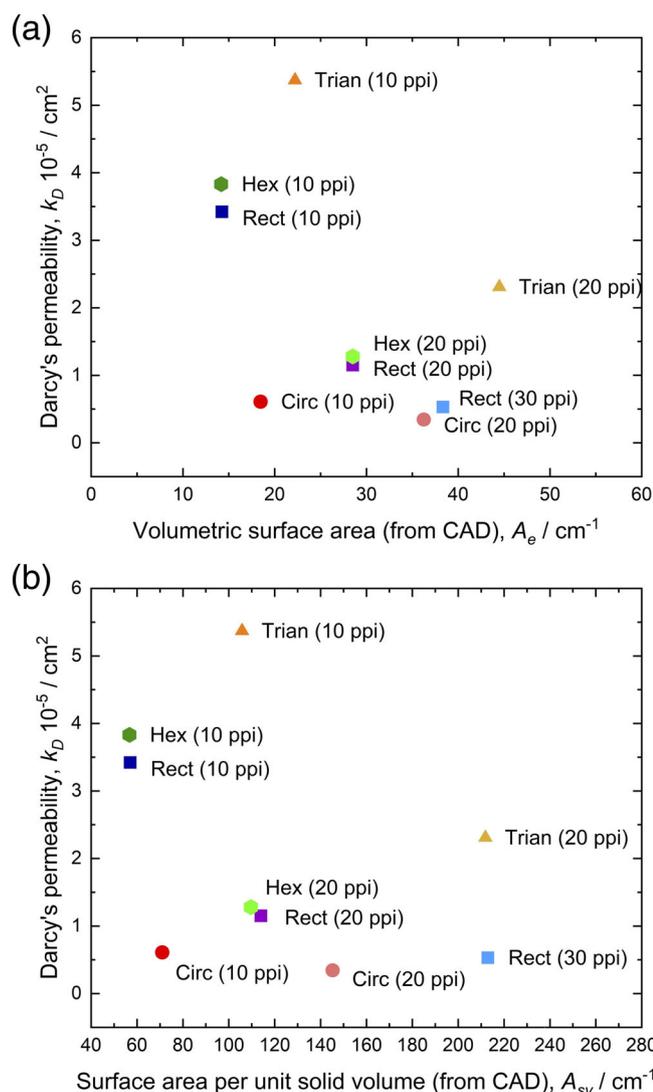


Figure 10. Relationship between hydraulic and surface area properties for different porous electrode architectures. Surface area taken from CAD dimensions. (a) Darcy's permeability versus volumetric surface area. (b) Darcy's permeability versus surface area per unit solid volume.

Darcy's friction factor, f_D

The normalized frictional losses across the porous materials were determined using f_D . Figure 8 shows f_D versus mean linear velocity and channel Re . The usual trend of frictional losses decreasing with rising flow rate was observed. The highest friction factors were 2113 and 2436 at 3.1 and 4 cm s^{-1} , respectively, for the circular 10 and 20 ppi materials. Their values of f_D dropped down to 897 and 1413, respectively, at 13.6 cm s^{-1} . The 20 ppi rectangular and 20 ppi hexagonal specimens displayed approximately the same values over the whole range of mean linear flow velocity. Meanwhile, the lowest values were produced by the triangular pore shape, reaching a minimum 854.6 at 22 cm s^{-1} for the 10 ppi porosity grade. These values are similar to those reported for Pt/Ti mesh and micromesh, 375 to 12.6 and 3399 to 173, respectively, in a rectangular channel flow cell.⁷³ Still, they were considerably lower than values achieved with a Pt/Ti felt, which reached a maximum value of 78 157, having pore sizes in the order of micrometers.⁷³ When compared to porous electrodes in the FM01-L

Table 6. Permeability coefficients of various porous materials and porous electrodes

Material	Porosity grade (ppi)	Volumetric porosity, ϵ	K_D (10^{-5} cm ²)	Source
SiC-Al ₂ O ₃ foam	45	0.88	25.6	39
	60	0.85	5.1	39
Al ₂ O ₃ foam	45	0.80	6.23	55
	45	0.85	9.95	55
Al foam	N/A	0.30	0.1	77
	N/A	0.70	1.2	77
Ni foam	10	0.92	352.9	68
	20	0.92	108.9	68
	40	0.93	70.2	68
	45	0.97	21.4	34
	60	0.97	8.23	34
	60	0.90	21.2	76
C felt	100	0.97	3.15	34
	N/A	0.96	0.24	56
Pt/Ti felt	N/A	0.80	0.13	73
Pt/Ti mesh	N/A	0.71	71.0	73
Pt/Ti micromesh	N/A	0.53	1.67	73
	N/A	0.78	44.5	73
Pt/Ti plate + TP	N/A	0.78	44.5	73

reactor, the 3D printed materials are intermediate between the values for stacked nets and metal foams.⁵⁰

Darcy's permeability, K_D

Darcy's permeability also was calculated based on the pressure drop readings. This coefficient is independent of the viscosity of the fluid and density, therefore, K_D of porous electrodes determined in different liquids (or electrolytes) can be compared. Figure 9 shows the permeability of the 3D printed materials against the mean linear flow rate and Re . The permeability values displayed slight deviations as the flow rate velocity increased, a behaviour also noted in compressed Al foam.⁶⁸ This could be explained by the anisotropy found in the 3D printed structures and the compressed foams, see top and side views of Fig. 2. By contrast, for uniform porous electrodes in a rectangular channel flow cell, permeability values were constant over the evaluated range of mean linear flow velocity.⁷³

The average values of K_D for each porous architecture are listed in Table 5 in increasing order. The 3D printed structure with circular pores, grade 20 ppi is the least permeable, and therefore not the best option in terms of increasing the efficiency of an electrochemical reactor. It is followed by the 30 ppi rectangular electrode. Interestingly, the 10 ppi rectangular and 10 ppi rectangular (2 mm pore size) specimens as well as the 20 ppi rectangular and 20 ppi rectangular (1 mm pore size) specimens show very close values for all of the evaluated mean linear flow velocities. One could argue that, in these cases, the size of the pores affects the permeability coefficient to a greater extent than their shape. Therefore, it could be stated that the electrodes with rectangular and hexagonal pores could be used interchangeably. However, when considering its greater volumetric surface area

(see Table 3), the rectangular 20 ppi material should be chosen for an electrochemical application over the hexagonal equivalent.

Triangular porous structures are the most permeable, having higher K_D values than those of the other geometrical shapes for both 10 ppi and 20 ppi materials (see Table 5). Moreover, the 10 ppi triangular 3D printed material also produced the lowest pressure gradient and frictional losses. This means that, as a flow-through or flow-across porous electrode, it would require the lowest electrolyte pumping power among the specimens evaluated in this study (as long as the same flow direction relative to the structure is kept). This is seen more clearly in a plot of K_D versus A_e (as given by CAD). Such relationships, shown in Fig. 10(a) for all of the evaluated porous architectures, indicate the ideal trade-off between electrode surface area and hydraulic permeability (i.e. resistance to the fluid flow of an electrolyte). (The same plot taking the A_e values estimated from uncalibrated CT can be seen in Fig. S8, wherein the triangular architectures also perform better than the other pore geometries.)

Continuing with Fig. 10, the A_e of the CAD 10 ppi triangular pore specimen was between ≈ 1.2 - and 1.7 -fold larger than the surface areas of the electrodes of the same grade but different geometries (see Table 3). It also has close to 25% less mass (see Table 2). This could be a beneficial factor in terms of minimizing the net size, mass and cost of the electrochemical reactor. Furthermore, the 20 ppi triangular specimen has about twice the A_e of its 10 ppi grade equivalent, being also $\approx 30\%$ superior to the rectangular and hexagonal geometries. This, suggests that the 20 ppi triangular structure could be advantageous as a porous electrode in an electrochemical flow reactor, having the best combination of high permeability and high surface area among the materials designed in this work. A plot of K_D versus A_{sv} , seen in Fig. 10(b), shows essentially the same trends.

These K_D values of the 3D printed porous materials can be put in perspective when compared to those reported in the literature (see Table 6). K_D decreases with decreasing pore diameter of open-cell foams.^{75,76} The reason for this is that for decreasing pore diameter there are more struts in the same volume that obstruct fluid flow.³⁹ Materials with similar volumetric porosity display close values. Among those reported previously, porous SiC-Al₂O₃ ($\varepsilon = 0.85$)³⁹ and alumina foams ($\varepsilon = 0.80$)⁵⁵ have permeability values of 5.1×10^{-5} and 6.2×10^{-5} cm², respectively, being close to the triangular 10 ppi design. Meanwhile, 0.70 porous Al foam has a permeability of 1.2×10^{-5} cm²,⁷⁷ being quite close to the 20 ppi hexagonal and rectangular pore architectures. Additionally, the latter is just under the 1.7×10^{-5} cm² values reported for Pt/Ti micromesh electrodes.⁷³ As expected, the permeabilities of materials having significantly larger volumetric porosity or much larger pore sizes are at least one order of magnitude higher than the values presented in the current work. This is the case of Al foams with a porosity of 0.92 (108.9×10^{-5} cm²)⁶⁸ and expanded metal mesh (71.0×10^{-5} cm²).⁷³ The opposite is true for materials with very small pores, such as C felt (0.2×10^{-5} cm²),⁵⁶ or Ti felt (0.1×10^{-5} cm²),⁷³ which are less permeable than the circular 20 ppi geometry. In summary, the 3D printed porous architectures display a wide range of hydrodynamic permeabilities and can be made analogous to conventional porous materials.

CONCLUSIONS

- Structures with triangular pores were found to be superior to other architectures considered in this work in terms of suitability for specialized electrochemical cells and reactors as flow-

through or flow-across electrodes. The triangular architectures displayed higher permeability, lower mass and increased surface area. These characteristics will diminish electrolyte pumping power, increase the limiting current and mass transfer of the electrochemical reaction and reduce cost and time of manufacture. Improvements of open-cell materials for electrodes can be expected by further topology optimization, tailoring anisotropy and by control of current and potential distribution.

- CT revealed irregularities in the 3D printed materials resulting from laser movement tolerances, although this could be avoided with the optimization of printing parameters. Volumetric porosity values obtained from CT corresponded to the ones calculated from the measured mass and volume of the specimens. However, CT surface area estimations turned out to be between 10% and 36% higher than the CAD surface areas. Nevertheless, our results indicate the importance of surface area metrology in 3D printed porous materials for better accuracy in these estimations.

ACKNOWLEDGEMENTS

The authors thank R. P. Boardman for his assistance with the CT scans and acknowledge provision of tomographic imaging facilities by the μ -VIS centre at the University of Southampton, supported by EPSRC grant EP-H01506X (UK). This study was initiated by NK's MSc dissertation at the University of Southampton.

SYMBOLS

A	Surface area (cm ²)
A_e	Volumetric surface area (cm ⁻¹)
A_{sv}	Surface area per unit volume of solid material (cm ⁻¹)
D	Diameter of porous electrode (cm)
d	Hydraulic channel diameter (cm)
e	Empirical coefficient in Eqn (5) (Pa)
F	Faraday constant (C mol ⁻¹)
f_D	Darcy's friction factor (dimensionless)
H	Height of porous electrode (cm)
h	Empirical coefficient in Eqn (5) (dimensionless)
I_L	Limiting current (A)
K_D	Darcy's permeability (cm ²)
k_m	Mass transfer coefficient (cm s ⁻¹)
L	Length of porous electrode in the direction of flow (cm)
m	Mass (g)
P	Pressure (Pa)
Q	Volumetric flow rate (cm ³ s ⁻¹)
Re	Reynolds number (dimensionless)
V_{bulk}	Bulk volume of the electrode (cm ³)
V_e	Overall volume of the porous electrode (cm ³)
V_{solid}	Volume of solid metal in the electrode (cm ³)
v	Mean linear velocity of fluid cm s ⁻¹
W	Width of porous electrode cm

GREEK SYMBOLS

ΔP	Pressure drop (Pa)
ε	Volumetric porosity (dimensionless)
μ	Dynamic viscosity of fluid (g cm ⁻¹ s ⁻¹)
ρ	Density (g cm ⁻³)

ABBREVIATIONS

CAD	computer-aided design
-----	-----------------------

CT	X-ray computed tomography
ppi	pores per linear inch (porosity grade)
ROI	region of interest
RTD	residence time distribution
RVC	reticulated vitreous carbon
SEM	scanning electron microscopy
SLM	selective laser melting
TP	turbulence promoter

SUPPORTING INFORMATION

Supporting information may be found in the online version of this article.

REFERENCES

- Lee C-Y, Taylor AC, Nattestad A, Beirne S and Wallace GG, 3D printing for electrocatalytic applications. *Joule* **3**:1835–1849 (2019).
- Ambrosi A, Shi RRS and Webster RD, 3D-printing for electrolytic processes and electrochemical flow systems. *J Mater Chem A* **8**:21902–21929 (2020).
- Arenas LF, Ponce de León C and Walsh FC, 3D-printed porous electrodes for advanced electrochemical flow reactors: a Ni/stainless steel electrode and its mass transport characteristics. *Electrochem Commun* **77**:133–137 (2017).
- Tai XY, Zhakeyev A, Wang H, Jiao K, Zhang H and Xuan J, Accelerating fuel cell development with additive manufacturing technologies: state of the art, opportunities and challenges. *Fuel Cells* **19**:636–650 (2019).
- Arenas LF and Walsh FC, Ponce de León C, 3D-printing of redox flow batteries for energy storage: a rapid prototype laboratory cell. *ECS J Solid State Sci Technol* **4**:P3080–P3085 (2015).
- Márquez-Montes RA, Collins-Martínez VH, Pérez-Reyes I, Chávez-Flores D, Graeve OA and Ramos-Sánchez VH, Electrochemical engineering assessment of a novel 3D-printed filter-press electrochemical reactor for multipurpose laboratory applications. *ACS Sustainable Chem Eng* **8**:3896–3905 (2020).
- Ambrosi A and Pumera MP, Multimaterial 3D-printed water electrolyzer with earth-abundant electrodeposited catalysts. *ACS Sustainable Chem Eng* **6**:16968–16975 (2018).
- Walsh FC, Arenas LF and Ponce de León C, Developments in plane parallel flow channel cells. *Curr Opin Electrochem* **16**:10–18 (2019).
- Walsh FC, Arenas LF and Ponce de León C, A virtuous cycle in materials engineering and surface finishing: design-print-image. *Trans IMF* **98**:65–72 (2020).
- Tian X and Zhou K, 3D printing of cellular materials for advanced electrochemical energy storage and conversion. *Nanoscale* **12**:7416–7432 (2020).
- Egorov V and O'Dwyer C, Architected porous metals in electrochemical energy storage. *Curr Opin Electrochem* **21**:201–208 (2020).
- Abrantes LM, Three-dimensional electrode, in *Encyclopedia of Applied Electrochemistry*, ed. by Kreysa G, Ota K-I and Savinell RF. Springer, New York, pp. 2077–2081 (2014).
- Couper AM, Pletcher D and Walsh FC, Electrode materials for electro-synthesis. *Chem Rev* **90**:837–865 (1990).
- Walsh FC and Arenas LF, Ponce de León C, developments in electrode design: structure, decoration and applications of electrodes for electrochemical technology. *J Chem Technol Biotechnol* **93**:3073–3090 (2018).
- Arenas LF, Ponce de León C and Walsh FC, Three-dimensional porous metal electrodes: fabrication, characterisation and use. *Curr Opin Electrochem* **16**:1–9 (2019).
- Szyrkowicz L, Application of electrochemical oxidation for treatment of industrial wastewater — the influence of reactor hydrodynamics on direct and mediated processes. *J Chem Technol Biotechnol* **81**:1375–1383 (2006).
- Anglada A, Urriaga A and Ortiz I, Contributions of electrochemical oxidation to waste-water treatment: fundamentals and review of applications. *J Chem Technol Biotechnol* **84**:1747–1755 (2009).
- Pletcher D, Organic electrosynthesis – a road to greater application: a mini review. *Electrochem Commun* **88**:1–4 (2018).
- Llanos J, Moraleda I, Sáez C, Rodrigo MA and Cañizares P, Reactor design as a critical input in the electrochemical production of peroxyacetic acid. *J Chem Technol Biotechnol* **94**:2955–2960 (2019).
- Soloman PA, Basha CA, Velan M and Balasubramanian N, Electrochemical degradation of pulp and paper industry waste-water. *J Chem Technol Biotechnol* **84**:1303–1313 (2009).
- González Pérez O, Castro Larragoitia S and Rodríguez-Torres I, Preliminary studies on the electrochemical recovery of Zn and Cd from effluent produced by a zinc refinery plant using a filterpress reactor. *J Chem Technol Biotechnol* **88**:1371–1379 (2012).
- Sánchez-Díez E, Ventosa E, Guarnieri M, Trovò A, Flox C, Marcilla R et al., Redox flow batteries: status and perspective towards sustainable stationary energy storage. *J Power Sources* **481**:228804 (2021).
- Zhang Y-Z, Wang Y, Cheng T, Yao L-Q, Li X, Lai W-Y et al., Printed supercapacitors: materials, printing and applications. *Chem Soc Rev* **48**:3229–3264 (2019).
- Gu DD, Meiners W, Wissenbach K and Poprawe R, Laser additive manufacturing of metallic components: materials, processes and mechanisms. *Int Mater Rev* **57**:133–164 (2012).
- Lee C-Y, Taylor AC, Beirne S and Wallace GG, 3D-printed conical arrays of TiO₂ electrodes for enhanced photoelectrochemical water splitting. *Adv Energy Mater* **7**:1701060 (2017).
- Arenas LF, Kaishubayeva N, Ponce de León C and Walsh FC, Electrodeposition of platinum on 3D-printed titanium mesh to produce tailored, high area anodes. *Trans IMF* **98**:48–52 (2020).
- Lölsberg J, Starck O, Stiefel S, Hereijgers J and Breugelmans TMW, 3D-printed electrodes with improved mass transport properties. *Chem-ElectroChem* **4**:3309–3313 (2017).
- Hereijgers J, Schalck J, Lölsberg J, Wessling M and Breugelmans T, Indirect 3D printed electrode mixers. *ChemElectroChem* **6**:378–382 (2019).
- Cheng TS, Nasir MZM, Ambrosi A and Pumera M, 3D-printed metal electrodes for electrochemical detection of phenols. *Appl Mater Today* **9**:212–219 (2017).
- Huang X, Chang S, Lee WSV, Ding J and Xue JM, Three-dimensional printed cellular stainless steel as a high-activity catalytic electrode for oxygen evolution. *J Mater Chem A* **5**:18176–18182 (2017).
- Arenas LF, Boardman RP and Ponce de León C, Walsh FC, X-ray computed micro-tomography of reticulated vitreous carbon. *Carbon* **135**:85–94 (2018).
- Catañeda LF, Rivera FF, Pérez T and Nava JL, Mathematical modeling and simulation of the reaction environment in electrochemical reactors. *Curr Opin Electrochem* **16**:75–82 (2019).
- Trasatti S and Petrii OA, Real surface area measurements in electrochemistry. *Pure Appl Chem* **63**:711–734 (1991).
- Langlois S and Coeuret F, Flow-through and flow-by porous electrodes of nickel foam. II. Diffusion-convective mass transfer between the electrolyte and the foam. *J Appl Electrochem* **19**:51–60 (1989).
- Jervis R, Kok MDR, Neville TP, Meyer Q, Brown LD, Iacoviello F et al., In situ compression and X-ray computed tomography of flow battery electrodes. *J Energy Chem* **27**:1353–1361 (2018).
- Olvera OG and Lapidus-Lavine GT, Use of X-ray tomography for the experimental verification of a mathematical model for the recovery of Cu and Cd in a flow-by porous electrode reactor. *Int J Chem React Eng* **10**:A36 (2012).
- Arenas LF, Ponce de León C, Boardman RP and Walsh FC, Electrodeposition of platinum on titanium felt in a rectangular channel flow cell. *J Electrochem Soc* **164**:D57–D66 (2017).
- Arenas LF, Ponce de León C, Boardman RP and Walsh FC, Characterisation of platinum electrodeposits on a titanium micromesh stack in a rectangular channel flow cell. *Electrochim Acta* **247**:994–1005 (2017).
- Innocentini MDM, Salvini VR, Macedo A and Pandolfelli VC, Prediction of ceramic foams permeability using Ergun's equation. *Materials Research* **2**:283–289 (1999).
- Ou X, Zhang X, Lowe T, Blanc R, Rad MN, Wang Y et al., X-ray micro computed tomography characterization of cellular SiC foams for their applications in chemical engineering. *Mater Charact* **123**:20–28 (2017).
- Liu X, Li X, Ju S, Gu Y, Tan W, Li X et al., Miniaturized application of 3D-printed large-flow microreactor in extraction and separation of platinum, palladium, and rhodium. *J Chem Technol Biotechnol* **96**:1007–1015 (2021).
- Brown CJ, Walsh FC and Pletcher D, Mass transfer and pressure drop in a laboratory filterpress electrolyser. *Trans IChemE* **73**:196–205 (1995).
- Kim MJ, Seo Y, Cruz MA and Wiley BJ, Metal nanowire felt as a flow-through electrode for high-productivity electrochemistry. *ACS Nano* **13**:6998–7009 (2019).

- 44 MacDonald M and Darling RM, Modeling flow distribution and pressure drop in redox flow batteries. *AIChE J* **64**:3746–3755 (2018).
- 45 Pletcher D, Whyte I, Walsh FC and Millington JP, Reticulated vitreous carbon cathodes for metal ion removal from process streams part I: mass transport studies. *J Appl Electrochem* **21**:659–666 (1991).
- 46 Milshtein JD, Tenny KM, Barton JL, Drake J, Darling RM and Brushett FR, Quantifying mass transfer rates in redox flow batteries. *J Electrochem Soc* **164**:E3265–E3275 (2017).
- 47 Langlois S and Coeuret F, Flow-through and flow-by porous electrodes of nickel foam I material characterization. *J Appl Electrochem* **19**:43–50 (1989).
- 48 González-García J, Bonete P, Expósito E, Montiel V, Aldaz A and Torregrosa-Maciá R, Characterization of a carbon felt electrode: structural and physical properties. *J Mater Chem* **9**:419–426 (1999).
- 49 Pletcher D and Walsh FC, Three-dimensional electrodes, in *Electrochemistry for a Cleaner Environment*, ed. by Genders D and Weinberg N. The Electroynthesis Company, New York, NY, pp. 51–100 (1992).
- 50 Brown CJ, Pletcher D, Walsh FC, Hammond JK and Robinson D, Studies of space-averaged mass transport in the FM01-LC laboratory electrolyser. *J Appl Electrochem* **23**:38–43 (1993).
- 51 Rousar I and Cezner V, *Mass transfer coefficients and friction coefficients for rough electrodes*, in Institution of Chemical Engineers Symposium Series, IChemE, Vol. **98**, pp. 85–95 (1986).
- 52 Müller V and Rousar I, *Mass transfer coefficient and pressure losses for membrane cell with spacers*, in Dechema Monographs, ed. by G Kreysa, Vol. **123**. VCH, Weinheim, pp. 331–345 (1991).
- 53 Culcasi A, Gurreri L, Zaffora A, Cosenza A, Tamburini A and Micale G, On the modelling of an acid/base flow battery: an innovative electrical energy storage device based on pH and salinity gradients. *Appl Energy* **277**:115576 (2020).
- 54 Aparicio-Mauricio G, Rodríguez FA, Pijpers JH and Cruz-Díaz MR, CFD modeling of residence time distribution and experimental validation in a redox flow battery using free and porous flow. *J Energy Storage* **29**:101337 (2020).
- 55 Incera Garrido G, Patcas FC, Lang S and Kraushaar-Czarnetzki B, Mass transfer and pressure drop in ceramic foams: a description for different pore sizes and porosities. *Chem Eng Sci* **63**:5202–5217 (2008).
- 56 Averbukh M, Pozin A and Sukoriansky S, Electrolyte pumping optimization in already manufactured vanadium redox battery based on experimentally determined electrical and hydrodynamic losses. *J Energy Eng* **143**:04016050 (2017).
- 57 Forner-Cuenca A, Penn EE, Oliveira AM and Brushett FR, Exploring the role of electrode microstructure on the performance of non-aqueous redox flow batteries. *J Electrochem Soc* **166**:A2230–A2241 (2019).
- 58 Bracconi M, Ambrosetti M, Okafor O, Sans V, Zhang X, Ou X *et al.*, Investigation of pressure drop in 3D replicated open-cell foams: coupling CFD with experimental data on additively manufactured foams. *Chem Eng J* **377**:120123 (2019).
- 59 Yamashin Steel Co. Inc., Specific gravity (density) of stainless steel, etc. (2015). Available: http://www.yamco-yamashin.com/en/products/guide_specific_gravity.html [20 June 2019].
- 60 Cengel YA and Cimbala JM, *Fluid Mechanics. Fundamentals and Applications*, McGraw-Hill, London (2010).
- 61 Jorné J and Roayaie E, Effect of pore-size distribution on metal ion removal in flow-through porous electrodes. *J Electrochem Soc* **133**:1649–1653 (1986).
- 62 Walsh FC, Arenas LF, Ponce de León C, Reade GW, Whyte I and Mellor BG, The continued development of reticulated vitreous carbon as a versatile electrode material: structure, properties and applications. *Electrochim Acta* **215**:566–591 (2016).
- 63 Kruth J-P, Bartscher M, Carmignato S, Schmitt R, De Chiffre L and Weckenmann A, Computed tomography for dimensional metrology. *CIRP Annals* **60**:821–842 (2011).
- 64 Kiekens K, Welkenhuyzen F, Tan Y, Bleys P, Voet A, Kruth J-P *et al.*, A test object with parallel grooves for calibration and accuracy assessment of industrial computed tomography (CT) metrology. *Meas Sci Technol* **22**:115502 (2011).
- 65 Friedrich JM, Ponce de León C, Reade GW and Walsh FC, Reticulated vitreous carbon as an electrode material. *J Electroanal Chem* **561**:203–217 (2004).
- 66 Bruns S, Stipp SLS and Sørensen HO, Statistical representative elementary volumes of porous media determined using greyscale analysis of 3D tomograms. *Adv Water Resour* **107**:32–42 (2017).
- 67 Pletcher D, Whyte I and Walsh FC, Reticulated vitreous carbon cathodes for metal ion removal from process streams part II: removal of copper(II) from acid sulphate media. *J Appl Electrochem* **21**:667–671 (1991).
- 68 Boomsma K and Poulikakos D, The effects of compression and pore size variations on the liquid flow characteristics in metal foams. *J Hydroinf* **124**:263–272 (2002).
- 69 Inayat A, Schwerdtfeger J, Freund H, Körner C, Singer RF and Schwioger W, Periodic open-cell foams: pressure drop measurements and modeling of an ideal tetrakaidecahedra packing. *Chem Eng Sci* **66**:2758–2763 (2011).
- 70 Castañeda LF, Walsh FC, Nava JL and Ponce de León C, Graphite felt as a versatile electrode material: properties, reaction environment, performance and applications. *Electrochim Acta* **258**:1115–1139 (2017).
- 71 González-García J, Montiel V, Aldaz A, Conesa JA, Pérez JR and Codina G, Hydrodynamic behavior of a filter-press electrochemical reactor with carbon felt as a three-dimensional electrode. *Ind Eng Chem Res* **37**:4501 (1998).
- 72 Montillet A, Comiti J and Legrand J, Application of metallic foams in electrochemical reactors of filter-press type part I: flow characterization. *J Appl Electrochem* **23**:1045–1050 (1993).
- 73 Arenas LF, Ponce de León C and Walsh FC, Pressure drop through platinumized titanium porous electrodes for cerium-based redox flow batteries. *AIChE J* **64**:1135–1146 (2018).
- 74 Colli AN, Toelzer R, Bergmann MEH and Bisang JM, Mass-transfer studies in an electrochemical reactor with a small interelectrode gap. *Electrochim Acta* **100**:78–84 (2013).
- 75 Khayargoli P, Loya V, Lefebvre LP and Medraj M, The impact of microstructure on the permeability of metal foams, in *Proceedings of the 2004 Canadian Society of Mechanical Engineering*. CSME forum 2004, London (Canada), pp. 221–228 (2004).
- 76 Miwa S and Revankar ST, Hydrodynamic characterization of nickel metal foam, part 1: single-phase permeability. *Transp Porous Med* **80**:269–279 (2009).
- 77 Antohe BV, Lage JL, Price DC and Weber RM, Experimental determination of permeability and inertia coefficients of mechanically compressed aluminum porous matrices. *J Fluids Eng* **119**:404–412 (1997).