

Nanoscale Advances

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: N. Mohamed, Y. Han, S. Harcourt-Vernon, A. L. Hector, A. Houghton, G. Reid, D. R. Williams and W. Zhang, *Nanoscale Adv.*, 2023, DOI: 10.1039/D3NA00031A.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

Effects of surfactant head group modification on vertically oriented mesoporous silica produced by the electrochemically assisted surfactant assembly method

Nabil A. N. Mohamed,^a Yisong Han,^b Sarah Harcourt-Vernon,^a Andrew L. Hector,^{a*} Anthony R. Houghton,^c Gillian Reid,^a Daryl R. Williams^c and Wenjian Zhang^a

^a School of Chemistry, University of Southampton, Highfield, Southampton SO17 1BJ, UK. Email A.L.Hector@soton.ac.uk

^b Department of Physics, University of Warwick, Coventry CV4 7AL, UK

^c Department of Chemical Engineering, Imperial College London SW7 2AZ, UK

Abstract

Production of mesoporous silica films with vertically oriented pores has been a challenge since interest in such systems developed in the 1990s. Vertical orientation can be achieved by the electrochemically assisted surfactant assembly (EASA) method using cationic surfactants such as cetyltrimethylammonium bromide (C₁₆TAB). The synthesis of porous silicas using a series of surfactants with increasing head sizes is described, from octadecyltrimethylammonium bromide (C₁₈TAB) to octadecyltriethylammonium bromide (C₁₈TEAB). These increase pore size, but the degree of hexagonal order in the vertically aligned pores reduces as the number of ethyl groups increases. Pore accessibility is also reduced with the larger head groups.

Introduction

In the 1990s, Mobil researchers reported the M41S silica materials^{1,2} and since then mesoporous silicas have found many applications, including in catalysis^{3,4}, biosensing⁵, electrochemical sensing⁶ and the encapsulation of metals, metal oxides and semiconductors to produce novel materials.^{7,8,9,10,11} Mesoporous silica materials possess attractive characteristic properties such as high specific surface areas, often greater than 1000 m² g⁻¹,¹² well organised arrays of pores and a pore size distributions in the range of 2-50 nm, depending on the method applied.

The most common approach to the synthesis of mesoporous silica films is by the evaporation induced self-assembly method (EISA).¹⁵ This process involves the use of tetraethylorthosilicate and a surfactant in a prepared ethanol/water solution. The solution is sprayed, spin-coated or dip-coated onto the surface and, as the solvent evaporates from the substrate surface, the concentration of the surfactant increases locally, driving the growth of surfactant micelles *via* self-assembly. The



surfactant is often removed either by Soxhlet extraction or calcination. Zhao et al.¹⁶ studied the influence of cationic surfactants such as cetyltriethylammonium bromide (C₁₆TEAB) and Gemini surfactants (C₁₈₋₃₋₁) in the formation of mesoporous silica films by dip-coating from aqueous and non-aqueous solutions. It was demonstrated that silica films containing C₁₆TEAB tend to produce 3D cubic pore structures in aqueous conditions, whereas under highly acidic conditions, 2D-hexagonal pores are favoured using the same surfactant. Under aqueous and non-aqueous environments, silica films with Gemini surfactant, C₁₈₋₃₋₁, produce either 3D-hexagonal or 2D-hexagonal structures, where the pores in the 2D structures are oriented parallel to the surface.

Vertical pore orientation is rather more difficult to achieve in comparison to horizontal orientation using the EISA method. Vertically-oriented mesopores can be achieved by a Stöber process with C₁₆TAB under basic conditions, but these methods suffer from long preparation times to make very thin films.¹⁷ An alternative method is electrochemically assisted surfactant assembly (EASA) using a cationic surfactant, usually C₁₆TAB, and a silica precursor.^{18,12} A conductive substrate is placed in an ethanol/water sol containing a cationic surfactant and a negative potential is applied, resulting in the production of hydroxide ions that increase pH in the vicinity of the electrode, which accelerates the rate of Si-O-Si bond formation around the formed hemi-micelles. The surfactant is removed from the mesopores by washing with an acidic alcoholic solution or calcination for 30 minutes to generate mesoporous silica films with vertical pore channels. We previously reported variations in those oriented mesoporous silica films that can be achieved with C_nTAB surfactants from C₁₄ to C₂₄.¹⁹ Faster ion diffusion rates were observed from a variety of redox probe molecules for films with increasing surfactant chain lengths, linked to increases in pore size. EASA most commonly uses C₁₆TAB, resulting in small diameter pores of 2-3 nm diameter. Ryoo et al.¹⁴ showed that under hydrothermal conditions that would produce MCM-41 powders with CTAB, C₂₂TAB produced lamellar structures. Post-synthesis grafting may facilitate better electrolyte access to the substrate surface during electrodeposition.²¹ The use of swelling agents such as mesitylene is also an alternative way to produce larger pores.^{22,20}

The effects of various modifications to surfactants in the hydrothermal synthesis of mesoporous powdered silicas have been reported. Lin et al.¹³ investigated a surfactant chain length of 16 carbon atoms with various other head groups. The substitution of a methyl for an ethyl or benzyl group in the conventional C₁₆TAB surfactant brought about a decline in pore order and a shrinkage in pore size from 4.0 nm (C₁₆TAB) to 3.6 nm (cetyldimethylethylammonium bromide) surfactants. Ryoo et al.¹⁴ found that mixing C_nTAB and alkyltriethylammonium bromide surfactants, with a carbon chain length from C₁₂ to C₂₂, could increase the structural order of MCM-41. Furthermore, Campos et al.²³ produced aqueous dispersions of mesoporous silica using mixtures of C₁₆TAB and



cetyltripropylammonium bromide (C_{16} TPAB) under hydrothermal conditions, showing that increasing the surfactant head group resulted in larger lattice spacings but also a significant reduction in hexagonal ordering. The understanding of such head group modifications in the EASA process, which works very differently due to surfactant ordering by the electric field, is limited to a study by Robertson et al.²⁰ who evaluated the influence on the lattice parameters and pore ordering of switching the head group of the surfactant to a bulkier cetylpyridinium bromide (CPyB). The film became less well-organised, but an increase in the lattice spacings was noticed. In this paper, the porosity, structural pore order and pore size are systematically evaluated for porous silicas produced using the EASA method with cationic surfactants with a tetraalkylammonium head group containing a hydrophobic chain of 18 carbons, and a mixture of zero, one, two or three ethyl groups, with methyl groups making up the remainder, $[C_{18}H_{37}NMe_{3-x}Et_x]Br$ with $x = 0, 1, 2$ or 3 .


Experimental

Octadecyltrimethylammonium bromide (C_{18} TAB, 98%) was purchased from Sigma Aldrich. The octadecylalkylammonium bromide surfactants were prepared by the reaction of alkylamine and 1-bromooctadecane in ethanol according to Scheraga et al.²⁴ The synthesis used 1-bromooctadecane (5.0001 g, $\geq 97\%$, Sigma Aldrich) which was dissolved in ethanol (25 cm³) and dimethylethylamine (10 x mol eq, $\geq 99\%$, Sigma Aldrich), diethylmethylamine (10 x mol eq, 97%, Sigma Aldrich) or triethylamine (10 x mol eq, $\geq 99.5\%$, Sigma Aldrich) was added into the solution. The mixture was refluxed for 8 h under stirring at 100 °C using a dry ice condenser. The solution was filtered first to remove particulates, then the filtrate was placed in the freezer. The crude product was collected by filtration and a rotary evaporator was used to reduce the ethanol solvent to recover the solid from the filtrate. Recrystallisation of the combined 2 crop crystals from ethanol produced a final yield of 4.98 g octadecyldimethylethylammonium bromide, (C_{18} DMEAB, yield = 99% after drying, white solid), 4.80 g octadecyldiethylmethylammonium bromide (C_{18} DEMAB, yield = 96% after drying, off white solid) and 4.76 g octadecyltriethylammonium bromide (C_{18} TEAB, yield = 95% after drying, off-white solid). ¹H and ¹³C{¹H} NMR and positive ion ESI MS are shown in the supplementary information.

View Article Online
DOI: 10.1039/D3NA00031A

Nanoscale Advances Accepted Manuscript



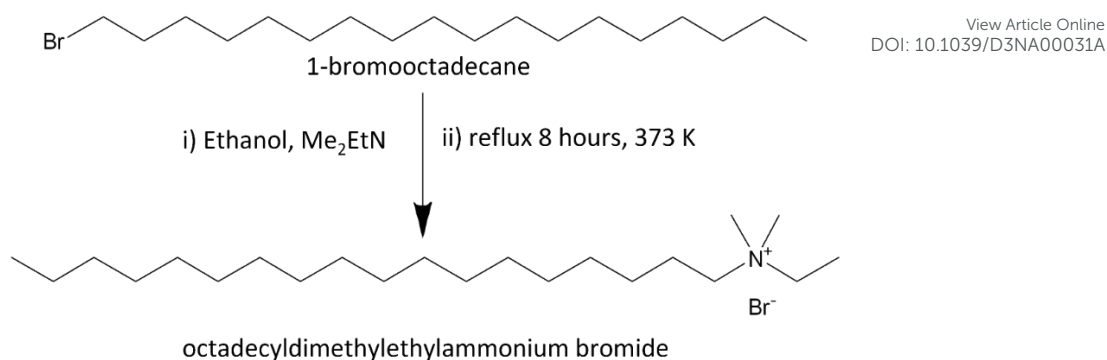

Scheme 1 The reaction used to produce octadecyldimethylethylammonium bromide surfactant, C₁₈DMEAB. The same method was used for the C₁₈DEMAB and C₁₈TEAB surfactants.

All ¹H and ¹³C{¹H} NMR spectra for surfactants C₁₈DMEAB and C₁₈TEAB in D-chloroform and C₁₈DEMAB in D₄-methanol were run on a Bruker AV11-400 spectrometer at 25 °C. Solutions used for mass spectrometry analysis were prepared by dissolving 50 μg of surfactant in 1 ml of methanol. Ultrahigh performance liquid chromatography (UHPLC) coupled to a TQD mass tandem quadrupole mass spectrometer (Waters) with a TUV detector at 254 nm was used to analyse the surfactants. A Waters BEH C18 column (50 mm x 2.1 mm, 1.7 μm) with a flow rate of 0.6 ml/min was used for the chromatography. The mobile phase was 0.2 % formic acid in an aqueous solution and 0.2 % formic acid in acetonitrile. The mass spectrum in the positive ion electrospray ionisation mode was used for the data analysis of surfactants.

C₁₈DMEAB. ¹H NMR (CDCl₃): δ/ppm 0.81 (t, CH₃, [3H]), 1.17-1.39 (br s, CH₂, [33H]), 1.61-1.71 (m, CH₂, [2H]), 3.32 (s, CH₃, [6H]), 3.42-3.50 (m, CH₂, [2H]), 3.66 (q, CH₂, [2H]). ¹³C{¹H} NMR (CDCl₃): δ/ppm 8.57, 14.05, 22.61, 22.72, 26.24, 29.18, 29.28, 29.34, 29.41, 29.53, 29.58, 29.61, 29.63, 31.85, 32.78, 34.02, 50.64, 59.35, 63.46, 76.85, 77.17, 77.49. MS (ESI⁺ in CH₃OH): found *m/z* = 326.6; required for {C₂₂H₄₈N⁺}: *m/z* = 326.

C₁₈DEMAB. ¹H NMR (CDCl₃): δ/ppm 0.81 (t, CH₃, [3H]), 1.02-1.46 (br s, CH₂, [36H]), 1.61-1.75 (m, CH₂, [2H]), 2.96 (s, CH₃, [3H]), 3.14-3.25 (m, CH₂, [2H]), 3.3 (q, CH₂, [4H]). ¹³C{¹H} NMR (CDCl₃): δ/ppm 8.81, 14.09, 22.39, 22.66, 26.40, 28.15, 29.33, 29.39, 29.42, 29.45, 29.48, 29.52, 29.58, 29.63, 31.90, 32.83, 34.04, 56.62, 60.62, 76.76, 77.08, 77.40. MS (ESI⁺ in CH₃OH): found *m/z* = 340.6; required for {C₂₃H₅₀N⁺}: *m/z* = 340.

C₁₈TEAB. ¹H NMR (CDCl₃): δ/ppm 0.81 (t, CH₃, [3H]), 1.11-1.46 (br s, CH₂, [36H]), 1.29-1.41 (m, CH₃, [3H]), 1.78 (m, CH₂, [2H]), 3.28 – 3.48 (m, CH₂, [8H]). ¹³C{¹H} NMR (CDCl₃): δ/ppm 8.15, 14.11, 22.13, 22.69, 26.55, 28.19, 28.77, 29.17, 29.36, 29.41, 29.44, 29.55, 29.59, 29.62, 29.66, 29.69, 31.93, 32.86, 34.02, 53.64, 57.65, 76.72, 77.03, 77.35. MS (ESI⁺ in CH₃OH): found *m/z* = 354.6; required for {C₂₄H₅₂N⁺}: *m/z* = 354.



Growth of mesoporous silica on indium-tin oxide electrodes

View Article Online
DOI: 10.1039/D3NA00031A

The silica films were prepared on transparent indium-tin oxide (ITO) electrode using the EASA method previously reported by Goux et al.²⁵ The sol electrolyte prepared from a 0.1 mol dm⁻³ sodium nitrate (0.1700 g, 2.00 mmol, >97 %, Timstar Laboratory Suppliers Ltd) solution in 20 cm³ water and 20 cm³ ethanol, to which tetraethylorthosilicate (TEOS, 98 %, Sigma Aldrich, 905 μL) and C₁₈TAB (0.4801 g, 1.22 mmol) was added. The pH was adjusted to 3 using 0.2 mol dm⁻³ HCl in water and the sol was then hydrolysed for 2.5 h with stirring at 25 °C. For C₁₈DMEAB (0.4801 g, 1.18 mmol), the ethanol component was replaced with 20 cm³ isopropyl alcohol to dissolve the surfactant at room temperature. When using C₁₈DEMAB (0.4801 g, 1.14 mmol) and C₁₈TEAB (0.4801 g, 1.10 mmol), in addition to using isopropyl alcohol it was necessary to increase the temperature to 40 °C to fully dissolve the surfactants.

The electrochemical cell for silica depositions consisted of a Teflon vessel with a 15 mm × 20 mm ITO-coated glass (surface resistivity = 14-16 Ω⁻¹, Ossila), stainless steel cone counter electrode and a silver rod pseudo reference electrode. A constant potential of -1.25 V vs. Ag/Ag⁺ was applied for a duration of 20 sec. using a Biologic SP150 potentiostat. The silica films were quickly washed with water and ethanol after each deposition, then placed in a drying oven at 130 °C for 16 h. The surfactants were removed by washing the films in a solution of 0.2 mol dm⁻³ HCl/ethanol for 15 mins.

Film characterisation

Cyclic voltammetry (CV) was used to examine pore accessibility of a range of mesoporous silica films on transparent ITO electrodes using redox active molecules. For CV measurements, an aqueous solution of 0.5 mmol dm⁻³ potassium hexacyanoferrate(III) ([Fe(CN)₆]³⁻) and 0.1 mol dm⁻³ NaNO₃ supporting electrolyte was used. The working electrode was a silica/ITO coated film, the counter electrode was a platinum gauze, and the reference was Ag/AgCl in 4 mol dm⁻³ KCl solution.

Electrochemical impedance spectroscopy (EIS) data were recorded with a frequency range from 250 kHz to 100 mHz with a perturbation amplitude of 10 mV.

All grazing incidence small angle X-ray scattering (GISAXS) measurements were carried out using a Rigaku Smartlab X-ray diffractometer coupled with an incidence angle of 0.25° using a Hypix 2D detector and a copper K_α source. 1D patterns were recorded in-plane with 0.5° incident and 0.228° exit slitter slits over a 2θ range of 1-10°. Scanning electron microscopy (SEM) images were recorded with a Jeol JSM-6500F and JSM-7200F with a 5 kV accelerating voltage. Scanning transmission electron microscopy (STEM) images of the mesoporous silica films were recorded using a JEOL ARM200F double-corrected TEM operated at 200 kV. TEM specimens were prepared by scraping the



silica films off the substrate and suspending them on lacey carbon films. The TEM specimens were tilted during the TEM observations to allow for the establishment of an edge-on condition for some silica flakes (the pores directly facing the electron beam), when the size and the arrangements of the pores are clearly revealed.

Ellipsometric porosimetry (EP) experiments were performed using a dynamic vapour sorption (DVS) instrument (Surface Measurement Systems Ltd., UK) coupled with a FS-1 multi-wavelength ellipsometer (Film Sense, USA). The toluene vapour sorption experiments were carried out in an environmental chamber at a fixed temperature of 25 °C, at atmospheric pressure and a solvent partial pressure range between 0-95% P/P₀. The partial pressure was maintained using mass-flow controllers operating in closed-loop mode using dry air as the carrier gas with a flow rate of 100 mL/min and the partial pressure monitored using a speed of sound sensor. The ellipsometer uses four wavelengths (465, 525, 595 and 635 nm) at an angle of incidence of approximately 65°, to produce the highest possible signal intensity in the detector. The mesoporous silica films were exposed to toluene in fixed partial pressure steps ranging between 0.5-5% for 20 mins. per step to reach equilibrium, and the refractive index was continuously measured to produce isotherms.

Results and discussion

We investigated the impact of substituting one or more of the methyl groups on C₁₈TAB for ethyl groups to determine whether increasing the head size would affect the pore growth/arrangements in EASA silica films and the electrochemistry of redox molecules in the presence of such films. Films were characterised with a range of analytical techniques such as cyclic voltammetry, electrochemical impedance spectroscopy, GISAXS, electron microscopy and ellipsometric porosimetry.

Pore structure and characterisation of EASA films


The surfactant chain length was kept constant at 18 carbons as the hydrophilic head was substituted with ethyl groups, thus steadily increasing the surfactant head size. The increase in head size also increased its hydrophobicity and reduced its solubility in the sol, so the sol composition was modified. The surfactant and TEOS concentrations were approximately 30 mmol dm⁻³ and 101 mmol dm⁻³ throughout, a surfactant:silica ratio of 0.3. As the solubility of the surfactant started to impede silica deposition with *P6mm* pore symmetry and vertical orientation, the water:ethanol ratio was varied, e.g. for C₁₈DMEAB 50: 50, 75: 25 and 15: 85 mixtures were tried. When this approach failed the water: ethanol mixture was replaced with water:isopropyl alcohol with a ratio of 50:50 and the desired ordered films were obtained. For C₁₈DEMAB and C₁₈TEAB, the 50:50 water: isopropyl alcohol-based sol required its temperature to be raised to 40 °C to achieve complete surfactant



dissolution and hence EASA films with the preferred structure and orientation. Depositions were carried out at an applied potential of -1.2 V for 20 seconds. Longer deposition times resulted in a build-up of silica spheres on the ITO surface due to condensation reactions in the bulk sol.^{19,25,18} The sol electrolyte was maintained at approximately 40 °C during depositions for the surfactants with ethyl rich head groups, and the resulting films were then cleared of silica by-products using deionized water and ethanol on the surface and dried. Surfactant was removed from the pores by soaking in a solution containing ethanol acidified with a little HCl.

In-plane GISAXS patterns (Fig. 1) were used to determine pore ordering and orientation in the silica films. All films were well-adhered, visually smooth, and free of any irregularities. The 1D in-plane scattering pattern for the silica film with C₁₈TAB revealed 10 (2.13°), 11 (3.71°), 20 (4.35°) and 21 (5.71°) reflections of highly ordered mesoporous silica with hexagonal nanopores (space group *P6mm*). This is characteristic of the hexagonal patterns of MCM silica materials,^{1,26} C_nTAB templated EASA films¹⁹ and hexagonal silica films produced by EISA.²⁷ The 10 reflection position corresponds to a d-spacing of 4.15 nm and a pore spacing of a_H = 4.80 nm for the film templated by C₁₈TAB. For the surfactant C₁₈DMEAB, the displacement of a single methyl group with ethyl from the cationic head group saw a significant shift in the 10 (2.02°), 11 (3.50°) and 20 (4.18°) diffraction peaks. The 10 of the EASA film with C₁₈DMEAB had a d-spacing of 4.40 nm resulting in a pore spacing of a_H = 5.10 nm. Campos et al²³ reported similar XRD features for the synthesis of mesoporous hybrid silica powders using cetyltrimethylammonium bromide. In addition to increasing the pore spacing, modifying the surfactant head resulted in reduced intensity and broadening of the 10 diffraction peak, suggesting a reduction in hexagonal pore order for the silica film templated by C₁₈DEMAB. The silica film containing C₁₈TEAB gave rise to a disordered film, as indicated by the 1D GISAXS pattern shown in Fig. 1. A significant reduction in the peak intensity of the 10 diffraction peak and the absence of 11, 20 and 21 peaks were evident, suggesting a loss in the ordering of pores.



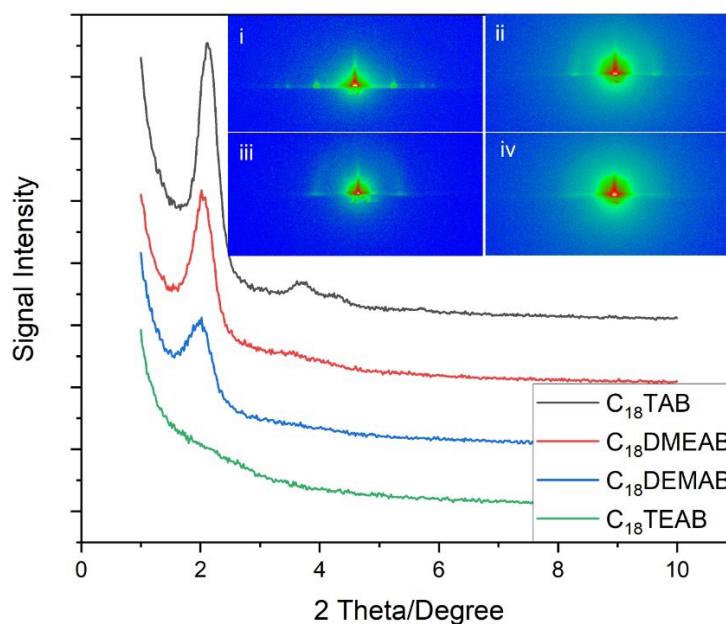

View Article Online
DOI: 10.1039/D3NA00031A

Figure 1. 1D in-plane GISAXS patterns of EASA films produced with $C_{18}TAB$, $C_{18}DMEAB$, $C_{18}DEMAB$ and $C_{18}TEAB$ at a potential of -1.25 V (vs. Ag/Ag^+) for 20 s on ITO electrodes (inset: 2D GISAXS images of EASA films templated by (i) $C_{18}TAB$, (ii) $C_{18}DMEAB$, (iii) $C_{18}DEMAB$ and (iv) $C_{18}TEAB$).

The 2D GISAXS in the inset of Fig. 1 (i) clearly reveals well-defined diffraction spots in the horizontal plane corresponding to the 10, 11 and 20 reflections of the EASA film with $C_{18}TAB$ after removal of surfactant. The position of these spots demonstrates that the pores are aligned vertical to the plane of the substrate. Out of plane features or rings are not observed in the 2D pattern. Previous reports have linked the appearance of rings to the build-up of silica spheres on the electrode surface.^{19,25} The 2D diffraction images in the insets to Fig. 1 (ii), (iii) and (iv) show EASA films templated by $C_{18}DMEAB$, $C_{18}DEMAB$ and $C_{18}TEAB$, respectively. These spots also suggest that the films have pores oriented vertically to the surface. The 10 Bragg spots drop in intensity as the surfactant head size increases, and long range order also decreases, as evidenced by the loss of the higher order diffraction spots. Additional rings of low intensity are seen for the films with $C_{18}DMEAB$ and $C_{18}DEMAB$, which become intense at longer deposition times. Such rings from EASA films with $C_{16}TAB$, $C_{22}TAB$ and $C_{24}TAB$ have previously been attributed to the presence of silica spheres on the surface of the film after formation in the bulk solution.^{25,19}

There are two ways to remove the surfactant template either by washing in an acidic alcoholic bath or calcination. The former method was applied and the resulting porous silica films were characterised by SEM (Fig. 2). The top view SEM images of each film show good surface coverage with no signs of microcracks or poor adhesion. The estimated film thickness for the EASA film with



C_{18} TAB was 125 nm as determined by SEM and was found to be similar to the other EASA films. The silica aggregates noted above that result in diffraction rings are visible on the surface of the films.

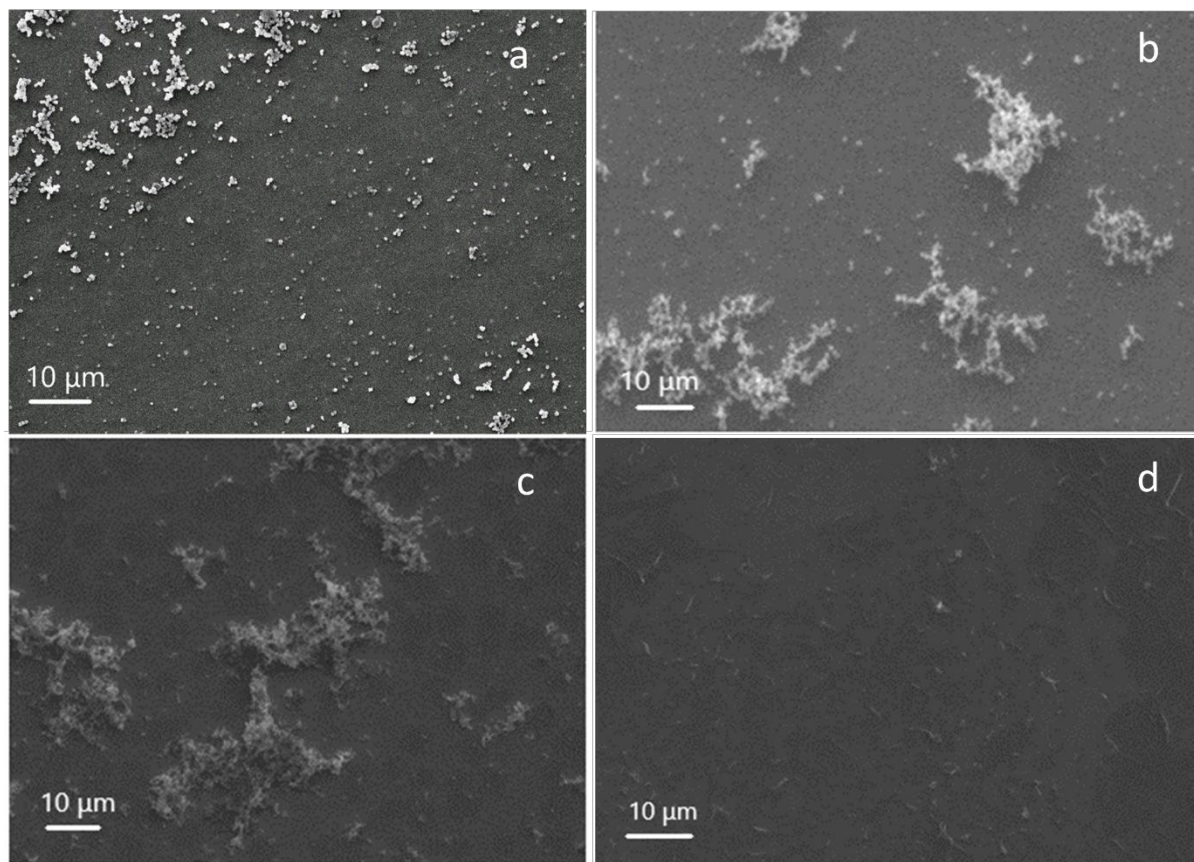


Figure 2. Top view SEM images of EASA films with (a) C_{18} TAB, (b) C_{18} DMEAB, (c) C_{18} DEMAB and (d) C_{18} TEAB deposited at an applied potential of -1.25 V (Ag/Ag^+) for 20 s on ITO electrodes.

TEM images were taken by stripping small sections of film from the ITO surface to investigate the mesoporous structure. The GISAXS data (Fig. 1) had suggested a gradual loss of hexagonal organisation with increasing head group size. The TEM images in Fig. 3 show that the C_{18} TAB produced film had a highly organised hexagonal structure of mesopores. As the surfactant head size increases, the hexagonally ordered domains become smaller with C_{18} DMEAB. With C_{18} DEMAB and C_{18} TEAB, further loss in pore ordering is observed, which correlates with the GISAXS data in Fig. 1. It should be noted that the GISAXS confirms that all films possess vertically-oriented pores, it is only the hexagonal ordering that is lost in comparison to the film with C_{18} TAB. Loss of order with increasing cationic surfactant head size has been linked to repulsions between the larger surfactant head groups causing steric hinderance to occur slowing down the process of micellization as a result of fewer bromide counterions condensing in the vicinity of the micelle.^{13,28} Film formation occurs below the critical micellar concentration (CMC) which is stated to be around 30 mmol dm^{-3} for CTAB



in a sol electrolyte with 50:50 water: ethanol.^{25,29} This provides evidence that the surfactant template does not self-assemble in the desired hexagonal arrangement in the sol, it is the electric field which drives the interaction between positively charged surfactant molecule and the negatively charged ITO electrode. In turn, this favours the formation of hemimicelles (in its hexagonal shape) and induces silica condensation and hence SiO₂ film formation with vertical pores. We are currently working below the CMC for this reason, so knowledge of the CMC is less critical here than it would be in a “typical” sol-gel study.


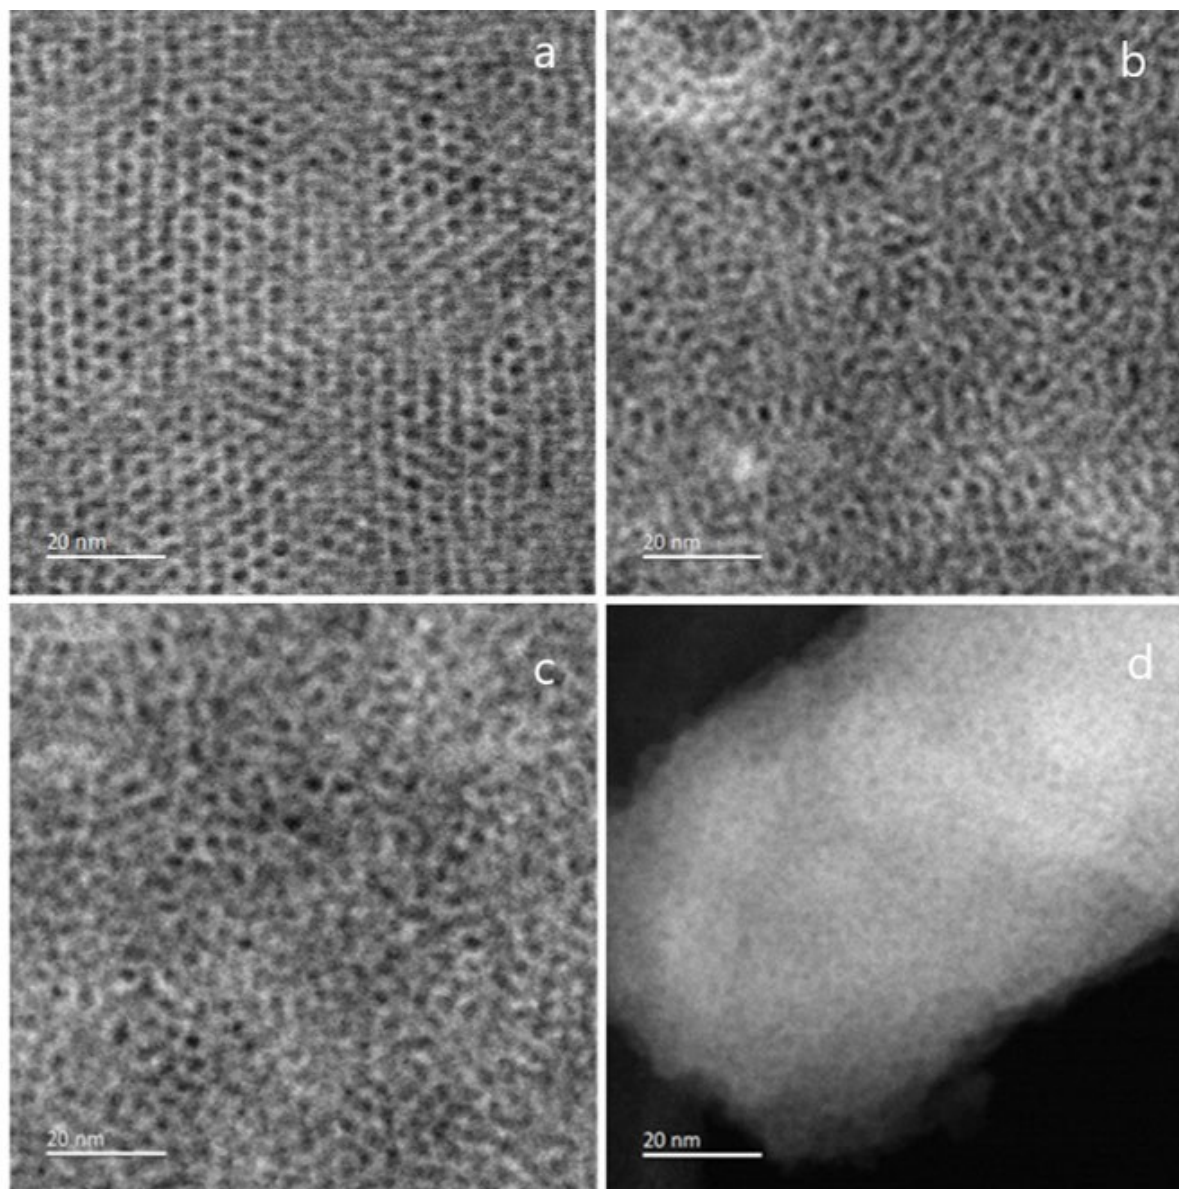


Figure 3. TEM images of mesoporous silica films generated with (a) C₁₈TAB, (b) C₁₈DMEAB, (c) C₁₈DEMAB and (d) C₁₈TEAB deposited at -1.25 V (vs. Ag/Ag⁺) for 20 s on ITO electrodes.



*Electrochemical characterisation of the films*View Article Online
DOI: 10.1039/D3NA00031A

Pore transit measurements were carried out for a range of EASA films using an anionic probe molecule, a $0.5 \text{ mmol dm}^{-3} [\text{Fe}(\text{CN})_6]^{3-/4-}$ in a solution also containing $0.1 \text{ mol dm}^{-3} \text{ NaNO}_3$ as the background electrolyte. These investigations were undertaken to determine whether the effect of increasing the surfactant head size would influence the ability of ions to move through the pores. The electrochemical reduction and oxidation of ferricyanide is shown in Eq 1.



Upon extracting the film's surfactant, a drop in peak current in the CVs and a large peak to peak separation is most likely due to electrostatic repulsions between the anionic molecule and silanol groups attached to the silica pore walls, which could be associated with the Donnan exclusion effect³⁰ which is seen for ionically charged regions in semi-permeable membranes (as shown in the supplementary information, Table S1).³¹ The peak current for the film produced with C_{18}TAB (Fig 4a) was similar to that of bare ITO (shown in Fig. 4a inset), but that with $\text{C}_{18}\text{DMEAB}$ was significantly lower. Films with $\text{C}_{18}\text{DEMAB}$ and C_{18}TEAB reveal no faradaic current with the voltammograms adopting a rectangular shape, exhibiting capacitive behavior³² as well as resembling the films with blocked pores before removal of surfactant.^{33,34} GISAXS experiments were carried out before and after surfactant elimination to provide further evidence that the mesopores were indeed open for the film with $\text{C}_{18}\text{DEMAB}$ prior to CV studies (Fig. S10). The featureless 1D GISAXS pattern indicates the presence of surfactant filled pores within the silica film however, after surfactant removal, a broad 10 reflection is noticed, suggesting that the surfactant has largely been removed from the pores. As the films' hexagonal pore order reduces due to the bulkier surfactant heads, a curtailment of the mass transport properties is found. This suggests the less ordered films have closed pores.

respond to the final reviewer comment? The featureless GISAXS before surfactant removal and a good 10 reflection after removal seem to show the pores being opened up. Would you be able to think about how to incorporate this message in the manuscript?



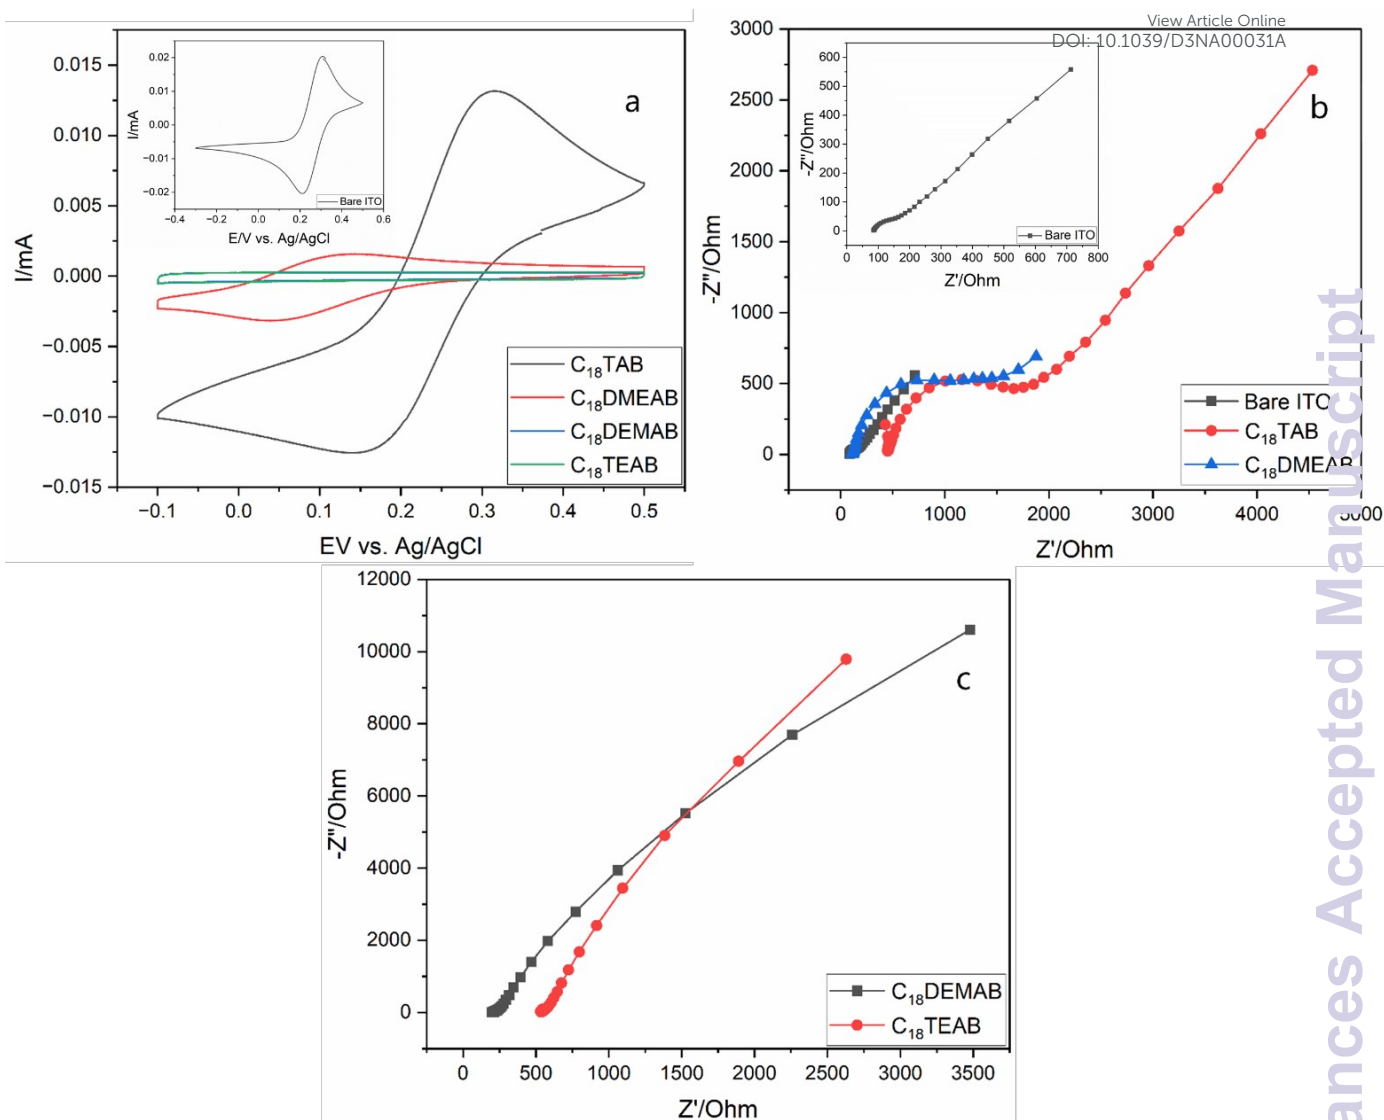


Figure 4. Cyclic voltammograms (a) (20 mV s^{-1} sweep rate) of $0.5 \text{ mmol dm}^{-3} [\text{Fe}(\text{CN})_6]^{3-/4-}$ in $0.1 \text{ mol dm}^{-3} \text{ NaNO}_3(\text{aq})$ on bare ITO electrode (inset). The mesoporous silica films using C₁₈TAB (black line), C₁₈DMEAB (red line), C₁₈DEMAB (blue line) and C₁₈TEAB (green line) as the surfactants were deposited at -1.25 V (vs. Ag/Ag^+) for 20 s on ITO electrodes. Nyquist plots (Fig. 4b) of bare ITO (inset) and mesoporous silica films on ITO electrodes with C₁₈TAB and C₁₈DMEAB as the surfactant templates, whereas Nyquist plots (Fig. 4c) of mesoporous silica films on ITO electrodes with C₁₈DEMAB and C₁₈TEAB as the surfactant templates. All experiments were carried out after surfactant removal.

EIS was employed to further characterise the EASA films produced with the various head groups (Fig 4b and 4c). The Nyquist plots were carried out in the same redox probe molecule solution as the pore transit measurements described above. The EIS plots can be simulated using a simple Randles equivalent circuit where R_s , R_{ct} and C_{dl} are the electrolyte resistance, charge transfer resistance and



double layer capacitance. The Nyquist plots of C₁₈TAB and C₁₈DMEAB produced silica films contain a semicircle in the high frequency region and a straight line with a 45° phase angle due to the Warburg impedance (Z_w). Previous works have shown that mass transport of redox-active molecules through porous silica films is governed by diffusion processes.^{19,12,25} Therefore, the charge transfer resistance (R_{ct}) is highly dependent on the number of open pores available for ion transport and ionic charge from redox active molecules. Fitting to the Randles circuit revealed a R_{ct} of bare ITO of 144.0 Ω, which was lower than the R_{ct} of 416.6 Ω and 830.2 Ω obtained in films produced by C₁₈TAB and C₁₈DMEAB, showing higher conductivity for the transparent electrode. The incorporation of two or three ethyl groups attached to the surfactant's hydrophobic tail resulted in much larger and imperfect semicircles (Fig. 4b and c), suggesting poorer pore accessibility of the redox active ion, [Fe(CN)₆]^{3-/4-} transporting through the silica films than that seen with the C₁₈TAB and C₁₈DMEAB films. Moreover, despite the increased pore spacing and possible pore expansion found in C₁₈DMEAB produced film, the R_{ct} value is higher than for C₁₈TAB due to pore disorder and limited number of available pores present which hinder the diffusion of redox molecules within the silica pore channels. The EIS data agree with those from the CVs, presenting further evidence that the reducing pore order with increasing head size is accompanied by loss of access to the electrode surface.

Ellipsometric porosimetry measurements of EASA films on ITO electrodes

Ellipsometric porosimetry (EP) is used to determine the porous structure of thin films deposited onto a solid substrate. Sorption isotherms, and hence pore size distribution and the open pore volume fraction, can be determined from the changes in refractive index of the film (Fig. 5). These changes are monitored by the film's exposure to toluene, which continuously condenses/adsorbs within the porous network. The high boiling point of toluene means that it easily condenses in the pores at relatively low partial pressure compared with highly polar solvents such as water.

In Fig. 5b the isotherm for the film templated with C₁₈DMEAB shows a substantial initial uptake of toluene, with a minor step noticeable between 0.05 and 0.12 P/P₀, and plateaus at around 0.175 P/P₀. The adsorption/desorption process is also completely reversible with no significant hysteresis present, indicating the absence of any capillary condensation within the pores. The shape and characteristics of this isotherm is best described as a mix of type I (b) and type IV (b), with mixed monolayer-multilayer formation and micro-mesopore filling occurring up to the saturation.³⁵ The plateau increases constantly until 0.95 P/P₀, which does suggest some minor heterogeneity in the mesoporosity is present, as noticed in the pore size reduction after the peak in the pore size distribution (PSD). Both the adsorption and desorption branches of the PSD agree, with the latter branch having a peak pore size of around 3.42 nm (shown in Fig. 5b inset), which is larger than the



peak pore size of the silica film with C_{18} TAB at 3.24 nm (shown in Fig. 5a inset), determined from the desorption isotherm.¹⁹ The shape of this isotherm is common with templated porous materials with large micropores and small mesopores. Previous work on silica thin films templated by C_n TAB^{36,19} has shown similar isotherms in the presence of toluene.

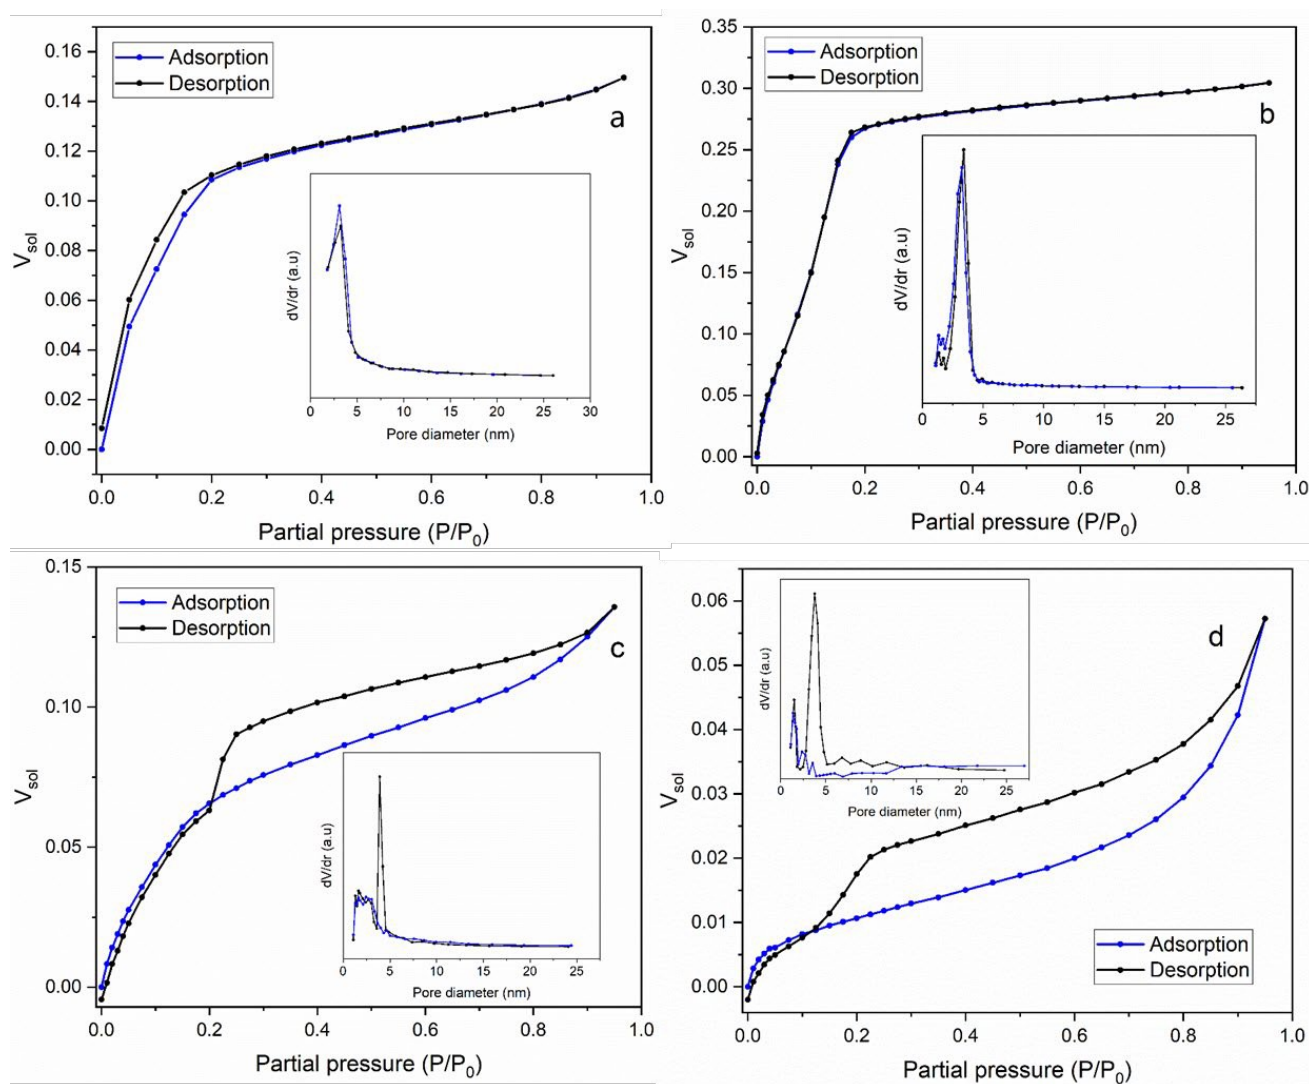


Figure 5. The adsorption/desorption isotherms of EASA films produced using (a) C_{18} TAB (Mohamed et al.¹⁹), (b) C_{18} DMEAB, (c) C_{18} DEMAB and (d) C_{18} TEAB surfactants using toluene as the adsorptive. The pore size distribution curves are shown in the insets.

In the film templated by C_{18} DEMAB (Fig. 5c), the isotherm initially shows broad adsorption of toluene from low partial pressures up to 0.2 P/P_0 , followed by a constant increase up to 0.8 P/P_0 and ends with a minor inflection point. The desorption branch of the isotherm shows large hysteresis, implying that capillary condensation has occurred in the mesopores, and there is a significant drop in V_{sol} between 0.25 and 0.2 P/P_0 . The broad uptake of vapour at the lower end of partial pressures in the adsorption branch is a typical characteristic of overlapping monolayer formation and multilayer sorption



occurring, in this case happening at a much more significant level than the other films. This is a consequence of the film having a wide PSD range, rather than a sharp one, particularly within the larger micropore and narrow mesopore range. This can be seen in the adsorption branch of the PSD plot as a broad peak going up to 4-5 nm in addition to showing a gradual decrease in pore volume towards larger values. The shape of the isotherm best matches that of a mix between type I (b) and type II, with a type H4 hysteresis loop.³⁵ The drop in V_{sol} in the desorption branch of this sample is a distinctive feature in this type of loop, which can be caused by the sample experiencing some degree of pore blockage or cavitation due to reduced porosity, pore size and pore geometry.³⁷ This can happen, for example, when the larger pores in the structure have narrow entries or have neighbouring pores which are smaller in size, where the entry diameter generally dictates if pore blockage or cavitation will occur. A challenge with this phenomenon is that the sharp peak in the PSD of the desorption branch at 3.90 nm (Fig. 5c inset) could be an artifact due to the rapid desorption of the adsorbate because of the pore structure as opposed to the pore size, as described in a previous review.³⁸ Therefore, for clarity, both the adsorption and desorption branches of the PSD are included in the plot, where they are in good agreement with each other except for the peak.

For the film templated by $C_{18}TEAB$ (Fig. 5d), the adsorption branch uptake shows clearer distinction between pore filling, monolayer coverage, and multilayer adsorption/condensation, like a type II isotherm. There is more uptake at higher partial pressure than lower ones, implying that there is more volume contribution from larger pores and voids. This is also seen in the PSD as there are multiple broad peaks present with low dV/dr at larger pore sizes. Although, the toluene volume fraction values are quite low for this sample, with a saturation V_{sol} of 5.73% at 95% P/P_0 , indicating low pore accessibility. The desorption branch shows significant hysteresis, with a rapid drop visible between 0.225 and 0.125 P/P_0 , and a shift towards lower partial pressures with a wider range. This is a similar phenomenon to $C_{18}DEMAB$, that can cause an artificial peak in the desorption PSD, in this case at around 3.76 nm (Fig. 5d inset), which is larger than the peak pore sizes of 3.24 and 3.42 nm for $C_{18}TAB$ ¹⁹ and $C_{18}DMEAB$ films (Fig 5a and b insets). However, there is a smaller peak present in the adsorption branch at around 3.53 nm (Fig 5d inset), which implies there is some distribution of pores at that size and not completely artificial. Even though the film has been prepared with a surfactant of larger head group, a shift to lower partial pressures in the drop range can imply a decreasing cavity diameter.³⁹ At the same time, a more gradual drop in the range can indicate enlargement of necks/connected pores, which would mean that pore blockage is more likely occurring rather than cavitation.⁴⁰ The shape and hysteresis of the isotherm resembles more of that with a type H3 hysteresis loop rather than type H4 for $C_{18}DEMAB$, where there is less volume uptake at lower partial pressures due to lower micropore availability.³⁵ The PSD shows quite some pore size heterogeneity, with other peaks also at smaller sizes



visible in the adsorption branch, around 1.58 and 2.36 nm, although the BJH method is not very accurate at calculating the size of micropores. Both C₁₈TEAB and C₁₈DEMAB show some degree of hierarchical pore sizes and do not necessarily have very ordered structure. Isotherms of these shapes and pore blocking/cavitation phenomena have been associated with a range of ordered and disordered porous materials such as clays, sandstones, zeolites, and other silica-based materials.³⁷

Conclusions

A series of surfactants based on C₁₈TAB with increasing numbers of ethyl groups replacing the usual methyl ones were used to synthesise vertically aligned mesoporous silica films by the electrochemically assisted self-assembly method. A gradual reduction in the pore order was observed as the surfactant head size grew, but alignment of the pores remained vertical. Introducing one ethyl group, an increase in the lattice spacing and pore size was observed without a significant reduction in hexagonal pore arrangement relative to the film produced with C₁₈TAB. Resistance to transit of redox active species through the film did increase, however. No faradaic current was observed for films templated with surfactants with two or three ethyl groups, and pore order was also reduced (while again retaining vertical pore orientation). Ellipsometric porosimetry confirmed that the pore diameter of the silica films increased with increasing head group size, although accessible pore volume also decreased.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was carried out under the Advanced Devices by ElectroPlating (ADEPT) EPSRC programme grant (EP/N035437/1). The authors also thank EPSRC for funding the Smartlab diffractometer under EP/K00509X/1 and EP/K009877/1, and Dr Li Shao for collection of some of the GISAXS patterns.

References

- 1 J. S. Beck, J. C. Vartuli, W. J. Roth, M. E. Leonowicz, C. T. Kresge, K. D. Schmitt, C. T. W. Chu, D. H. Olson, E. W. Sheppard, S. B. McCullen, J. B. Higgins and J. L. Schlenker, A New Family of Mesoporous Molecular Sieves Prepared with Liquid Crystal Templates, *J. Am. Chem. Soc.*, 1992, **114**, 10834–10843.
- 2 J. C. Vartuli, C. T. Kresge, M. E. Leonowicz, A. S. Chu, S. B. McCullen, I. D. Johnson and E. W. Sheppard, Synthesis of Mesoporous Materials : Liquid-Crystal Templating versus Intercalation of Layered Silicates, *Chem. Mater.*, 1994, **6**, 2070–2077.
- 3 M. J. Climent, A. Corma, S. Iborra, M. C. Navarro and J. Primo, Use of mesoporous MCM-41



aluminosilicates as catalysts in the production of fine chemicals: Preparation of dimethylacetals, *J. Catal.*, 1996, **161**, 783–789.

View Article Online
DOI: 10.1039/D3NA00031A

- 4 S. V. Sirotin, I. F. Moskovskaya and B. V. Romanovsky, Synthetic strategy for Fe-MCM-41 catalyst: A key factor for homogeneous or heterogeneous phenol oxidation, *Catal. Sci. Technol.*, 2011, **1**, 971–980.
- 5 M. Hasanzadeh, N. Shadjou, M. de la Guardia, M. Eskandani and P. Sheikhzadeh, Mesoporous silica-based materials for use in biosensors, *TrAC - Trends Anal. Chem.*, 2012, **33**, 117–129.
- 6 T. Nasir, G. Herzog, M. Hébrant, C. Despas, L. Liu and A. Walcarius, Mesoporous Silica Thin Films for Improved Electrochemical Detection of Paraquat, *ACS Sensors*, 2018, **3**, 484–493.
- 7 S. Bhattacharyya, G. Lelong and M. L. Saboungi, Recent progress in the synthesis and selected applications of MCM-41: A short review, *J. Exp. Nanosci.*, 2006, **1**, 375–395.
- 8 J. Wu, A. F. Gross and S. H. Tolbert, Host-guest chemistry using an oriented mesoporous host: Alignment and isolation of a semiconducting polymer in the nanopores of an ordered silica matrix, *J. Phys. Chem. B*, 1999, **103**, 2374–2384.
- 9 T. Abe, Y. Tachibana, T. Uematsu and M. Iwamoto, Preparation and characterization of Fe₂O₃ nanoparticles in mesoporous silicate, *J. Chem. Soc. Chem. Commun.*, 1995, 1617–1618.
- 10 P. N. Bartlett, R. Beanland, J. Burt, M. M. Hasan, A. L. Hector, R. J. Kashtiban, W. Levason, A. W. Lodge, S. Marks, J. Naik, A. Rind, G. Reid, P. W. Richardson, J. Sloan and D. C. Smith, Exploration of the Smallest Diameter Tin Nanowires Achievable with Electrodeposition: Sub 7 nm Sn Nanowires Produced by Electrodeposition from a Supercritical Fluid, *Nano Lett.*, 2018, **18**, 941–947.
- 11 J. Ke, W. Su, S. M. Howdle, M. W. George, D. Cook, M. Perdjon-Abel, P. N. Bartlett, W. Zhang, F. Cheng, W. Levason, G. Reid, J. Hyde, J. Wilson, D. C. Smith, K. Mallik and P. Sazio, Electrodeposition of metals from supercritical fluids, *Proc. Natl. Acad. Sci. U. S. A.*, 2009, **106**, 14768–14772.
- 12 A. Walcarius, Mesoporous materials and electrochemistry, *Chem. Soc. Rev.*, 2013, **42**, 4098–4140.
- 13 H. Lin and S. Cheng, Effect of delayed neutralization on the synthesis of mesoporous MCM-41 molecular sieves, *Microporous Mater.*, 1997, **10**, 111–121.
- 14 R. Ryoo, C. H. Ko and I. Park, Synthesis of highly ordered MCM-41 by micelle-packing control with mixed surfactants, *Chem. Commun.*, 1999, 1413–1414.
- 15 C. J. Brinker, Evaporation-induced self-assembly: Functional nanostructures made easy, *MRS Bull.*, 2004, **29**, 631–640.
- 16 D. Zhao, P. Yang, D. I. Margolese, F. Chmelka and G. D. Stucky, Synthesis of continuous mesoporous silica thin films with three-dimensional accessible pore structures, *Chem. Commun.*, 1998, **1**, 2499–2500.
- 17 Z. Teng, G. Zheng, Y. Dou, W. Li, C. Y. Mou, X. Zhang, A. M. Asiri and D. Zhao, Highly ordered mesoporous silica films with perpendicular mesochannels by a simple stöber-solution growth approach, *Angew. Chemie - Int. Ed.*, 2012, **51**, 2173–2177.



- 18 A. Walcarius, E. Sibottier, M. Etienne and J. Ghanbaja, Electrochemically assisted self-assembly of mesoporous silica thin films, *Nat. Mater.*, 2007, **6**, 602–608. View Article Online
DOI: 10.1039/D3NA00031A
- 19 N. A. N. Mohamed, Y. Han, A. L. Hector, A. R. Houghton, E. Hunter-Sellars, G. Reid, D. R. Williams and W. Zhang, Increasing the Diameter of Vertically Aligned, Hexagonally Ordered Pores in Mesoporous Silica Thin Films, *Langmuir*, 2022, **38**, 2257–2266.
- 20 C. Robertson, R. Beanland, S. A. Boden, A. L. Hector, R. J. Kashtiban, J. Sloan, D. C. Smith and A. Walcarius, Ordered mesoporous silica films with pores oriented perpendicular to a titanium nitride substrate, *Phys. Chem. Chem. Phys.*, 2015, **17**, 4763–4770.
- 21 D. F. Rohlfiing, J. Rathouský, Y. Rohlfiing, O. Bartels and M. Wark, Functionalized mesoporous silica films as a matrix for anchoring electrochemically active guests, *Langmuir*, 2005, **21**, 11320–11329.
- 22 Y. Guillemin, J. Ghanbaja, E. Aubert, M. Etienne and A. Walcarius, Electro-assisted self-assembly of cetyltrimethylammonium-templated silica films in aqueous media: Critical effect of counteranions on the morphology and mesostructure type, *Chem. Mater.*, 2014, **26**, 1848–1858.
- 23 A. F. P. De Campos, A. R. O. Ferreira, L. Lorena, P. Paulo, M. Neto and D. Cardoso, Synthesis and properties of hybrid silicas containing alkylammonium surfactants, *Catal. Today*, 2020, **344**, 41–51.
- 24 H. A. Scheraga and J. K. Backus, Flow Birefringence in Solutions of n-Hexadecyltrimethylammonium Bromide, *J. Am. Chem. Soc.*, 1951, **73**, 5108–5112.
- 25 A. Goux, M. Etienne, E. Aubert, C. Lecomte, J. Ghanbaja and A. Walcarius, Oriented mesoporous silica films obtained by electro-assisted self-assembly (EASA), *Chem. Mater.*, 2009, **21**, 731–741.
- 26 S. Wang, D. Wu, Y. Sun and B. Zhong, The synthesis of MCM-48 with high yields, *Mater. Res. Bull.*, 2001, **36**, 1717–1720.
- 27 J. H. Pan and W. I. Lee, Derivation of Cubic and Hexagonal Mesoporous Silica Films by Spin-coating Derivation of Cubic and Hexagonal Mesoporous Silica Films by Spin-coating, *Bull. Korean Chem. Soc.*, 2005, **26**, 418–422.
- 28 N. V. Sastry, N. M. Vaghela and V. K. Aswal, Fluid Phase Equilibria Effect of alkyl chain length and head group on surface active and aggregation behavior of ionic liquids in water, *Fluid Phase Equilib.*, 2012, **327**, 22–29.
- 29 S. Besson, C. Ricolleau, T. Gacoin, C. Jacquiod and J. P. Boilot, Highly ordered orthorhombic mesoporous silica films, *Microporous Mesoporous Mater.*, 2003, **60**, 43–49.
- 30 C. Karman, N. Vilà and A. Walcarius, Amplified Charge Transfer for Anionic Redox Probes through Oriented Mesoporous Silica Thin Films, *ChemElectroChem*, 2016, **3**, 2130–2137.
- 31 S. Sarkar, A. K. Sengupta and P. Prakash, The Donnan membrane principle: Opportunities for sustainable engineered processes and materials, *Environ. Sci. Technol.*, 2010, **44**, 1161–1166.
- 32 K. Seok, L. Ye, J. Seo and H. Taek, Capacitive behavior of functionalized activated carbon - based all - solid - state supercapacitor, *Carbon Lett.*, 2021, **31**, 1041–1049.



- 33 T. Sikolenko, C. Despas, N. Vilà and A. Walcarius, Electrochemistry Communications, Thickness control in electrogenerated mesoporous silica films by wet etching and electrochemical monitoring of the process, *Electrochem. commun.*, 2019, **100**, 11–15. View Article Online
DOI: 10.1039/D3NA00031A
- 34 G. Giménez and G. Ybarra, Preparation of mesoporous silica thin films at low temperature : a comparison of mild structure consolidation and template extraction procedures, *J. Sol-Gel Sci. Technol.*, 2020, 287–296.
- 35 M. Thommes, K. Kaneko, A. V. Neimark, J. P. Olivier, F. Rodriguez-Reinoso, J. Rouquerol and K. S. W. Sing, Physisorption of gases, with special reference to the evaluation of surface area and pore size distribution (IUPAC Technical Report), *Pure Appl. Chem.*, 2015, **87**, 1051–1069.
- 36 C. Robertson, A. W. Lodge, P. Basa, M. Carravetta, A. L. Hector, R. J. Kashtiban, J. Sloan, D. C. Smith, J. Spencer and A. Walcarius, Surface modification and porosimetry of vertically aligned hexagonal mesoporous silica films, *RSC Adv.*, 2016, **6**, 113432–113441.
- 37 M. Thommes, Characterization of Nanoporous Materials, *Chemie Ing. Tech.*, 2010, **82**, 1059–1073.
- 38 C. Schlumberger and M. Thommes, Characterization of Hierarchically Ordered Porous Materials by Physisorption and Mercury Porosimetry — A Tutorial Review, *Adv. Mater. Interfaces*, 2021, **8**, 1–25.
- 39 C. J. Rasmussen, A. Vishnyakov, M. Thommes, B. M. Smarsly, F. Kleitz and A. V Neimark, Cavitation in Metastable Liquid Nitrogen Confined to Nanoscale Pores, *Langmuir*, 2010, **26**, 10147–10157.
- 40 T. Kim, R. Ryoo, M. Kruk, K. P. Gierszal and M. Jaroniec, Tailoring the Pore Structure of SBA-16 Silica Molecular Sieve through the Use of Copolymer Blends and Control of Synthesis Temperature and Time, *J. Phys. Chem. B*, 2004, **108**, 11480–11489.

