

Influence of Fluorinated Substituents on the Near-Infrared Phosphorescence of 5d Metallocorroles

Krister Engedal Johannessen, Martin Amund Langaas Johansen, Rune F. Einrem, Laura J. M^cCormick M^cPherson, Abraham B. Alemayehu,* Sergey M. Borisov,* and Abhik Ghosh*



Cite This: <https://doi.org/10.1021/acsorginorgau.3c00016>



Read Online

ACCESS |



Metrics & More




Article Recommendations



Supporting Information

ABSTRACT: The influence of fluorinated substituents on the luminescent properties of rhenium-oxo, osmium-nitrido, and gold triarylcorroles was studied via a comparison of four ligands: triphenylcorrole (TPC), tris(*p*-trifluoromethylphenyl)corrole (TpCF₃PC), tris{3,5-bis(trifluoromethyl)phenyl}corrole (T3,5-CF₃PC), and tris(pentafluorophenyl)corrole (TPFPC). For each metal series examined, fluorinated substituents were found to enhance the luminescent properties, with the phosphorescence quantum yields and triplet decay times increasing in the order TPC < TpCF₃PC < T3,5-CF₃PC < TPFPC. Among the 11 complexes examined, the highest phosphorescence quantum yield, 2.2%, was recorded for Re[TPFPC](O).

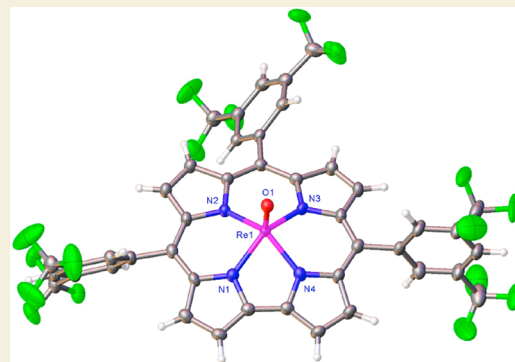


KEYWORDS: Fluorinated compounds, fluorous, corrole, phosphorescence, triplet photosensitizer, gold, rhenium

The last decade has witnessed the emergence of a unique class of transition metal complexes, the 5d metallocorroles.¹ Their uniqueness derives from their size-mismatched nature, which involves a large 5d ion encapsulated by a sterically constrained, macrocyclic corrole ligand.^{2–4} In spite of the steric strain inherent in their structures, the middle and late 5d transition metal (Re,^{5–8} Os,⁹ Ir,¹⁰ Pt,^{11,12} and Au^{13–20}) corroles have proved thermally and photochemically rugged. Furthermore, their photophysical properties are conducive to applications as photosensitizers, most notably in photodynamic therapy and oxygen sensing.^{21–33} Interestingly, in the course of our photophysical studies on 5d metallotriarylcorroles, we observed somewhat higher phosphorescence quantum yields for tris{(*p*-trifluoromethyl)phenyl}corrole complexes than for their more electron-rich counterparts.^{24,28–30} The observation made us wonder whether fluorinated substituents might have a beneficial effect on the luminescence properties of 5d metallocorroles. A photophysical study was accordingly carried out on the complexes depicted in Chart 1, except for the M = OsN, Ar = C₆F₅ case, which was not studied because of synthetic difficulties. We found that fluorinated substituents indeed appear to have a beneficial effect on the luminescence properties of the complexes, significantly increasing both the phosphorescence quantum yields and the triplet decay times.

The influence of fluorinated substituents on the luminescence properties of rhenium-oxo, osmium-nitrido, and gold triarylcorroles was studied via a comparison of four ligands: triphenylcorrole (TPC), tris(*p*-trifluoromethylphenyl)corrole

Chart 1. Molecules Studied in This Work

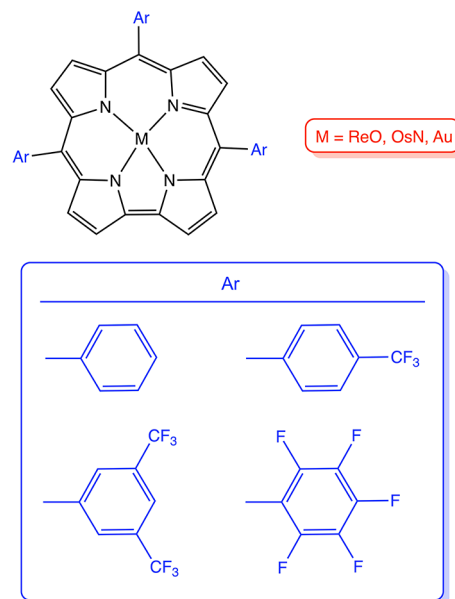

Received: May 2, 2023

Revised: July 3, 2023

Accepted: July 5, 2023

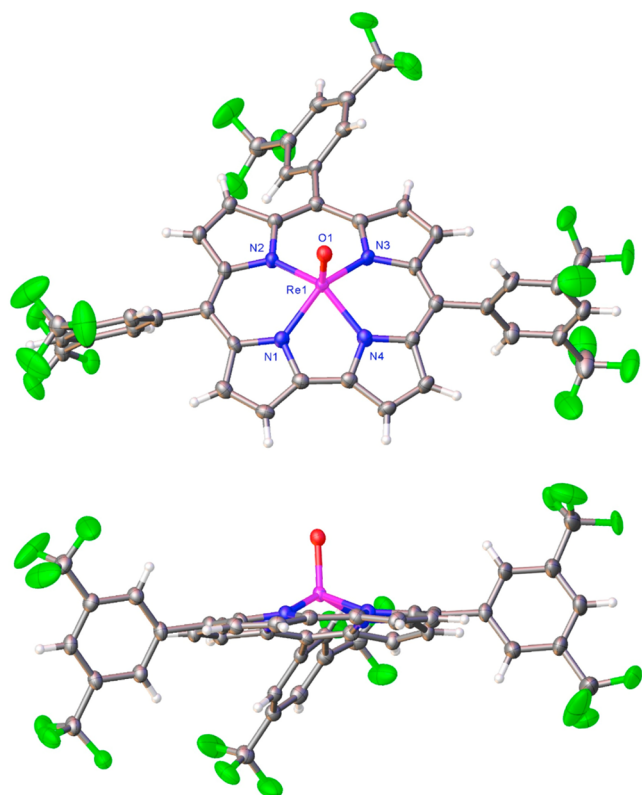


Figure 1. Two views of the thermal ellipsoid plot for Re[T3,5-CF₃PC](O) at 50% probability. Selected distances (Å): Re1–N1 1.992(3), Re1–N2 2.006(3), Re1–N3 2.015(3), Re1–N4 1.996(3), and Re1–O1 1.574(3) Å.

(TpCF₃PC), tris{3,5-bis(trifluoromethyl)}corrole (T3,5-CF₃PC), and tris(pentafluorophenyl)corrole (TPFPC). The majority of the compounds in question have been previously synthesized;^{5,9,15} four new compounds were synthesized specifically for this study, namely, Re[T3,5-CF₃PC](O), Os[T3,5-CF₃PC](N), Au[T3,5-CF₃PC], and Re[TPFPC](O). Unfortunately, Os[TPFPC](N) could not be synthesized because the azide used as part of the synthetic protocol resulted in nucleophilic displacement of the *para*-fluorines in the TPFPC ligand (consonant with multiple similar reactions in the literature^{34–36}). Aside from that, the syntheses of the new compounds proved uneventful, and one, Re[T3,5-CF₃PC](O), yielded a single-crystal X-ray structure (Figure

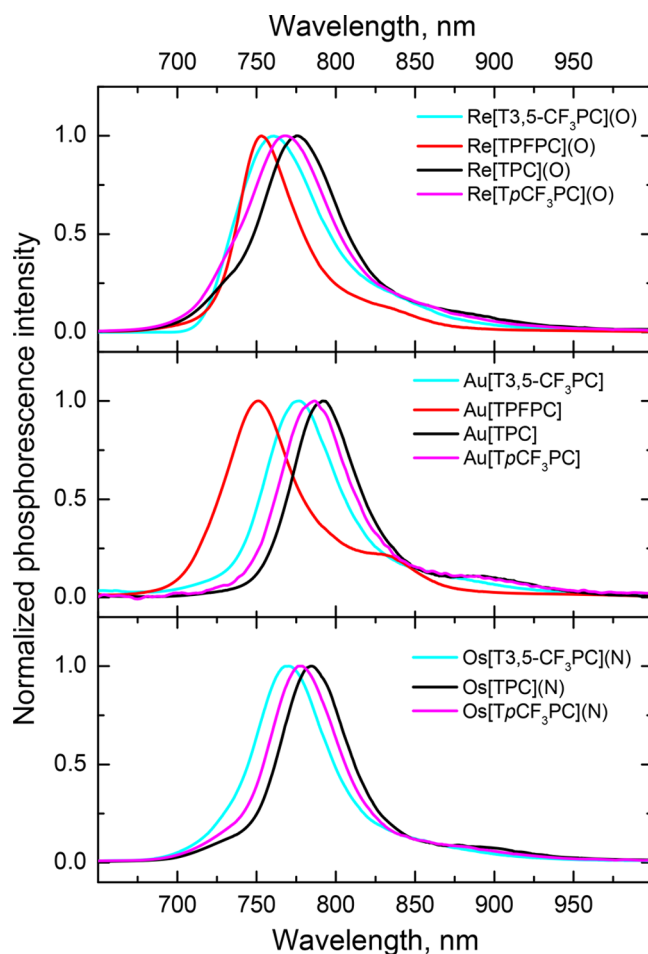


Figure 2. Emission spectra of the complexes in anoxic toluene at 23 °C. Excitation into the maximum of the Soret band of the complexes was performed.

1 and Table S1). Key photophysical and electrochemical properties of the compounds are listed in Table 1.

All of the complexes proved emissive in deoxygenated toluene at room temperature (Figure 2 and Table 1). The emission was efficiently quenched by molecular oxygen and is thus ascribed to phosphorescence. The absorption and excitation spectra (Figures S19–S23) proved virtually identical, indicating that the emission originates solely from the metal complexes while also confirming the purity of the

Table 1. Photophysical and Electrochemical Properties of ReO, OsN, and Au Triarylcorroles in Anoxic Toluene (23 °C)

complex	λ_{\max} abs, nm	λ_{\max} -phos (nm)	Φ_{phos} (%)	τ_{phos} (μs)	$E_{1/2,\text{ox1}}$ (V)	$E_{1/2,\text{red1}}$ (V)	$E_{1/2,\text{red2}}$ (V)	ref
Re[TPC](O)	440, 554, 586	776(770) ^a	1.2	60	0.98	−1.26		5, 29
Re[TpCF ₃ PC](O)	440, 553, 586	768(777) ^a	1.4 (1.5) ^a	74	1.10	−1.16		5, 29
Re[T3,5-CF ₃ PC](O)	440, 553, 586	760	1.6	75	1.21	−1.11	−1.64	this work
Re[TPFPC](O)	437, 552, 586	753	2.2	99	1.31	−1.04	−1.68	this work
Os[TPC](N)	444, 554, 595	784	0.64 (0.54) ^b	125(128) ^c	0.91	−1.28		9, 24
Os[TpCF ₃ PC](N)	444, 554, 593	778	0.7 (0.54) ^b	139(150) ^c	1.02	−1.19		9, 24
Os[T3,5-CF ₃ PC](N)	443, 553, 588	770	0.81	155	1.12	−1.10	−1.62	this work
Au[TPC]	421, 494, 532, 561, 575	792	0.23 (0.18) ^d	94(86) ^d	0.80	−1.38		15
Au[TpCF ₃ PC]	423, 494, 532, 562 (sh), 575	786	0.26 (0.19) ^d	97(98) ^d	0.94	−1.29		15
Au[T3,5-CF ₃ PC]	421, 493, 529, 567	777	0.33	99	1.05	−1.19	−1.62	this work
Au[TPFPC]	415, 491, 527, 561	751	0.68	170	1.18	−1.11	−1.68	this work

^aRef 29; excitation in the Q-band. ^bRef 24; the Φ_{phos} values have been recalculated based on the corrected value (21%) for the standard platinum(II) tetraphenyltetrazinoporphyryr (Pt[TPTBP]).³⁷ ^cRef 24; frequency domain measurement. ^dRef 23.

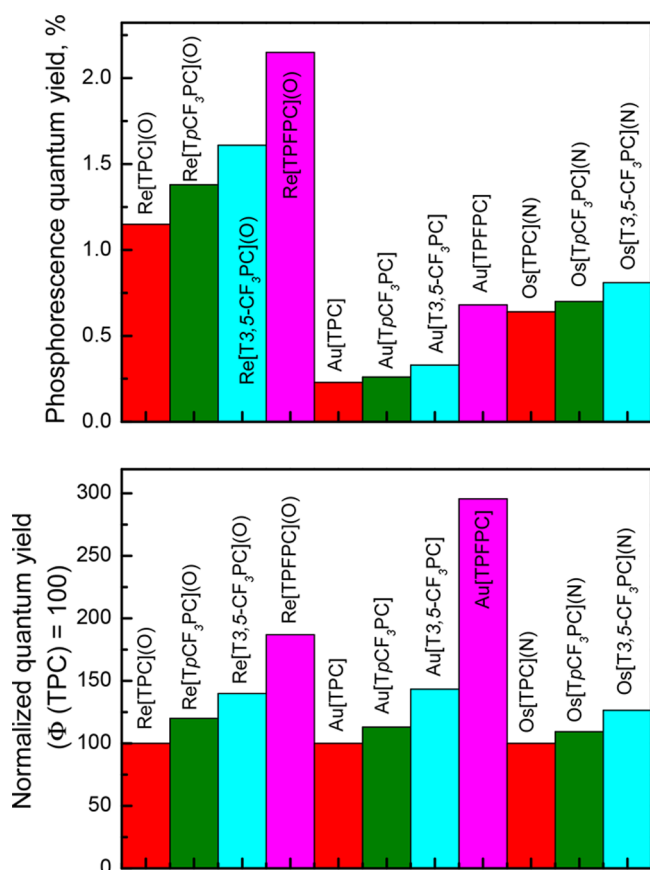


Figure 3. Phosphorescence quantum yields of the ReO, OsN, and Au corroles. The lower plot depicts the enhancement of the quantum yield upon fluorination: the values are normalized for the quantum yields of the TPC complex of each metal; i.e., the Φ_{phos} values of Re[TPC](O), Os[TPC](N), and Au[TPC] are each set as 100%.

compounds. Although the emission spectra of the T3,5-CF₃PC and TPFPC complexes are generally similar to those of the previously studied TPC and TpCF₃PC complexes (which were also remeasured in this study), the emission maxima were found to shift hypsochromically with increasing electron-withdrawing character of the *meso*-aryl substituents; this effect was observed for all three metal series examined.

As shown in Table 1, fluorination results in an increase in both luminescence quantum yields and decay times in the order TPC < TpCF₃PC < T3,5-CF₃PC < TPFPC, which is also the order of the redox potentials (see Figures S9–S13 for selected cyclic voltammograms). Figure 3 presents a graphical representation of the quantum yields for the different complexes. The ReO complexes are by far the strongest emitters, followed by the OsN, and last by the Au (Figure 3, upper panel). Notably, compared with their TPC analogues, the luminescence of Au[TPFPC] is enhanced much more strongly than that of Re[TPFPC](O) (Figure 3, lower panel). Thus, whereas the phosphorescence quantum yield triples on going from Au[TPC] to Au[TPFPC], the enhancement is less than double for their ReO counterparts. As a result of the fluorination-mediated enhancement, Au[TPFPC] emits as efficiently as Os[TPC](N). The trend in the luminescence decay times parallels that observed for the luminescence quantum yields (Table 1). The decay time of Au[TPFPC] is thus much longer (170 μs) than that of the other Au triarylcorroles (94–99 μs). Interestingly, although the

parallelism is far from exact, the present findings appear similar to those of Liu and co-workers, who observed fluorination-induced enhancements of triplet quantum yields for free-base and gallium triarylcorroles.³⁸

The fact that the order of phosphorescence quantum yields parallels the order of redox potentials for each of three series of 5d metalcorroles suggests that the mechanism of enhanced luminescence is largely electronic in origin. However, the *ortho* fluorines in the TPFPC complexes may confer some degree of conformational rigidity, leading to increased triplet lifetimes. Fluorination also has a major impact on solute–solvent interactions, which, in turn, may also affect the luminescence properties. At this point, these potential influences remain to be disentangled, and the striking impact of fluorination is simply presented as an empirical observation.

In conclusion, introduction of fluorinated substituents onto the *meso*-phenyl groups results in enhancement of the luminescence properties of all three series of 5d metalcorroles: ReO, OsN, and Au. Substitution of phenyl groups by pentafluorophenyl groups leads to the highest increase in the luminescence quantum yields and decay times. This enhancement is particularly strong in the case of the Au corroles, where the phosphorescence quantum yield triples on going from Au[TPC] to Au[TPFPC]. An intriguing question concerns whether peripheral fluorination might have a similar positive effect on the luminescence properties of other porphyrin-type complexes such as true porphyrins, carbaporphyrins, hydroporphyrins, and dipyrin derivatives. Time will tell.

ASSOCIATED CONTENT

Data Availability Statement

The data underlying this study are available in the published article and its Supporting Information.

Supporting Information

The Supporting Information is available free of charge at <https://pubs.acs.org/doi/10.1021/acsorginorgau.3c00016>.

Experimental methods, ¹H and ¹⁹F NMR spectra, electrospray ionization mass spectra, optical spectra, and additional photophysical data (PDF)

Accession Codes

CCDC 2247280 contains the supplementary crystallographic data for this paper. These data can be obtained free of charge via www.ccdc.cam.ac.uk/data_request/cif, or by emailing data_request@ccdc.cam.ac.uk, or by contacting The Cambridge Crystallographic Data Centre, 12 Union Road, Cambridge CB2 1EZ, UK; fax: +44 1223 336033.

AUTHOR INFORMATION

Corresponding Authors

Abraham B. Alemayehu – Department of Chemistry, UiT–The Arctic University of Norway, 9037 Tromsø, Norway; orcid.org/0000-0003-0166-8937; Email: abraham.alemayehu@uit.no

Sergey M. Borisov – Institute of Analytical Chemistry and Food Chemistry, Graz University of Technology, 8010 Graz, Austria; orcid.org/0000-0001-9318-8273; Email: sergey.borisov@tugraz.at

Abhik Ghosh – Department of Chemistry, UiT–The Arctic University of Norway, 9037 Tromsø, Norway; orcid.org/0000-0003-1161-6364; Email: abhik.ghosh@uit.no

Authors

Krister Engedal Johannessen – Department of Chemistry, UiT–The Arctic University of Norway, 9037 Tromsø, Norway

Martin Amund Langaas Johansen – Department of Chemistry, UiT–The Arctic University of Norway, 9037 Tromsø, Norway; orcid.org/0000-0002-6329-0514

Rune F. Einrem – Department of Chemistry, UiT–The Arctic University of Norway, 9037 Tromsø, Norway

Laura J. M^cCormick M^cPherson – EPSRC National Crystallography Service, School of Chemistry, University of Southampton, Southampton SO17 1BJ, U.K.; orcid.org/0000-0002-6634-4717

Complete contact information is available at:

<https://pubs.acs.org/10.1021/acsorginorgau.3c00016>

Author Contributions

CRediT: **Krister Engedal Johannessen** data curation (equal), investigation (equal), methodology (equal), writing-original draft (supporting); **Martin Amund Langaas Johansen** investigation (supporting), methodology (supporting), writing-original draft (supporting); **Rune F. Einrem** investigation (supporting), methodology (supporting), writing-original draft (supporting); **Laura J. M^cCormick M^cPherson** investigation (equal), methodology (equal), writing-original draft (supporting); **Abraham B. Alemayehu** formal analysis (lead), investigation (lead), methodology (lead), supervision (lead), writing-original draft (lead); **Abhik Ghosh** conceptualization (lead), formal analysis (lead), project administration (lead), resources (lead), supervision (lead), writing-original draft (lead), writing-review & editing (lead); **Sergey M. Borisov** formal analysis (lead), investigation (lead), methodology (lead), resources (lead), validation (lead), writing-original draft (lead), writing-review & editing (lead).

Notes

The authors declare no competing financial interest.

ACKNOWLEDGMENTS

This work was supported in part by the Research Council of Norway (grant no. 262229 to A.G.). The UK National Crystallography Service, supported by grant no. EP/W02098X/1 from the EPSRC, is also gratefully acknowledged.

REFERENCES

- (1) Alemayehu, A. B.; Thomas, K. E.; Einrem, R. F.; Ghosh, A. The Story of 5d Metalloporphyrins: From Metal–Ligand Misfits to New Building Blocks for Cancer Phototherapeutics. *Acc. Chem. Res.* **2021**, *54*, 3095–3107.
- (2) Ghosh, A. Electronic Structure of Corrole Derivatives: Insights from Molecular Structures, Spectroscopy, Electrochemistry, and Quantum Chemical Calculations. *Chem. Rev.* **2017**, *117*, 3798–3881.
- (3) Nardis, S.; Mandoj, F.; Stefanelli, M.; Paolesse, R. Metal complexes of corrole. *Coord. Chem. Rev.* **2019**, *388*, 360–405.
- (4) Buckley, H. L.; Arnold, J. Recent Developments in Out-of-Plane Metalloporphyrin Chemistry Across the Periodic Table. *Dalton Trans* **2015**, *44*, 30–36.
- (5) Einrem, R. F.; Gagnon, K. J.; Alemayehu, A. B.; Ghosh, A. Metal-Ligand Misfits: Facile Access to Rhenium-Oxo Corroles by Oxidative Metalation. *Chem.—Eur. J.* **2016**, *22*, 517–520.
- (6) Alemayehu, A. B.; Teat, S. J.; Borisov, S. M.; Ghosh, A. Rhenium-Imido Corroles. *Inorg. Chem.* **2020**, *59*, 6382–6389.

(7) Alemayehu, A. B.; Einrem, R. F.; McCormick-McPherson, L. J.; Settineri, N. S.; Ghosh, A. Synthesis and molecular structure of perhalogenated rhenium-oxo corroles. *Sci. Rep.* **2020**, *10*, 19727.

(8) Einrem, R. F.; Jonsson, E. T.; Teat, S. J.; Settineri, N. S.; Alemayehu, A. B.; Ghosh, A. Regioselective formylation of rhenium-oxo and gold corroles: substituent effects on optical spectra and redox potentials. *RSC Adv.* **2021**, *11*, 34086–34094.

(9) Alemayehu, A. B.; Gagnon, K. J.; Terner, J.; Ghosh, A. Oxidative Metalation as a Route to Size-Mismatched Macrocyclic Complexes: Osmium Corroles. *Angew. Chem., Int. Ed.* **2014**, *53*, 14411–14414.

(10) Palmer, J. H.; Day, M. W.; Wilson, A. D.; Henling, L. M.; Gross, Z.; Gray, H. B. *J. Am. Chem. Soc.* **2008**, *130*, 7786–7787.

(11) Alemayehu, A. B.; Vazquez-Lima, H.; Beavers, C. M.; Gagnon, K. J.; Bendix, J.; Ghosh, A. Platinum Corroles. *Chem. Commun.* **2014**, *50*, 11093–11096.

(12) Alemayehu, A. B.; McCormick, L. J.; Gagnon, K. J.; Borisov, S. M.; Ghosh, A. Stable Platinum(IV) Corroles: Synthesis, Molecular Structure, and Room-Temperature Near-IR Phosphorescence. *ACS Omega* **2018**, *3*, 9360–9368.

(13) Alemayehu, A. B.; Ghosh, A. Gold Corroles. *J. Porphyrins Phthalocyanines* **2011**, *15*, 106–110.

(14) Rabinovich, E.; Goldberg, I.; Gross, Z. Gold(I) and Gold(III) Corroles. *Chem.—Eur. J.* **2011**, *17*, 12294–12301.

(15) Thomas, K. E.; Alemayehu, A. B.; Conradi, J.; Beavers, C.; Ghosh, A. Synthesis and Molecular Structure of Gold Triarylcorroles. *Inorg. Chem.* **2011**, *50*, 12844–12851.

(16) Thomas, K. E.; Beavers, C. M.; Ghosh, A. Molecular Structure of a Gold β -Octakis(trifluoromethyl)-meso-triarylcorrole: An 85° Difference in Saddling Dihedral Relative to Copper. *Mol. Phys.* **2012**, *110*, 2439–2444.

(17) Thomas, K. E.; Vazquez-Lima, H.; Fang, Y.; Song, Y.; Gagnon, K. J.; Beavers, C. M.; Kadish, K. M.; Ghosh, A. Ligand Noninnocence in Coinage Metal Corroles: A Silver Knife-Edge. *Chem. - Eur. J.* **2015**, *21*, 16839–16847.

(18) Capar, J.; Zonneveld, J.; Berg, S.; Isaksson, J.; Gagnon, K. J.; Thomas, K. E.; Ghosh, A. Demetalation of Copper Undecaarylcorroles: Molecular Structures of a Free-Base Undecaarylisocorrole and a Gold undecaarylcorrole. *J. Inorg. Biochem.* **2016**, *162*, 146–153.

(19) Sinha, W.; Sommer, M. G.; van der Meer, M.; Plebst, S.; Sarkar, B.; Kar, S. Structural, electrochemical and spectroelectrochemical study on the geometric and electronic structures of [(corrolato)Au^{III}]ⁿ (n = 0, +1, -1) complexes. *Dalton Trans* **2016**, *45*, 2914–2923.

(20) Thomas, K. E.; Gagnon, K. J.; McCormick, L. J.; Ghosh, A. Molecular structure of gold 2,3,7,8,12,13,17,18-octabromo-5,10,15-tris(4'-pentafluorosulfanylphenyl)corrole: Potential insights into the insolubility of gold octabromocorroles. *J. Porphyrins Phthalocyanines* **2018**, *22*, 596–601.

(21) Palmer, J. H.; Durrell, A. C.; Gross, Z.; Winkler, J. R.; Gray, H. B. Near-IR Phosphorescence of Iridium(III) Corroles at Ambient Temperature. *J. Am. Chem. Soc.* **2010**, *132*, 9230–9231.

(22) Sinha, W.; Ravotto, L.; Ceroni, P.; Kar, S. NIR-emissive iridium(III) corrole complexes as efficient singlet oxygen sensitizers. *Dalton Trans* **2015**, *44*, 17767–17773.

(23) Alemayehu, A. B.; Day, N. U.; Mani, T.; Rudine, A. B.; Thomas, K. E.; Gederaas, O. A.; Vinogradov, S. A.; Wamser, C. C.; Ghosh, A. Gold Tris(carboxyphenyl)corroles as Multifunctional Materials: Room Temperature Near-IR Phosphorescence and Applications to Photodynamic Therapy and Dye-Sensitized Solar Cells. *ACS Appl. Mater. Interfaces* **2016**, *8*, 18935–18942.

(24) Borisov, S. M.; Alemayehu, A.; Ghosh, A. Osmium-Nitrido Corroles as NIR Indicators for Oxygen Sensors and Triplet Sensitizers for Organic Upconversion and Singlet Oxygen Generation. *J. Mater. Chem. C* **2016**, *4*, 5822–5828.

(25) Sudhakar, K.; Mizrahi, A.; Kosa, M.; Fridman, N.; Tumanskii, B.; Saphier, M.; Gross, Z. Effect of selective CF₃ substitution on the physical and chemical properties of gold corroles. *Angew. Chem., Int. Ed.* **2017**, *56*, 9837–9841.

(26) Lemon, C. M.; Powers, D. C.; Brothers, P. J.; Nocera, D. G. Gold Corroles as Near-IR Phosphors for Oxygen Sensing. *Inorg. Chem.* **2017**, *56*, 10991–10997.

(27) Teo, R. D.; Hwang, J. Y.; Termini, J.; Gross, Z.; Gray, H. B. Fighting Cancer with Corroles. *Chem. Rev.* **2017**, *117*, 2711–2729.

(28) Alemayehu, A. B.; McCormick, L. J.; Gagnon, K. J.; Borisov, S. M.; Ghosh, A. Stable Platinum(IV) Corroles: Synthesis, Molecular Structure, and Room-Temperature Near-IR Phosphorescence. *ACS Omega* **2018**, *3*, 9360–9368.

(29) Borisov, S. M.; Einrem, R. F.; Alemayehu, A. B.; Ghosh, A. Ambient-temperature near-IR phosphorescence and potential applications of rhenium-oxo corroles. *Photochem. Photobiol. Sci.* **2019**, *18*, 1166–1170.

(30) Thomassen, I. K.; McCormick-McPherson, L. J.; Borisov, S. M.; Ghosh, A. Iridium Corroles Exhibit Weak Near-Infrared Phosphorescence but Efficiently Sensitize Singlet Oxygen Formation. *Sci. Rep.* **2020**, *10*, 7551.

(31) Lemon, C. M. Corrole photochemistry. *Pure Appl. Chem.* **2020**, *92*, 1901–1919.

(32) Higashino, T.; Kurumisawa, Y.; Alemayehu, A. B.; Einrem, R. F.; Sahu, D.; Packwood, D.; Kato, K.; Yamakata, A.; Ghosh, A.; Imahori, H. Heavy Metal Effects on the Photovoltaic Properties of Metallocorroles in Dye-Sensitized Solar Cells. *ACS Appl. Energy Mater.* **2020**, *3*, 12460–12467.

(33) Einrem, R. F.; Alemayehu, A. B.; Borisov, S. M.; Ghosh, A.; Gederaas, O. A. Amphiphilic Rhenium-Oxo Corroles as a New Class of Sensitizers for Photodynamic Therapy. *ACS omega* **2020**, *5*, 10596–10601.

(34) Kadish, K. M.; Araullo-McAdams, C.; Han, B. C.; Franzen, M. M. Syntheses and Spectroscopic Characterization of (T(*p*-Me₂N)-F₄PP)H₂ and (T(*p*-Me₂N)F₄PP)M Where T(*p*-Me₂N)F₄PP Is the Dianion of *meso*-Tetrakis(*o,o,m,m*-tetrafluoro-*p*-(dimethylamino)-phenyl)porphyrin and M = Co(II), Cu(II), or Ni(II). Structures of (T(*p*-Me₂N)F₄PP)Co and {*meso*-Tetrakis(pentafluorophenyl)-porphinato)cobalt(II)}, (TFSPP)Co. *J. Am. Chem. Soc.* **1990**, *112*, 8364–8368.

(35) Battioni, P.; Brigaud, O.; Desvaux, H.; Mansuy, D.; Traylor, T. G. Preparation of functionalized polyhalogenated tetraaryl-porphyrins by selective substitution of the *p*-fluorines of *meso*-tetra-(pentafluorophenyl)porphyrins. *Tetrahedron Lett.* **1991**, *32*, 2893–2896.

(36) Hori, T.; Osuka, A. Nucleophilic Substitution Reactions of *meso*-5,10,15-Tris(pentafluorophenyl)-corrole; Synthesis of ABC-Type Corroles and Corrole-Based Organogels. *Eur. J. Org. Chem.* **2010**, *2010*, 2379–2386.

(37) Zach, P. W.; Freunberger, S. A.; Klimant, I.; Borisov, S. M. Electron-Deficient Near-Infrared Pt(II) and Pd(II) Benzoporphyrins with Dual Phosphorescence and Unusually Efficient Thermally Activated Delayed Fluorescence: First Demonstration of Simultaneous Oxygen and Temperature Sensing with a Single Emitter. *ACS Appl. Mater. Interfaces* **2017**, *9*, 38008–38023.

(38) Shao, W.; Wang, H.; He, S.; Shi, L.; Peng, K.; Lin, Y.; Zhang, L.; Ji, L.; Liu, H. Photophysical properties and singlet oxygen generation of three sets of halogenated corroles. *J. Phys. Chem. B* **2012**, *116*, 14228–14234.

Recommended by ACS

Impact of Electron-Withdrawing Effect on Sigma Hole Via Bromine-Based Interactions in Zn-5,10,15,20-tetra(4-bromo-2,6-difluoro Phenyl) Porphyrin

Goutam Nandi, Bharat Kumar Tripuramallu, *et al.*

JULY 10, 2023
CRYSTAL GROWTH & DESIGN

READ 

Large Steric Substituent-Entangled Luminescence Enhancement under High Pressure

Jun Han, Jinlong Zhu, *et al.*

AUGUST 02, 2023
THE JOURNAL OF PHYSICAL CHEMISTRY C

READ 

Design, Synthesis, and Density Functional Theory Studies of Indole Hydrazones as Colorimetric “Naked Eye” Sensors for F Ions

Rima D. Alharthy, Zahid Shafiq, *et al.*

APRIL 07, 2023
ACS OMEGA

READ 

Fluorinated Antimony(V) Tetraarylporphyrins as High-Valent Electron Acceptors with Unparalleled Reduction Potentials

Noah Holzer, Prashanth K. Poddutoori, *et al.*

APRIL 26, 2023
INORGANIC CHEMISTRY

READ 

Get More Suggestions >